



# **iJRASET**

International Journal For Research in  
Applied Science and Engineering Technology



---

# **INTERNATIONAL JOURNAL FOR RESEARCH**

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

---

**Volume: 5**

**Issue: V**

**Month of publication: May 2017**

**DOI:**

**[www.ijraset.com](http://www.ijraset.com)**

**Call: ☎ 08813907089**

**E-mail ID: [ijraset@gmail.com](mailto:ijraset@gmail.com)**

# **Compare the Peat Soil Stabilization Using Gypsum and Quick Lime With Fly Ash**

K.Vasu<sup>1</sup>, M. Dinesh<sup>2</sup>, V. John Sundar Raj<sup>3</sup>

<sup>1,2,3</sup>Assistant Professor, Civil and Structural Engineering, SCSVMV University, Kanchipuram – 631561

**Abstract:** These paper demonstrate the comparative study on peat soil stabilization with different stabilizing agents. Peat soil are highly organic content and well known for high compressibility, natural wetness content, dumpy shear strength and long term settlement. In this study, the peat soil is collected and to evaluate their index or physical and geotechnical properties. Some combination of gypsum and quick lime with fly ash is added for stabilizers. The amount of fly ash with gypsum and fly ash with quick lime were added to the peat soil sample, as a percentage of dry sample mass, were in the range 5 to 30% and 2 to 8%, respectively for a curing period of 7,14 and 28 days. The Unconfined compressive strength (UCS) test was carried out on stabilized soil samples with above mentioned percentages and compare the results of stabilizing agents shows the UCS value increases significantly with increasing all stabilization agents used and also with increasing curing periods.

**Keywords:** Peatsoil, gypsum, Flyash(FA), Quicklime(QL), Unconfinedcompressivestrength(UCS), stabilization.

## **I. INTRODUCTION**

Peat is generally defined as a soil which has build up partially decomposed plant and animal deposit under anaerobic conditions. Peat soil is well known for their very low shear strength and high compressibility characteristics. For this reason, these soil cause serious foundation problems and constitute one of the most difficult ground condition for the construction of civil engineering structure. The settlement characteristic associated with peat is very complex due to the high compressibility and mainly large secondary consolidation compression characteristic i.e., creep effect of the peat soil.

A number of researchers have tried to improve constructability on soft soil. The available methods are displacement method, replacement method, stage loading and surface reinforcement method, pile supported embankment, light weight fill raft method, deep-in-situ chemical stabilization method and Thermal precompression method to improve soft or peat soil. However, these methods have high financial cost. Out of several alternatives, one of the promising methods of construction on the peat soil is to stabilize the peat soil itself by appropriate stabilizer. Soil stabilization can be defined as a mean of permanently altering soil properties to increase its strength and bearing capacity, and decrease its water sensitivity and volume change potential.

There are many types of admixtures such as gypsum, quick lime, fly ash etc, available to stabilize the soft or peat soil. Hence, the present learn concentrates on comparison of the stabilization of peat soil samples with different types of stabilizers or admixtures i.e., combination of gypsum with flyash and combination of quick lime with fly ash. Finding the most suitable stabilizer and optimum mixing quantity for stabilizing the local peat soil are final outcomes of the study.

## **II. PHYSICAL PROPERTIES OF PEAT**

The natural moisture content of peat soil samples have been determined by drying soil sample in an oven at 105°C for 24 hours as per BS 1377: Part 2: 1990. The Loss on Ignition test has been determined as a percentage of oven-dried mass as per ASTM D 2974. Organic content (H) is calculated according to an equation proposed by Skempton and Petley as follows:

$$H\% = 100 - C(100 - N)$$

Where, C is the correction factor and N is the Loss On

Ignition in percent. The degree of decomposition is generally assessed by means of the Von Post scale. There are 10 degrees of humification (H1 to H10) in the Von Post system. The specific gravity ( $G_s$ ) of the highly organic or peat soil is determined based on procedure stated in BS 1377: Part 2:1990. In this test,  $G_s$  is determined by using small pycnometer. The average  $G_s$  is obtained from the results of three tests. The fiber content (FC) is determined from dry weight of fibers retained on ASTM D 1997-91 sieve no. 100 (> 0.15 mm opening size) as a percentage of oven dried mass. The particle size distribution of the peat soil samples were conducted by sieve analysis according to the method described in ASTM D 422-63. In this study, cone penetrometer method has been used to determine the liquid limit (LL) of peat soil sample. peat is the product of decomposition of

## International Journal for Research in Applied Science & Engineering Technology (IJRASET)

organic matter from plants and animals. It has the capacity of taking up and holding water.

High water content results in high pore volume leading to low bulk density and low bearing capacity. Voids ratio is an indicator for the compressibility of the material. Voids ratio of organic soils are generally higher than the inorganic soils. The higher specific gravity indicates a higher degree of decomposition and low mineral content. An easier method of determining specific gravity is to use ash content. The unit weight is influenced by the water content and organic content of peat. Unit weight will increase with increment of specific gravity. Unit weight of peat is typically lower compared to inorganic soils. Peat will sink extensively when dried.

### III. ENGINEERING PROPERTIES OF PEAT

The shear strength of peat soil is very low, however, the strength could increase significantly consolidation shear strength is associated with several variables such as the origin of soil, water content, organic content, and degree of decomposition. The shear strength of peat is determined based on drained condition. Considering the presence of peat soil is always below the groundwater level, the determination of undrained shear strength is also important. The compression behavior of fibrous peat is different from clay soil. Initial compression occurs instantaneously after the load being applied, the primary and secondary compression are time dependent. Permeability is one of the important properties of peat because it controls the rate of consolidation and increase in the shear strength of the soil.

### IV. METHODOLOGY

Physical properties such as moisture content, specific gravity, particle size and liquid limit are determined to establish the basic characteristics of peat soil. Peat soil are classified based on von Post scale for degree of decomposition, fibre content, loss of ignition and organic content. Engineering properties such as standard proctor test and unconfined test as also been studied.

The soil sample is collected, approximately at the depth of 0.5m to 1m, at first sundried followed by grinding and sieving. The soil particles pass through 1.18mm sieves are collected to conduct different test with different percentage of admixtures. The procedure for conducting the experimental investigation based on British standard BS 1377:1990 and ASTM standards. The tests on different portion of Fly ash with gypsum and fly ash with quick lime are designed to obtain the most appropriate proportion of stabilizer that will improve the peat soil sample most in terms of strength and other physical and engineering properties. Test on original peat soil alone also been conducted in order to assess the improvement made on the peat soil samples.

After obtaining the value of maximum dry density and optimum moisture content of the sample from standard proctor test, the specimens were tested using stabilized agents

such as gypsum of 2, 4, 6 and 8%, and fly ash of 5, 10, 20 and 30% of dry weight of the sample, and compare the stabilization with another sample with quick lime of 2, 4, 6 and 8%, and fly ash of 5, 10, 20 and 30% of dry weight of the samples. To prepare the cylindrical sample for UCS test, using a mould of 50mm diameter and 100mm height. After sample preparation, the sample has been kept for approximately 24 hours before it being immersed in the water tank for curing. The unconfined compressive strength test were conducted after curing period 7, 14 and 28 days to investigate the strength of treated soil.

### V. RESULTS AND DISCUSSION

#### A. Physical Properties

The results of different physical properties of the peat soil samples are presented in Table 1. From the laboratory test, it has been observed that samples fall in the category with degree of humification of H4 respectively, according to the Von Post scale (1922). In this study samples contain more than 75% OC and can be categorized as peat. Loss of ignition test has been conducted on the samples. From Table 1 it can be observed that the sample has very high value of loss of ignition and organic content. The value of liquid limit is high because the sample contains a lot of fibre which results in high water absorption capacity. The result also shows that sample has lower pH value i.e., more acidic due to higher organic content.

Table 1: Physical and geotechnical properties of soil.

Properties	Results
Natural moisture content, (%)	620.14
Degree of decomposition	H3
Loss on Ignition, (N) (%)	85.67
Organic content, (H) (%)	85.67

## International Journal for Research in Applied Science & Engineering Technology (IJRASET)

Specific gravity, ( $G_s$ )	1.45
Fiber content (FC) (%)	65.00
Liquid Limit (LL) (%)	78.00
Maximum Dry Density, MMD, (gm/cc)	0.56
Optimum Moisture Content, OMC (%)	95.17

### B. Unconfined Compressive Strength

Unconfined compressive strength (UCS) test was performed on the cured peat soil sample with the different percentages of stabilizers and the results are presented in the figure 1,2,3,4,5 and 6. UCS is the most common test used to determine the stabilizer of the soil. For each UCS test, the stress-strain relationship was determined. The sample was mixed with various percentages of gypsum (2%, 4%, 6% and 8%) with fly ash (5%, 10%, 20% and 30%). Figure 1, 2 and 3 shows the gain in UCS with combination of gypsum and fly ash. The sample was mixed with another admixture of Quick lime (2%, 4%, 6% and 8%) with fly ash (5%, 10%, 20% and 30%). Figure 4, 5 and 6 show the gain in UCS with combination of quick lime and fly ash added to peat soil with different curing periods. Compare the strength of admixtures.

In general, the compressive strength value indicates that all admixture treatment types resulted in strength gain. It can be noticed that the strength of treated soil increased with curing time. Most of the strength gain occurred within the first seven days curing. The results show the higher strength achieved for the sample mixed with gypsum and fly ash. The UCS value increases with combination of gypsum and fly ash and also with curing period of 28 days but decreases (UCS value of 20% FA plus 6% gypsum) after adding of 20% of FA and 6% of gypsum.

The UCS value increases with the increased combination of QL and FA, and also with a curing period of 28 days but decreases (UCS value of 10% FA plus 6% QL) after addition of 10% FA and 6% QL. It can be observed that, comparison of the Unconfined Compressive Strength (UCS) increases with the increasing of 20% percentage of FA and 6% of gypsum content added to the original peat soil sample and also with the curing period but decreases rather steadily beyond this percentage. But in the case of Flyash and QL, this result increases up to addition of 10% FA and 6% of QL, with a curing period of 28 days but decreases rather steadily beyond this percentage.

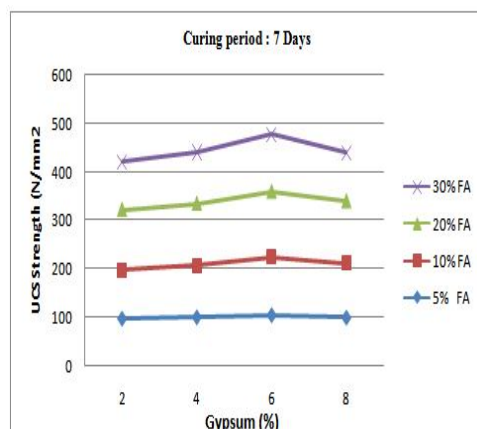


Fig- 1

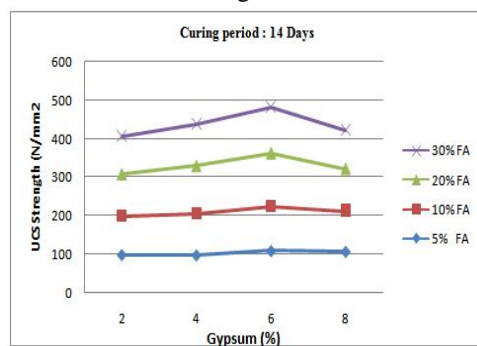


Fig- 2



# International Journal for Research in Applied Science & Engineering Technology (IJRASET)

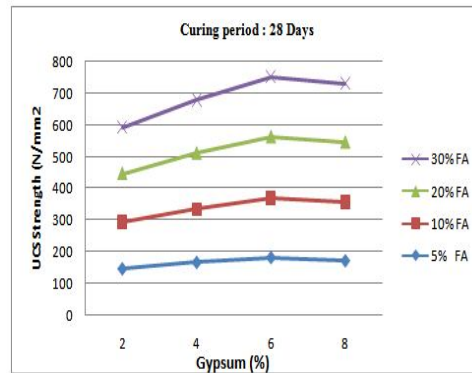


Fig- 3

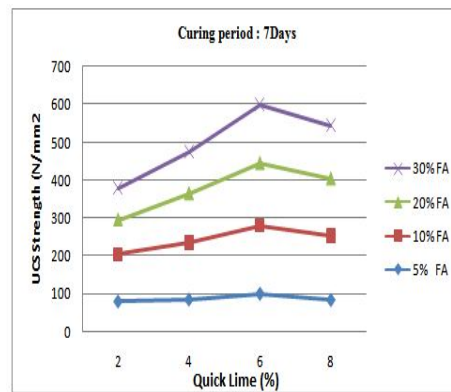


Fig- 4

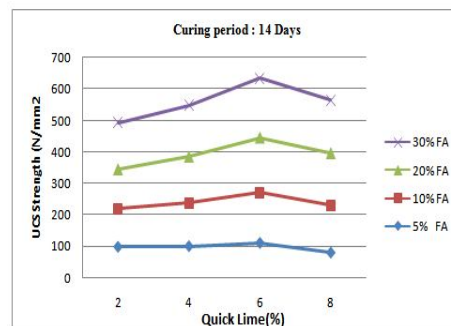


Fig- 5

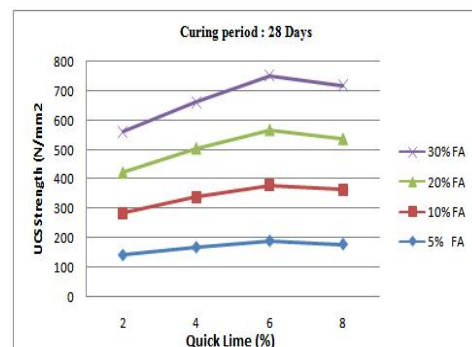


Fig- 6

## International Journal for Research in Applied Science & Engineering Technology (IJRASET)

### VI. CONCLUSION

The present paper investigates the effect of different types of stabilizer on peat soil samples. From the laboratory tests results, the following conclusions can be drawn:

- A. The result of UCS test for combined FA and gypsum shows better results in comparison with the combination of FA and QL.
- B. The stabilized peat soil sample increases with the increase of percentage of FA (i.e., 5,10, 20 and 30%) and gypsum (2%,4%,6% and 8%) added to the original peat sample.
- C. The UCS values for peat soil samples increase with 2, 4,6 and 8% of gypsum and 5,10,20 and 30% of FA but decrease rather steadily beyond 6% of gypsum and 20% FA added.
- D. The result of UCS test increases with curing period (i.e.,7, 14 and 28 days) for all types of stabilizer used.
- E. The UCS value for combined QL and FA shows with a reduction of gypsum and flyash because it decreases progressively beyond 6% QL and 10% of FA.
- F. In the present study, the comparison of gypsum with fly ash and quick lime with fly ash, the gypsum with fly ash is the most suitable stabilizer.

### REFERENCES

- [1] Ahnberg H., Hol G., Holmquist L. and Ljungkrantz C. (1994). "The Use of Different Additives in Deep Stabilization of Soft Soils", Proc. 13<sup>th</sup> Int. Conf. Soil Mech. and Foundation Engineering, New Delhi, India, 3:1191–1194.
- [2] Andersson R., Johansson S.E. and Axelsson K.G. (2002). "Stabilization of Organic Soils by Cement and Pozzolanic Reactions", A feasibility study within the project Swedish deep stabilization, Report 3
- [3] Andrew D.C. (1966). "Lime Soil Stabilization", Ph.D. thesis, University of Leeds, UK.
- [4] ASTM D 2166 (2000). "Standard Test Method for Unconfined Compressive Strength of Cohesive Soil", Annual Book of ASTM Standards, ASTM, Philadelphia, USA.
- [5] ASTM D 2974 (2000). "Standard Test Method for Moisture, Ash, and Organic Matter of Peat and other Organic Soils", Annual Book of ASTM Standards, ASTM, Philadelphia, USA
- [6] ASTM D 422 63 (1994). "Standard Test Method for Particle Size Analysis of Soils", Annual Book of ASTM Standards, ASTM, Philadelphia, USA, 04.08:10–16
- [7] ASTM D1997-91(1996). "Standard Test Method for Laboratory Determination of the Fiber Content of Peat Samples by Dry Mass", Annual Book of ASTM Standards, ASTM, Philadelphia, USA
- [8] Axelsson K., Johansson S.E. and Anderson R. (2002). "Stabilization of Organic Soils by Cement and Pozzolanic Reactions-feasibility Study", Swedish deep stabilization Research Centre, Report 3, English translation, 15–16.
- [9] Balasubramaniam A.S., Kamruzzaman A.H.M., Uddin K., Lin D.G., Phienwij N. and Bergado D.T. (1998). "Chemical Stabilization of Bangkok Clay with Cement, Lime and Flyash Additives", 13th Southeast Asian Geotechnical Conference, 253–258



10.22214/IJRASET



45.98



IMPACT FACTOR:  
7.129



IMPACT FACTOR:  
7.429



# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089  (24\*7 Support on Whatsapp)