



IJRASET

International Journal For Research in
Applied Science and Engineering Technology



INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Volume: 14 **Issue:** VI **Month of publication:** June 2026

DOI: <https://doi.org/10.22214/ijraset.2026.83590>

www.ijraset.com

Call:  08813907089

E-mail ID: ijraset@gmail.com

An Investigation on Medium Grade Concrete Impregnated with Polypropylene Fiber and Sugarcane Bagasse Ash with PPC

Md Afroz Safdar, Dr.Hemant Sood

PG Scholar, Construction Technology and Management, NITTTR, Chandigarh, India

Professor, Department of Civil Engineering, NITTTR, Chandigarh, India

Abstract: The construction industry is increasingly focusing on sustainable materials to reduce the environmental impact associated with cement production. Sugarcane Bagasse Ash (SCBA), an agricultural waste generated from sugar industries, possesses pozzolanic characteristics and can be utilized as a partial replacement of cement. Polypropylene Fiber (PPF) is known for improving tensile strength, crack resistance, and durability of concrete. This study investigates the combined effect of SCBA and PPF on M40 grade concrete prepared using Portland Pozzolana Cement (PPC). SCBA was used as a partial replacement of cement at 5% and 8%, while polypropylene fibers were incorporated at 0.5%, 1.0%, and 1.5% by volume. The experimental program included slump test, compressive strength test, split tensile strength test, and permeability test. Results indicated that the mix containing 5% SCBA and 1.0% polypropylene fiber exhibited optimum performance with a maximum compressive strength of 47 MPa at 28 days. The incorporation of SCBA and PPF improved mechanical properties and reduced permeability, thereby enhancing durability. The study demonstrates the feasibility of utilizing agricultural waste and synthetic fibers to produce sustainable and high-performance concrete.

Keywords: Sugarcane Bagasse Ash, Polypropylene Fiber, M40 Concrete, PPC, Compressive Strength, Split Tensile Strength, Permeability.

I. INTRODUCTION

Concrete is the most widely used construction material due to its versatility, durability, and economic advantages. However, cement manufacturing contributes significantly to greenhouse gas emissions. Therefore, the utilization of supplementary cementitious materials has become essential for sustainable construction. Sugarcane Bagasse Ash (SCBA) is a by-product obtained after burning sugarcane bagasse. Due to its high silica content (approximately 75.2%), it exhibits pozzolanic behavior and contributes to strength development in concrete. Polypropylene Fiber (PPF) is a synthetic fiber that improves crack resistance, toughness, and tensile properties of concrete. The combined utilization of SCBA and PPF can improve the performance of concrete while reducing environmental impact.

A fiber reinforced concrete enhances the compressive stress, strain and flexure and split tensile strength of concrete also acting as crack arrestor and reduce the propagation of cracks in concrete.

Fiber-reinforced concrete (FRC) that includes **bagasse ash**, a by-product of sugarcane processing, combines the advantages of both fiber reinforcement and the pozzolanic properties of bagasse ash.

This combination enhances the mechanical, durability, and environmental properties of concrete.

II. LITERATURE SURVEY

Several researchers have investigated the effects of polypropylene fibers and sugarcane bagasse ash on concrete properties.

- 1) Salahuddin Alsace and Mohsen Salem reported that polypropylene fibers increased compressive strength by 4–12%, with optimum performance at 2% fiber dosage.
- 2) Nishant Kumar and Ashutosh Sahu observed improvement in compressive and flexural strengths with increasing fiber content, although workability decreased.
- 3) Shruthi H.R. et al. found that 10% SCBA replacement produced maximum compressive strength.
- 4) R. Srinivasan reported that SCBA replacement up to 10% significantly improved compressive and tensile strength.

Research Gap

Most previous studies investigated SCBA and polypropylene fibers separately. Limited research is available on the combined influence of SCBA and polypropylene fibers on M40 grade concrete prepared using PPC.

III. OBJECTIVE OF THE WORK

To study the combined effect of SCBA and polypropylene fibers on M40 concrete and evaluate compressive and split tensile strength characteristics.

IV. METHODOLOGY

The methodology used regarding the work is as follows:

- 1) Identification and specification of material to be selected.
- 2) Collect and identify the properties of collected materials. Various tests were conducted on cement, fine aggregate, coarse aggregate.
- 3) Preparation of mix design of M40 grade concrete. 6) Cubes and cylinders were casted with control mix using natural aggregate.
- 4) Preparation of test specimens by adding 0.5, 1, 1.5% of polypropylene fibers in concrete mix with SCBA of 5% and 8%.
- 5) Workability tests, compressive strength, tensile strength of concrete were conducted.
- 6) Optimum percentage of fibre addition in concrete was determined.

V. MATERIAL TEST

Table-1: Material Testing Results

Test	Material	Equipment used	Values obtained
Specific gravity	PPC	Density Bottle	3.141
Initial setting time	PPC	Vicat apparatus	85 mins
Final setting time	PPC	Vicat apparatus	420 mins
Specific gravity	Fine aggregate	Pycnometer	2.348
Specific gravity	Coarse aggregate	Pycnometer	2.94
Water absorption	Coarse aggregate	Oven Dry Method	2.354 %
Workability	M340 Concrete	Slump cone apparatus	100mm

VI. MIX DESIGN

Table-2: M40 Mix Proportioning

Cement (Kg/m ³)	450
Fine aggregate (Kg/m ³)	580.14
Coarse aggregate (Kg/m ³)	1290.5
	9
Water (li/m ³)	164.96
Water cement ratio	0.37

Mix ratio 1:1.28:2.80:0.37

VII. EXPERIMENTAL INVESTIGATION

A. Test Procedure

For concrete test specimens consist of 150x150x150mm cubes and Cylinders of 150mm diameter and 300mm height . Compressive strength was obtain on the basis of concrete cube specimen tested at 7 and 28 and for split tensile strength cylindrical specimens were tested at 28 day.

B. Test on fresh concrete

On fresh concrete, workability test apply to check the affects of concrete strength and durability as well as the appearance of the finished product. For easily placed and well compacted in homogeneously without bleeding and segregation concrete is to be well workable. In this work the workability of concrete is measured by slump test.

C. Test on hardened concrete

To ensure the design strength of hardened concrete various test is to be done and quality of concrete construction is achieved. It includes compressive strength test, flexural tensile strength test, split tensile strength test and modulus of elasticity.

VIII. EXPERIMENTAL RESULTS AND DISCUSSION


A. Optimization of polypropylene fiber in concrete

In this section polypropylene fiber and sugarcane bagasse ash of different percentage added in concrete.

Table-3: Mean Compressive Strength test result

Mix	% of SCBA	% of PP Fiber	Mean Compressive Strength (MPa)	
			7 Days	28 Days
Mix1	5	0.5	32.0	45.0
Mix2	5	1	33.5	47.0
Mix3	5	1.5	30.5	43.0
Mix4	8	0.5	29.5	42.0
Mix5	8	1	31.0	44.0
Mix6	8	1.5	28.0	40.5

Fig 1: Mean Compressive Strength test result

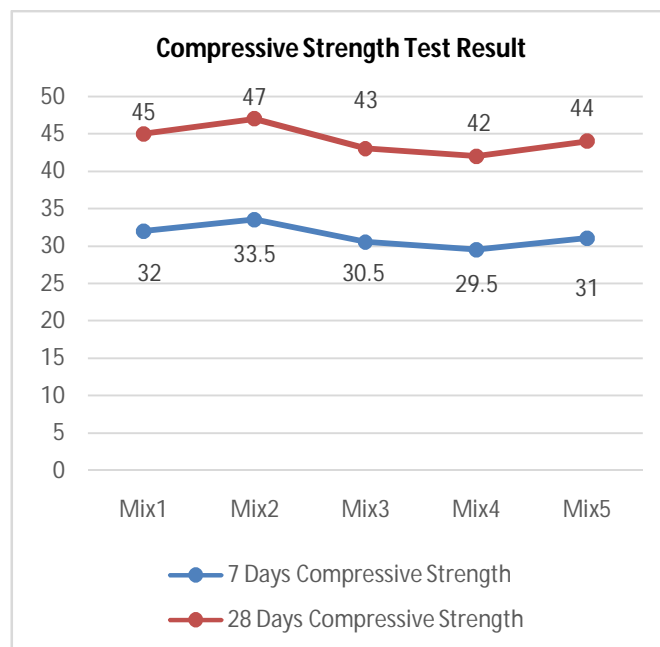


The above result show the maximum compressive strength is 47MPa at 28 days and 33.5Mpa at 7 days, which is Mix2. Compressive strength increases at 5% replacement of sugarcane bagasse ash with PPC in addition of mix with 1% of polypropylene fiber increase the bonding characteristics of concrete. On increase of sugarcane bagasse ash at 8%, the strength get decrease on addition of same percentage of polypropylene fiber.

Table-4: Mean Split tensile Strength test result

Mix	% of SCBA	% of PP Fiber	Mean Split Tensile Strength (MPa)	
			7 Days	28 Days
Mix1	5	0.5	3.4	4.5
Mix2	5	1	3.7	4.8
Mix3	5	1.5	3.5	4.6
Mix4	8	0.5	3.2	4.2
Mix5	8	1	3.5	4.5
Mix6	8	1.5	3.3	4.3

Fig 2: Mean Split Tensile Strength test result

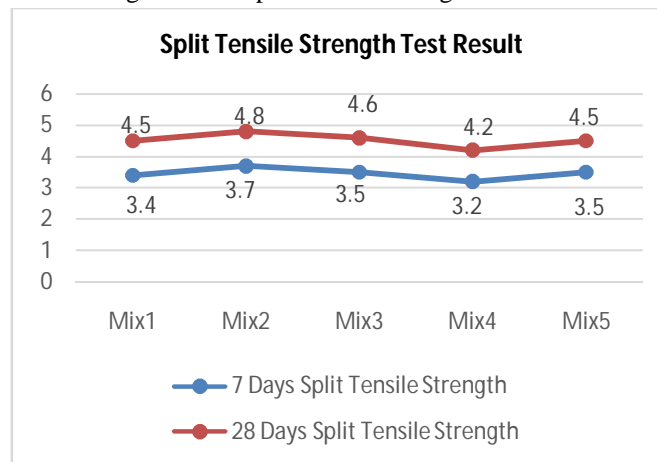

The above result show the maximum split tensile strength is 4.8MPa at 28 days and 3.7MPa at 7 days, which is Mix2. Split tensile strength increases at 5% replacement of sugarcane bagasse ash with PPC in addition of mix with 1% of polypropylene fiber increase the bonding characteristics of concrete. On increase of sugarcane bagasse ash at 8%, the strength get decrease on addition of same percentage of polypropylene fiber.

Permeability test result for all mix sample is as follow:

Table-5 Permeability Test Result After 28 days

Mix	SCBA (%)	PPF (%)	Depth of Penetration (mm)	Coefficient of Permeability ($\times 10^{-12}$ m/s)
Mix1	5	0.5	21	4.3
Mix2	5	1.0	18	3.8
Mix3	5	1.5	20	4.2
Mix4	8	0.5	18	3.6
Mix5	8	1.0	15	3.1
Mix6	8	1.5	17	3.5

The optimum mix was found that at 8% SCBA with 1.0% PPF, which produced the lowest water penetration depth and permeability coefficient, indicating a highly dense and durable concrete matrix.

IX. CONCLUSIONS

- 1) Based on the experimental results, 5% replacement of PPC cement with Sugarcane Bagasse Ash (SCBA) and 1.0% Polypropylene Fiber (PPF) is recommended for M40 grade concrete, as it provided the best overall mechanical performance.
- 2) The optimum mix achieved a 28-day compressive strength of 47 MPa and a split tensile strength of 4.8 MPa, indicating its suitability for structural concrete applications requiring enhanced strength and crack resistance.
- 3) The use of SCBA and PPF is recommended as a sustainable alternative in concrete production, as it reduces cement consumption and promotes the utilization of agricultural waste materials.

X. SCOPE OF FUTURE STUDY

Research can be extended to study the behavior under elevated temperatures and fire resistance, especially due to the presence of polypropylene fibers.

The use of chemical admixtures (superplasticizers, nano-materials like nano-silica) can be explored to further enhance workability and reduce permeability.

Advanced microstructural analysis using SEM, XRD, and FTIR techniques can be carried out to better understand pore refinement and bonding mechanisms.

The effect of curing methods (steam curing, self-curing, and accelerated curing) on permeability and microstructure of SCBA–fiber concrete can be studied.

Investigation on the flexural and shear crack pattern of fiber reinforced concrete. Comparative study on blended type, micro and macro length polypropylene fibers.

REFERENCES

- [1] Nili, M. Biglarijoo, N. Mirbagheri, S.A. A Review On The Use Of Various Kinds Of Debris And Demolitions In Concrete And Mortar Mixes. 10th International Congress On Advances In Civil Engineering. 17-19 October 2012 Middle East Technical University, Ankara, Turkey.
- [2] Sai Samanth, A, Prakhar. Study Of Strength Properties Of Concrete With Construction Debris As Aggregates. International Journal Of Engineering Research In Mechanical And Civil Engineering. 1(5), 2016, Pp 42-45.
- [3] Kumar, N.S.T. Siva, C. Use Of Construction Renovation And Demolition Waste In Partial Replacement Of Coarse Aggregate In M20 Concrete. International Journal Of Research In Engineering And Technology. 4(10), 2015, Pp 375-378.
- [4] Muthu Lakshmi, S. Nivedhitha, R.R. Effect Of Partial Replacement Of Aggregates By Recycled Concrete Debris On Strength Of Concrete. Malaysian Journal Of Civil Engineering. 27(2), 2015, Pp 250-259.
- [5] IS 456(2000): Plain And Reinforced Concrete - Code Of Practice.
- [6] IS 383 (2016): Specification For Coarse And Fine Aggregates From Natural Sources For Concrete.
- [7] IS 2386-3(1963): Methods Of Test For Aggregates For Concrete, Part 3: Specific Gravity, Density, Voids, Absorption And Bulking.
- [8] IS 10262(2009): Guidelines For Concrete Mix Design Proportioning.
- [9] IS 516(1959): Method Of Tests For Strength Of Concrete.
- [10] IS 7320-1974... Specification For Concrete Slump Test Apparatus.
- [11] I.S: 2386-1963, Methods Of Test For Aggregates For Concrete - Part 3: Specific Gravity, Density, Voids, Absorption And Bulking, Bureau Of Indian Standard, New Delhi.
- [12] I.S: 1199-1959, Indian Standard Methods Of Sampling And Analysis Of Concrete. Bureau Of Indian Standards, New Delhi



10.22214/IJRASET



45.98



IMPACT FACTOR:
7.129



IMPACT FACTOR:
7.429



INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089  (24*7 Support on Whatsapp)