



# IJRASET

International Journal For Research in  
Applied Science and Engineering Technology



# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

**Volume:** 10    **Issue:** II    **Month of publication:** February 2022

**DOI:** <https://doi.org/10.22214/ijraset.2022.40541>

**[www.ijraset.com](http://www.ijraset.com)**

**Call:** ☎ 08813907089

**E-mail ID:** [ijraset@gmail.com](mailto:ijraset@gmail.com)

# Fabrication and Depiction of Reinforced Human Hair Polymer Matrix Composites

Shweta Suthar<sup>1</sup>, Dr. Dinesh Kumar<sup>2</sup>

<sup>1</sup> Research Scholar, <sup>2</sup> Professor, Department of Mechanical Engineering, Jan Nayak Chaudhary Devi Lal Memorial College of Engineering, Sirsa

**Abstract:** In recent years, the use of fiber reinforced polymer composites in variety of applications play a major role due to their attractive properties such as light weight, fatigue resistance, easy moldability, high specific strength and modulus. Earlier researchers in past studies have shown that synthetic fiber reinforced polymer composites obtained a better mechanical properties but the applications are restricted to less because of high procurement and manufacturing cost and more weight. To overcome these, nowadays light weight natural fiber reinforced polymer composites are very widely used in the field of automobile, Aerospace, Marine, and Furniture's applications because of their recyclability, easy availability and low cost of materials and production. Human hair is a versatile material identified with a significant potential in the use of reinforcement in composites due to its excellent material properties.

The present work concentrates on the fabrication and study of various physical, mechanical and thermal properties of natural fiber reinforced thermo-set polymer matrix composites. The fabrication was done for eight different types of new set of natural fiber polymer composites which consist of human hair as reinforcement, Epoxy and Vinylester as the resin with four different set of fiber volume fractions (70:30, 75:25, 80:20, 85:15 ratio of matrix and fiber respectively) using hand layup technique. Then the samples were prepared according to ASTM standard for testing mechanical properties such as Impact Energy, Rockwell Hardness and physical properties such as Density and water absorption. Theoretical density of composites was determined for validating actual density of fabricated composites. Rockwell Hardness was measured on both dry and water absorbed composite samples. Internal structure between fiber and matrix was analyzed by using Scanning Electron Microscope (SEM).

**Keywords:** Composites, Fiber reinforced polymer, Fabrication process, Hard Facing Electrodes, Hand Layup Technique, Scanning Electron Microscope.

## I. INTRODUCTION

A composite material can be defined as a combination of two or more materials that results in improved mechanical and thermal properties than the individual components. The reinforcement and matrix are the two constituents of composites. The reinforcing phase provides the strength and stiffness. In most cases, the reinforcement is harder, stronger, and stiffer. The continuous phase is the matrix, which is a polymer, metal, or ceramic. Polymers have low strength and stiffness, metals have intermediate strength and stiffness but high ductility, and ceramics have high strength and stiffness but are brittle. The matrix (continuous phase) performs several critical functions, including maintaining the fibers in the proper orientation and spacing and protecting them from abrasion and the environment.

## II. MANUFACTURING METHODS OF COMPOSITES

Construction processes are those used to bring various forms of fiber and fabric reinforcement together to produce the reinforcement pattern desired for a given composite part or end item. Construction processes include both manual and automated methods of fiber placement, as well as adhesive bonding and sandwich construction. Manufacturing of composites can be broken down into the following categories:

- 1) **Open Mold Process:** Some of the original FRP manual procedures for laying resins and fibers onto forms. Family of FRP shaping processes that use a single positive or negative mold surface to produce laminated FRP structures. The starting materials (resins, fibers, mats, and woven roving's) are applied to the mold in layers, building up to the desired thickness. This is followed by curing and part removal.
- 2) **Hand Lay Up Method:** Hand layup, or contact molding, is the oldest and simplest way of making composites which is shown in below fig.3.3. It is the Oldest open mold method for FRP laminates, dating to the 1940s when it was first used for boat hulls. Generally large in size but low in production quantity not economical for high production. Applications are standard wind turbine blades, boats, etc.

### III. DESCRIPTION OF PROPOSED WORK

The composite materials consist of two phases such as discontinuous phase and continuous phase. The discontinuous phases consist of reinforcement material and continuous phase consist of matrix material.

#### A. Human Hair

Hair is used as a fiber reinforcing material in composites for the following reasons:

- 1) It has a high tensile strength
- 2) Hair, a non-degradable material
- 3) Available in abundance
- 4) Very low cost.

#### B. Physical and Mechanical Properties of Human Hair

Table 3.1 Physical properties of Human Hair

| Fiber      | Density,<br>g/cm <sup>3</sup> | Diameter<br>μm | Tensile Strength,<br>MPa | Elongation at<br>Break, % |
|------------|-------------------------------|----------------|--------------------------|---------------------------|
| Human Hair | 1.32                          | 17-180         | 400                      | 216.94                    |

(Source: International Journal of Mechanical and Industrial Engineering (IJMIE), ISSN No. 2231 –6477, Vol-2, Issue-1, 2012, [8])

In our work, the Human Hair is purchased from Om Balavinainayaga Enterprises, Chennai in India. The fibers are purchased in the size of 100 to 125 mm by the length as shown in Fig 3.1. The present work concentrates on the chopped type of fiber reinforcement. And the fiber size is selected as 30mm by length.



Figure 3.1 Human Hair Purchased From Industry



### C. Matrix Material

In the present work Epoxy LY556 and corresponding hardener HY 951 is used as the matrix material.

- 1) *Epoxy Resin:* Epoxy is chosen as the matrix material for the present research work. Its common name is Bi-sphenol-A-Di-glycidyl-Ether and it chemically belongs to the 'epoxide' family. It has superior mechanical and electrical properties as shown in below Table 3.2.

Table 3.2 physical properties of Epoxy resin.

| Epoxy Resin Property                  | Value    |
|---------------------------------------|----------|
| Density, g/cm <sup>3</sup>            | 1.1-1.14 |
| Tensile Strength, Mpa                 | 35-100   |
| Compressive Strength, MPa             | 100-200  |
| Impact Strength J/cm                  | 0.3      |
| Elastic Modulus, Gpa                  | 3-6      |
| Elongation , %                        | 1-6      |
| Water Absorption,<br>(24 Hrs at 20°C) | 0.1-0.4  |
| Cure Shrinkage, %                     | 1-2      |

(Source: [www.fibreglast.com](http://www.fibreglast.com))

- 2) *Vinylester Resin:* Vinyl Ester, or Vinylester, is a resin produced by the esterification of an epoxy resin with an unsaturated monocarboxylic acid. The reaction product is then dissolved in a reactive solvent, such as styrene, to 35–45 percent content by weight. It can be used as an alternative to polyester and epoxy materials in matrix or composite materials, where its characteristics, strengths, and bulk cost intermediate between polyester and epoxy. Table 3.3 shows the various Physical properties of Vinylester resin.

Table 3.3 Physical properties of Vinylester resin.

| Vinylester Resin Property             | Value   |
|---------------------------------------|---------|
| Density,g/cm <sup>3</sup>             | 1.1-1.3 |
| Tensile Strength, Mpa                 | 80-90   |
| Compressive Strength, MPa             | 100-200 |
| Impact Strength J/cm                  | 0.28    |
| Elongation , %                        | 4-7     |
| Water Absorption,<br>(24 Hrs at 20°C) | 0.1-0.3 |
| Cure Shrinkage, %                     | 1-2.2   |

### D. Hand Layup Technique

Open-molding is a term used for a number of methods. The simplest is hand lay-up molding. In this, the resins and reinforcement are deposited in a mold by hand or hand tools. This is also known as 'contact molding' as resin is in contact with air. Hand layup, or contact molding, is the oldest and simplest way of making composites. In the present work hand layup method is followed due to their simple principles to teach, low tooling cost. The tools used are silicon rubber with 5mm thickness, polyester lamination sheet, plywood, roller and weight for setting purpose. Typical applications are standard wind turbine blades, production boats, and architectural moldings.

### E. Material Fabrication

Composites materials were fabricated with the size 300 mm × 300 mm square plate with 5 mm as the laminate thickness. The hand layup method was used for fabrication. Four different fiber compositions have been fabricated. The composition and designation of the composites prepared for this work are listed in Table 3.4. The epoxy resin (Araldite LY 556) and corresponding hardener (HY951) are mixed in a ratio of 10:1 by weight. Vinylester resin and corresponding accelerator, catalyst and hardener were mixed in ratio of 10:1:1:1 by weight as recommended for human hair reinforced Vinylester composites. Human hair is reinforced randomly in polymer matrix by chopping it with fiber length equal to 20mm. The mould using plywood, silica rubber and lamination sheet were prepared. Next the epoxy resin is poured onto the mould then the chopped fibers are distributed uniformly over the resin. Finally the resin is applied on the randomly distributed fiber. Using another lamination sheet and plywood the mould was closed. The cast of each composite is cured under a load of about 50 kg for 24 hours before it removed from the mold. Finally the specimens for dynamic mechanical analysis are prepared according to ASTM standards using vertical Zig Zag cutting machine.

Before starting the fabrication process, the weight of the fiber and resin to make composite are calculated for selected volume fraction and fiber composition it has been listed as below table 3.5.

### F. Study of Mechanical Properties

Often materials are subject to forces (loads) when they are used. Mechanical engineers calculate those forces and material scientists how materials deform (elongate, compress, twist) or break as a function of applied load, time, temperature, and other conditions. The various tests like Impact Strength, Water Absorption Test, Density Analysis, Hardness Test have been conducted to study the mechanical properties of polymer composites.

## IV. RESULTS & DISCUSSIONS

This chapter presents the mechanical and physical properties of the human hair fiber reinforced with epoxy and vinylester polymer. The results of various characterization tests are reported here. This includes evaluation of impact strength, Hardness, Water absorption properties, both theoretical and experimental density has been studied and discussed.

### A. Impact Strength

The below Figure 4.1 shows the Impact test specimens after performing the test in Impact testing Machine. The formula used to find out the tensile stress and tensile modulus or young's modulus is given below,

Impact strength =  $mg(h_0 - h_f)$ , in J

Where,  $m$  – Mass of Hammer in kg,

$g$  – Gravitational acceleration,

$h_0$  – original height in mm,

$h_f$  – final height in mm.

The impact test is performed in three samples per composites. Totally of fifteen samples were tested and the values are directly noted from the dial gauge and is tabulated in below table 4.1.



Figure 4.1 Specimens used for performing Impact test.

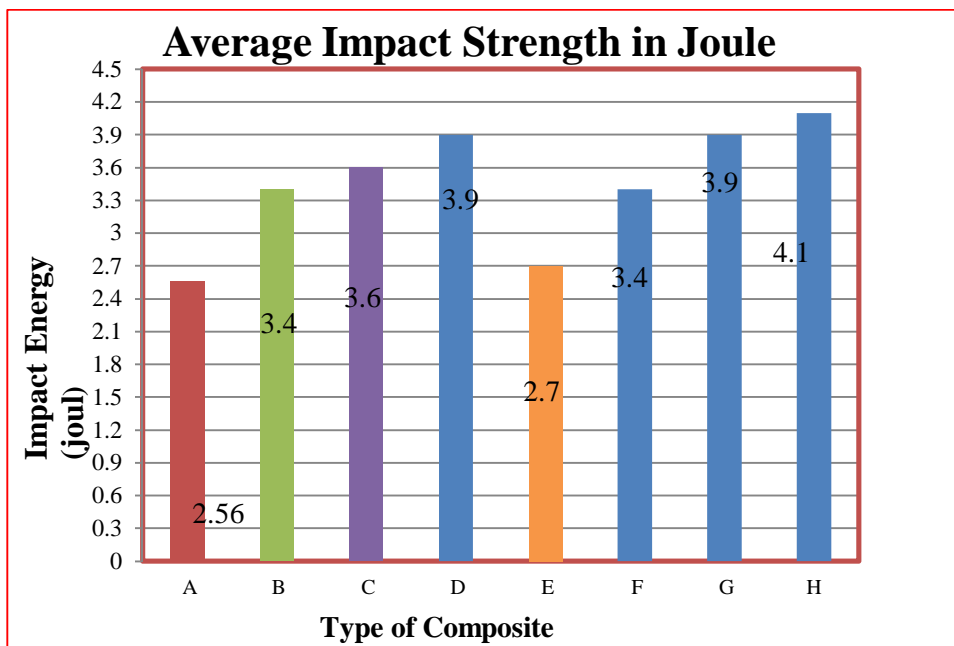


Figure 4.2 Average Impact Strength of the composites.

The figure 4.2 shows the impact energy found for the each composite. The graph shows that the impact energy of all the composite shows closer to each other. The composite with 15 Percentage of human hair in both epoxy matrix and vinylester matrix obtained lower impact energy than the other materials. Composite with 30 % of human hair reinforced composite has higher impact energy. The result shows that impact energy of composite are gradually increased in composite A, B and C and D. Similarly kind of result was observed for vinylester composite. From the impact energy test, it was found that while adding the human hair with polymer matrix the impact energy are increased as compared to pure matrix material.

Table 4.1 Impact test result of composites

| Sl.No. | Composite | Specimen | Impact Strength (Joul) | Average Impact Strength (Joul) |
|--------|-----------|----------|------------------------|--------------------------------|
| 1      | A         | A1       | 2.5                    | 2.56                           |
| 2      |           | A2       | 2.3                    |                                |
| 3      |           | A3       | 2.9                    |                                |
| 4      | B         | B1       | 3.4                    | 3.4                            |
| 5      |           | B2       | 3.7                    |                                |
| 6      |           | B3       | 3.1                    |                                |
| 7      | C         | C1       | 3.9                    | 3.6                            |
| 8      |           | C2       | 3.4                    |                                |
| 9      |           | C3       | 3.5                    |                                |
| 10     |           | D1       | 3.8                    | 3.9                            |

|    |   |    |     |     |
|----|---|----|-----|-----|
| 11 | D | D2 | 4.2 |     |
| 12 |   | D3 | 3.7 |     |
| 13 | E | E1 | 2.4 | 2.7 |
| 14 |   | E2 | 2.9 |     |
| 15 |   | E3 | 2.8 |     |
| 16 | F | F1 | 3.5 | 3.4 |
| 17 |   | F2 | 3.1 |     |
| 18 |   | F3 | 3.6 |     |
| 19 | G | G1 | 4.2 | 3.9 |
| 20 |   | G2 | 3.9 |     |
| 21 |   | G3 | 3.6 |     |
| 22 | H | H1 | 4.3 | 4.1 |
| 23 |   | H2 | 4.1 |     |
| 24 |   | H3 | 3.9 |     |

### B. Water Absorption

The water absorption tests of Human Hair fiber reinforced composites were done as per ASTM 570 by immersion in water at room temperature. The samples were taken out periodically and after wiping out the water from the surface of the sample weighted immediately using a precise balance machine to find out the content of water absorbed. The specimens were weighed regularly at 24, 48, 72, 96, 120 and 144 hours. The water absorption is calculated by the weight difference. The samples used for conducting the experiments are shown in fig.4.34.

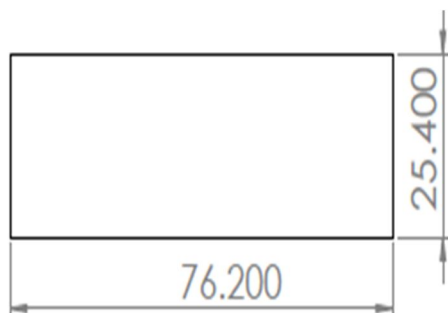


Figure 4.3 ASTM Standard Size of Water Absorption test specimen



Figure 4.4 prepared Water Absorption test specimen

The weight of the all the specimens are weighed regularly at every 24 Hrs. and the mass in grams are noted down. The table 4.7 shows the mass of the specimens at dry condition and wet conditions.

### C. Water Absorption Properties Various Composites

The mass of the specimens for human hair reinforced with epoxy matrix at every 24 hrs is weighed and it is tabulated below.

Table 4.2 Water Absorption Values of composites with Epoxy as the matrix material at Every 24 Hrs.

| Sl.No. | Specimen | Mass of the Composite in Gram |                      |                      |                      |                      |                       |                       |
|--------|----------|-------------------------------|----------------------|----------------------|----------------------|----------------------|-----------------------|-----------------------|
|        |          | Before Immersion              | After 24 hrs (Day 1) | After 48 hrs (Day 2) | After 72 hrs (Day 3) | After 96 hrs (Day 4) | After 120 hrs (Day 5) | After 144 hrs (Day 6) |
| 1      | A1       | 12.51                         | 12.522               | 12.53                | 12.539               | 12.542               | 12.55                 | 12.559                |
| 2      | A2       | 12.616                        | 12.625               | 12.626               | 12.63                | 12.635               | 12.637                | 16.644                |
| 3      | A3       | 12.071                        | 12.081               | 12.082               | 12.09                | 12.093               | 12.098                | 12.1                  |
| 4      | B1       | 14.819                        | 14.909               | 14.922               | 14.944               | 14.955               | 14.964                | 14.966                |
| 5      | B2       | 16.547                        | 16.576               | 16.592               | 16.616               | 16.625               | 16.64                 | 16.646                |
| 6      | B3       | 15.226                        | 15.258               | 15.293               | 15.305               | 15.347               | 15.346                | 15.348                |
| 7      | C1       | 14.213                        | 14.923               | 15.024               | 15.065               | 15.123               | 15.198                | 15.288                |
| 8      | C2       | 14.053                        | 14.39                | 15.512               | 15.716               | 15.801               | 15.828                | 15.825                |
| 9      | C3       | 15.356                        | 15.878               | 16.177               | 16.29                | 16.59                | 16.644                | 16.742                |
| 10     | D1       | 12.608                        | 12.981               | 13.35                | 13.38                | 13.391               | 13.402                | 13.416                |
| 11     | D2       | 14.51                         | 14.768               | 14.98                | 15.022               | 15.091               | 15.144                | 15.15                 |
| 12     | D3       | 12.379                        | 13.104               | 13.273               | 13.406               | 13.512               | 13.574                | 13.616                |

The table 4.7 and 4.8 shows gradual increase of the weight of the specimen at every 24 hrs. The moisture uptake by the specimen is increased when immersion time is increased. The values are getting closer after 4 to 5 days which was observed from the table 4.7 and table 4.8.

The mass of the specimens for human hair reinforced with vinylester matrix at every 24 hrs is weighed and it is tabulated below.

Table 4.3 Water Absorption Values of composites with Vinylester as the matrix material at Every24Hrs.

| Sl.No. | Specimen | Mass of the Composite in Gram |                      |                      |                      |                      |                       |                       |
|--------|----------|-------------------------------|----------------------|----------------------|----------------------|----------------------|-----------------------|-----------------------|
|        |          | Before Immersion              | After 24 hrs (Day 1) | After 48 hrs (Day 2) | After 72 hrs (Day 3) | After 96 hrs (Day 4) | After 120 hrs (Day 5) | After 144 hrs (Day 6) |
| 1      | E1       | 11.217                        | 11.249               | 11.267               | 11.272               | 11.275               | 11.276                | 11.278                |
| 2      | E2       | 11.68                         | 11.786               | 11.799               | 11.82                | 11.828               | 11.836                | 11.848                |
| 3      | E3       | 10.021                        | 10.123               | 10.135               | 10.17                | 10.203               | 10.221                | 10.235                |
| 4      | F1       | 18.212                        | 18.344               | 18.38                | 18.397               | 18.415               | 18.462                | 18.48                 |
| 5      | F2       | 18.19                         | 18.252               | 18.269               | 18.27                | 18.295               | 18.305                | 18.307                |
| 6      | F3       | 16.585                        | 16.666               | 16.675               | 16.68                | 16.688               | 16.692                | 16.696                |
| 7      | G1       | 16.06                         | 16.244               | 16.252               | 16.28                | 16.291               | 16.36                 | 16.426                |
| 8      | G2       | 19.617                        | 19.855               | 19.876               | 19.913               | 19.932               | 19.959                | 19.98                 |
| 9      | G3       | 19.378                        | 19.475               | 19.497               | 19.512               | 19.523               | 19.556                | 19.561                |
| 10     | H1       | 19.558                        | 19.794               | 19.99                | 20.041               | 20.15                | 20.32                 | 20.332                |
| 11     | H2       | 20.01                         | 20.208               | 20.291               | 20.334               | 20.361               | 20.398                | 20.424                |
| 12     | H3       | 19.967                        | 20.106               | 20.112               | 20.125               | 20.15                | 20.172                | 20.19                 |



The percentage weight gain of the samples is measured at different time intervals by using the following equation.

$$\text{Water absorption (\%)} = \frac{W_2 - W_1}{W_1} \times 100$$

Where, W1 and W2 are the weight of the dry and wet samples.

Table 4.4 Percentage of Moisture Absorption of composites with Epoxy as the matrix material at every 24 hrs

| Sl. No. | Specimen | % Gain of Water      |                      |                      |                      |                       |                       |                          |                           |                        |                         |
|---------|----------|----------------------|----------------------|----------------------|----------------------|-----------------------|-----------------------|--------------------------|---------------------------|------------------------|-------------------------|
|         |          | After 24 hrs (Day 1) | After 48 hrs (Day 2) | After 72 hrs (Day 3) | After 96 hrs (Day 4) | After 120 hrs (Day 5) | After 144 hrs (Day 6) | Average of Each Specimen | Average of Each Composite | Range of Each Specimen | Range of Each Composite |
| 1       | A1       | 0.096                | 0.064                | 0.072                | 0.024                | 0.064                 | 0.072                 | 0.065                    | 0.047                     | 0.024-0.096            | 0.015-0.096             |
| 2       | A2       | 0.071                | 0.008                | 0.032                | 0.040                | 0.016                 | 0.055                 | 0.037                    |                           | 0.015-0.079            |                         |
| 3       | A3       | 0.083                | 0.008                | 0.066                | 0.025                | 0.041                 | 0.017                 | 0.040                    |                           | 0.016-0.083            |                         |
| 4       | B1       | 0.607                | 0.087                | 0.147                | 0.074                | 0.060                 | 0.013                 | 0.165                    | 0.132                     | 0.013-0.165            | 0.013-0.229             |
| 5       | B2       | 0.175                | 0.097                | 0.145                | 0.054                | 0.090                 | 0.036                 | 0.099                    |                           | 0.036-0.175            |                         |
| 6       | B3       | 0.210                | 0.229                | 0.078                | 0.274                | -0.007                | 0.013                 | 0.133                    |                           | 0.013-0.229            |                         |
| 7       | C1       | 4.995                | 0.677                | 0.273                | 0.385                | 0.496                 | 0.592                 | 1.236                    | 1.575                     | 0.272-4.995            | 0.17-4.995              |
| 8       | C2       | 2.398                | 7.797                | 1.315                | 0.541                | 0.171                 | -0.019                | 2.034                    |                           | 0.17-2.398             |                         |
| 9       | C3       | 3.399                | 1.883                | 0.699                | 1.842                | 0.325                 | 0.589                 | 1.456                    |                           | 0.325-3.399            |                         |
| 10      | D1       | 2.958                | 2.843                | 0.225                | 0.082                | 0.082                 | 0.104                 | 1.049                    | 1.130                     | 0.082-2.958            | 0.039-5.856             |
| 11      | D2       | 1.778                | 1.436                | 0.280                | 0.459                | 0.351                 | 0.040                 | 0.724                    |                           | 0.039-1.778            |                         |
| 12      | D3       | 5.857                | 1.290                | 1.002                | 0.791                | 0.459                 | 0.309                 | 1.618                    |                           | 0.309-5.856            |                         |

The percentage increase in weight of the composite specimen after immersing it into water at every 24 hrs calculated by using above formula and the values are tabulated separately for human hair reinforced with both epoxy and vinylester matrix. The average values of the composite shows that the percentage moisture gain of the composite increases when the fiber volume in matrix increases. The composite with 15 Percentage volume of human hair shows lower moisture gain or lower increases of Percentage weight when compared to other composites. The higher fiber content composite obtained larger value of Percentage moisture absorption than other composite. The range of moisture absorption from initial day to final day is calculated and it is tabulated in above table. The range values also increases with increasing fiber content.

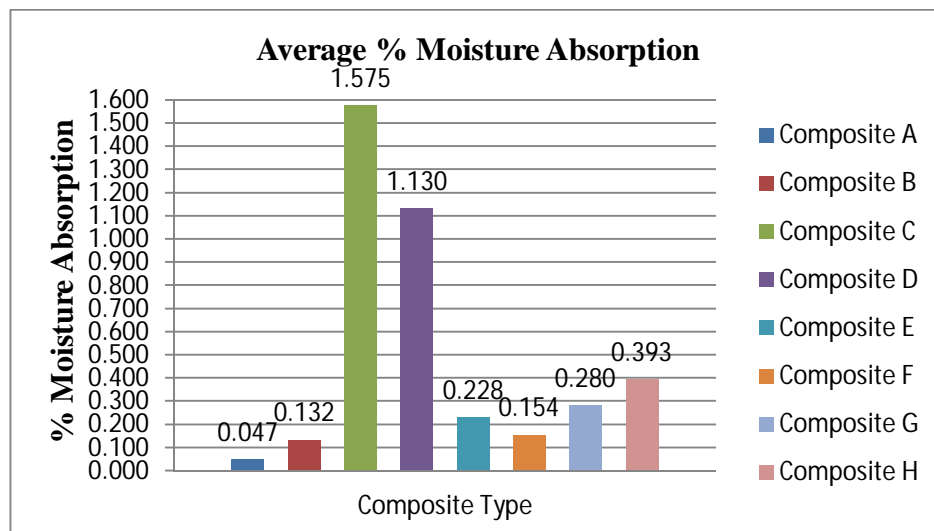


Figure 4.5 Average Percentage Gain of water at every 24 hrs.

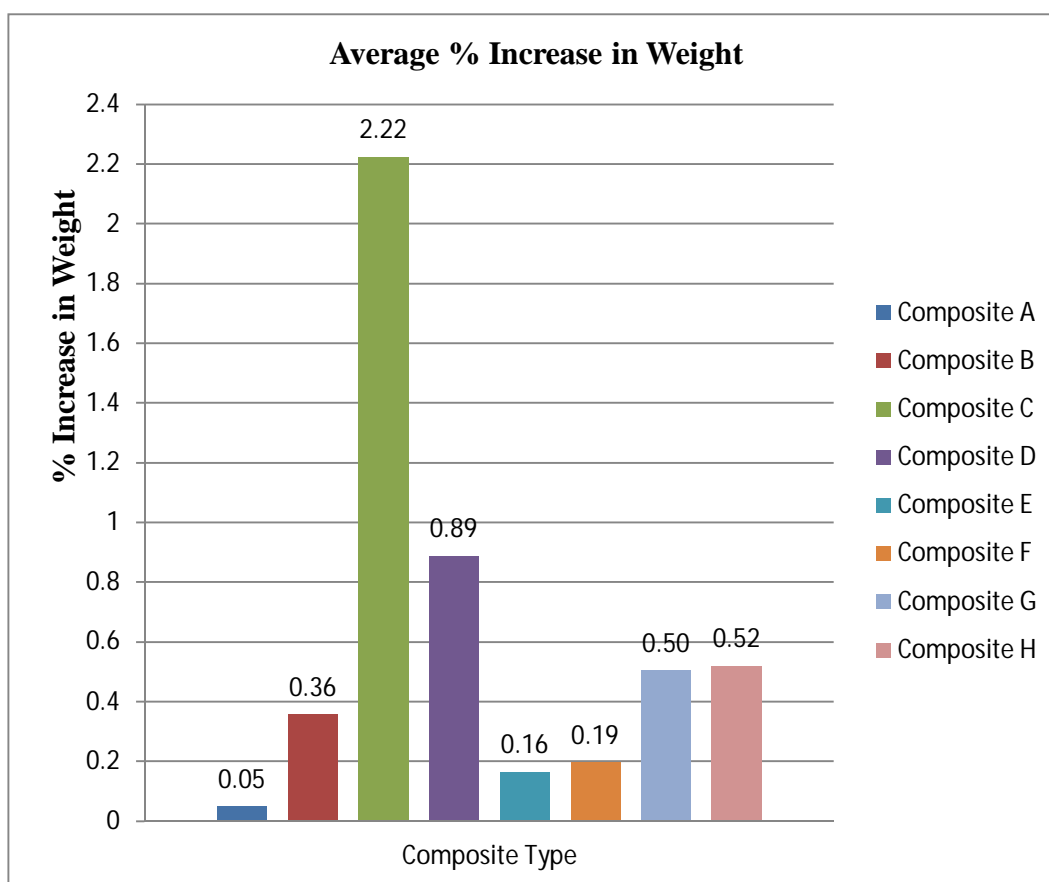


Figure 4.6 Average Percentage Increase in Weight of the Composite after Drying.

The Percentage increase in moisture absorption of the composite with vinylester matrix is shown in below table 4.9. The similar kind of result was obtained as the result obtained for the composite with epoxy matrix. When comparing the composite with epoxy matrix and composite with vinylester matrix, the vinylester matrix composite shows lower Percentage moisture absorption at all fiber volume fraction.

Table 4.5 Percentage of Moisture Absorption of composites with Vinylester as the matrix material at Every24Hrs

| Sl. No. | Specimen | % Gain of Water      |                      |                      |                      |                       |                       |                          |                            |                        |                          |
|---------|----------|----------------------|----------------------|----------------------|----------------------|-----------------------|-----------------------|--------------------------|----------------------------|------------------------|--------------------------|
|         |          | After 24 hrs (Day 1) | After 48 hrs (Day 2) | After 72 hrs (Day 3) | After 96 hrs (Day 4) | After 120 hrs (Day 5) | After 144 hrs (Day 6) | Average of Each Specimen | Average of Each Compo-site | Range of Each Specimen | Range of Each Compo-site |
| 1       | E1       | 0.285                | 0.160                | 0.044                | 0.027                | 0.009                 | 0.018                 | 0.090                    | 0.228                      | 0.008-0.285            | 0.008-1.017              |
| 2       | E2       | 0.908                | 0.110                | 0.178                | 0.068                | 0.068                 | 0.101                 | 0.239                    |                            | 0.067-0.907            |                          |
| 3       | E3       | 1.018                | 0.119                | 0.345                | 0.324                | 0.176                 | 0.137                 | 0.353                    |                            | 0.118-1.017            |                          |
| 4       | F1       | 0.725                | 0.196                | 0.092                | 0.098                | 0.255                 | 0.097                 | 0.244                    | 0.154                      | 0.092-0.724            | 0.005-0.724              |
| 5       | F2       | 0.341                | 0.093                | 0.005                | 0.137                | 0.055                 | 0.011                 | 0.107                    |                            | 0.005-0.341            |                          |
| 6       | F3       | 0.488                | 0.054                | 0.030                | 0.048                | 0.024                 | 0.024                 | 0.111                    |                            | 0.024-0.488            |                          |
| 7       | G1       | 1.146                | 0.049                | 0.172                | 0.068                | 0.424                 | 0.403                 | 0.377                    | 0.280                      | 0.049-1.145            | 0.025-1.213              |
| 8       | G2       | 1.213                | 0.106                | 0.186                | 0.095                | 0.135                 | 0.105                 | 0.307                    |                            | 0.095-1.213            |                          |
| 9       | G3       | 0.501                | 0.113                | 0.077                | 0.056                | 0.169                 | 0.026                 | 0.157                    |                            | 0.025-0.501            |                          |
| 10      | H1       | 1.207                | 0.990                | 0.255                | 0.544                | 0.844                 | 0.059                 | 0.650                    | 0.393                      | 0.059-1.206            | 0.059-1.206              |
| 11      | H2       | 0.990                | 0.411                | 0.212                | 0.133                | 0.182                 | 0.127                 | 0.342                    |                            | 0.132-0.989            |                          |
| 12      | H3       | 0.696                | 0.030                | 0.065                | 0.124                | 0.109                 | 0.089                 | 0.186                    |                            | 0.064-0.696            |                          |

The water absorbed specimens were dried at environmental temperature for 4 hrs and weight of the dried specimens were weighed and noted down. The increase in weight of the specimen was calculated from the specimen weight which obtained before immersing it into water. The weight of the specimen before immersing and after drying the specimens was used to calculate the increase in weight of the specimen which is tabulated for both the composite with epoxy matrix and vinylester matrix in below Table 4.10 and Table 4.11 respectively. And also the total increase in Percentage moisture absorption is calculated from day 6 values and day 1 values.

Table 4.6 Percentage of increase in weight of composites with Epoxy as the matrix material after fully dried condition.

| Sl.No. | Specimen | Mass of the Composite in Gram |               |                       |                                       |                      |
|--------|----------|-------------------------------|---------------|-----------------------|---------------------------------------|----------------------|
|        |          | Before Immersion              | After 144 hrs | Fully Dried Condition | % Gain on final day from dry specimen | Increase in Weight % |
|        |          |                               | (Day 6)       |                       |                                       |                      |
| 1      | A1       | 12.51                         | 12.559        | 12.512                | 0.392                                 | 0.016                |
| 2      | A2       | 12.616                        | 12.644        | 12.62                 | 0.222                                 | 0.032                |
| 3      | A3       | 12.071                        | 12.1          | 12.083                | 0.24                                  | 0.099                |
| 4      | B1       | 14.819                        | 14.966        | 14.875                | 0.992                                 | 0.378                |
| 5      | B2       | 16.547                        | 16.646        | 16.6                  | 0.598                                 | 0.32                 |
| 6      | B3       | 15.226                        | 15.348        | 15.283                | 0.801                                 | 0.374                |
| 7      | C1       | 14.213                        | 15.288        | 14.52                 | 7.563                                 | 2.16                 |
| 8      | C2       | 14.053                        | 15.825        | 14.458                | 12.609                                | 2.882                |
| 9      | C3       | 15.356                        | 16.742        | 15.606                | 9.026                                 | 1.628                |
| 10     | D1       | 12.608                        | 13.416        | 12.754                | 6.409                                 | 1.158                |
| 11     | D2       | 14.51                         | 15.15         | 14.573                | 4.411                                 | 0.434                |
| 12     | D3       | 12.379                        | 13.616        | 12.511                | 9.993                                 | 1.066                |

The result shows that for both epoxy and vinylester composite the Percentage moisture gain increases with increasing fiber content. The composite with 30% volume fraction shows higher value of Percentage moisture absorption than other composites.

Table 4.7 Percentage of increase in weight of composites with Vinylester as the matrix material after fully dried condition.

| Sl.No. | Specimen | Mass of the Composite in Gram |                       |                       |                                       |                      |
|--------|----------|-------------------------------|-----------------------|-----------------------|---------------------------------------|----------------------|
|        |          | Before Immersion              | After 144 hrs (Day 6) | Fully Dried Condition | % Gain on final day from dry specimen | Increase in Weight % |
| 1      | E1       | 11.217                        | 11.278                | 11.244                | 0.544                                 | 0.241                |
| 2      | E2       | 11.680                        | 11.848                | 11.699                | 1.438                                 | 0.163                |
| 3      | E3       | 10.021                        | 10.235                | 10.030                | 2.136                                 | 0.090                |
| 4      | F1       | 18.212                        | 18.480                | 18.252                | 1.472                                 | 0.220                |
| 5      | F2       | 18.190                        | 18.307                | 18.206                | 0.643                                 | 0.088                |
| 6      | F3       | 16.585                        | 16.696                | 16.631                | 0.669                                 | 0.277                |
| 7      | G1       | 16.060                        | 16.426                | 16.148                | 2.279                                 | 0.548                |
| 8      | G2       | 19.617                        | 19.980                | 19.755                | 1.850                                 | 0.703                |
| 9      | G3       | 19.378                        | 19.561                | 19.428                | 0.944                                 | 0.258                |
| 10     | H1       | 19.558                        | 20.332                | 19.726                | 3.957                                 | 0.859                |
| 11     | H2       | 20.010                        | 20.424                | 20.094                | 2.069                                 | 0.420                |
| 12     | H3       | 19.967                        | 20.190                | 20.023                | 1.117                                 | 0.280                |

#### D. Density Analysis

The actual density ( $\rho_c$ ) of the composites were determined using simple water immersion technique experimentally.

Experimental Density

$$\text{Density} = \text{Mass} / \text{Volume}$$

Where,

Mass = Weight of Specimen in Gram

Volume = Volume of water rise in Beaker in  $\text{cm} = \pi r^2 h$

Radius of Beaker,  $r = 3.06 \text{ cm}$

Height of water rise in beaker,  $h \text{ (cm)}$

Theoretical Density

The Theoretical density of the composite material can be calculated by using the following equation,

The density of the composite material in terms of volume fractions, the density of the composite material is written as

$$\rho_c = \rho_f V_f + \rho_m V_m$$

Where,

|          |   |                           |
|----------|---|---------------------------|
| $\rho_f$ | = | Density of Fiber          |
| $\rho_m$ | = | Density of Matrix         |
| $\rho_c$ | = | Density of Composite      |
| $V_f$    | = | Volume fraction of Fiber  |
| $V_m$    | = | Volume fraction of Matrix |



### E. Density Analysis of Various Composites

The density obtained from experimental method shows closer to the theoretical density values. Three specimens for each composite were used for determining experimental density of the composites. Average value of experimental density of each composite is shown in table 4.12 and table 4.13. The result shows that for epoxy composite human hair with 15%, 20 % and 30 % volume content posses slightly higher density than theoretical density. These may be due to the presence of moisture content in the composites. Similarly for the composites with Vinylester as the matrix material shows closer experimental values than theoretical density. And also obtained density is lighter than the conventional materials.

Table 4.8 Calculated Density of composites with epoxy as matrix material

| Sl.No. | Composite | Specimen | Density of Composite $\rho_c(\text{g/cm}^3)$ | Average Experimental Density of Composite $\rho_c(\text{g/cm}^3)$ | Theoretical Density of Composites |
|--------|-----------|----------|--|---|-----------------------------------|
|        |           |          |  |   | $\rho_c(\text{g/cm}^3)$           |
| 1      | A         | A1       | 1.316  | 1.276   | 1.2605                            |
| 2      |           | A2       | 1.34   |   |                                   |
| 3      |           | A3       | 1.172  |   |                                   |
| 4      | B         | B1       | 1.1992                                       | 1.3   | 1.26                              |
| 5      |           | B2       | 1.372  |   |                                   |
| 6      |           | B3       | 1.328  |   |                                   |
| 7      | C         | C1       | 1.052  | 1.076   | 1.2675                            |
| 8      |           | C2       | 1.112  |   |                                   |
| 9      |           | C3       | 1.064  |   |                                   |
| 10     | D         | D1       | 1.3  | 1.405   | 1.271                             |
| 11     |           | D2       | 1.296  |   |                                   |
| 12     |           | D3       | 1.62   |   |                                   |

Table 4.9 Calculated Density of composites with epoxy as matrix material

| Sl.No. | Composite | Specimen | Density of Composite $\rho_c(\text{g/cm}^3)$ | Average Experimental Density of Composite $\rho_c(\text{g/cm}^3)$ | Theoretical Density of Composites |
|--------|-----------|----------|--|---|-----------------------------------|
|        |           |          |  |   | $\rho_c(\text{g/cm}^3)$           |
| 13     | E         | E1       | 1.272  | 1.229   | 1.303                             |
| 14     |           | E2       | 1.24   |   |                                   |
| 15     |           | E3       | 1.176  |   |                                   |
| 16     | F         | F1       | 1.236  | 1.208   | 1.3                               |
| 17     |           | F2       | 1.26   |   |                                   |
| 18     |           | F3       | 1.128  |   |                                   |
| 19     | G         | G1       | 1.14   | 1.131   | 1.305                             |
| 20     |           | G2       | 1.136  |   |                                   |
| 21     |           | G3       | 1.116  |   |                                   |
| 22     | H         | H1       | 1.108  | 1.112   | 1.306                             |
| 23     |           | H2       | 1.096  |   |                                   |
| 24     |           | H3       | 1.132  |   |                                   |

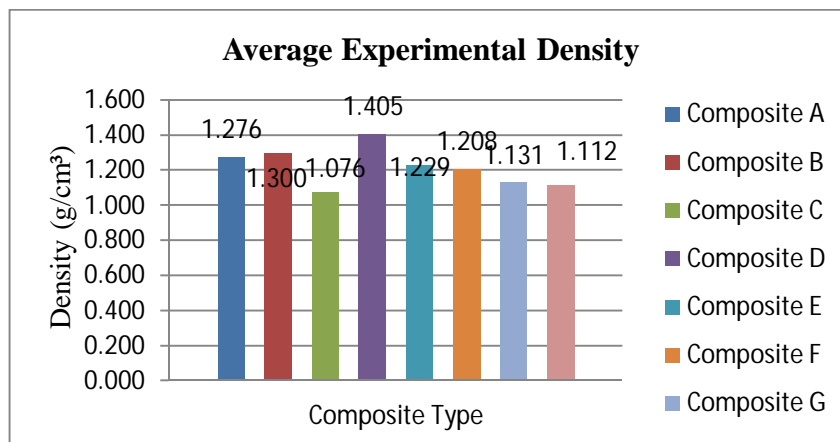


Figure 4.7 Average Experimental Density

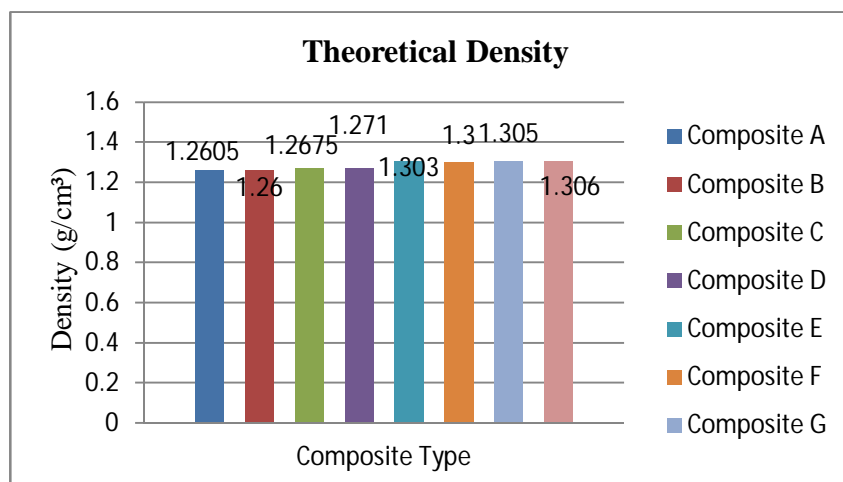


Figure 4.8 Theoretical Density



Figure 4.9 Specimens used for determining Density of Composites

### F. Hardness Test

According to ASTM E 10 standards for composites, the specimens were prepared for Rockwell-B hardness test. The hardness properties of the composites are studied by applying indentation load normal to fibers diameter. The effect of fiber loading time on Rockwell hardness of both dry and wet specimens is illustrated in Figures 8 and 9. Generally, fibers that increase the moduli of composites increase the hardness of the composite. This is because hardness is a function of the relative fiber volume and modulus.

Table 4.10 The Average Value of hardness

| Sl.No. | Composite | Dry Specimen |          |          | Average RHN | Wet Specimen |          |          | Average RHN |
|--------|-----------|--------------|----------|----------|-------------|--------------|----------|----------|-------------|
|        |           | Sample 1     | Sample 2 | Sample 3 |             | Sample 1     | Sample 2 | Sample 3 |             |
| 1      | A         | 50           | 57       | 41       | 49.33       | 59           | 55       | 55       | 56.33       |
| 2      | B         | 78           | 61       | 54       | 64.33       | 61           | 58       | 54       | 57.67       |
| 3      | C         | 53           | 42       | 60       | 51.67       | 59           | 58       | 52       | 56.33       |
| 4      | D         | 57           | 56       | 59       | 57.33       | 61           | 69       | 62       | 64.00       |
| 5      | E         | 80           | 81       | 61       | 74.00       | 59           | 60       | 70       | 63.00       |
| 6      | F         | 58           | 57       | 74       | 63.00       | 67           | 74       | 62       | 67.67       |
| 7      | G         | 79           | 82       | 70       | 77.00       | 65           | 73       | 82       | 73.33       |
| 8      | H         | 92           | 86       | 77       | 85.00       | 80           | 68       | 65       | 71.00       |

Specimen Size: (75 x 25 x 5) mm

Test Machine: Rockwell Hardness Machine.

Indenter=1/16" ball load=100kg for Polyester Composite.



Figure 4.10 Specimens used for Hardness Test

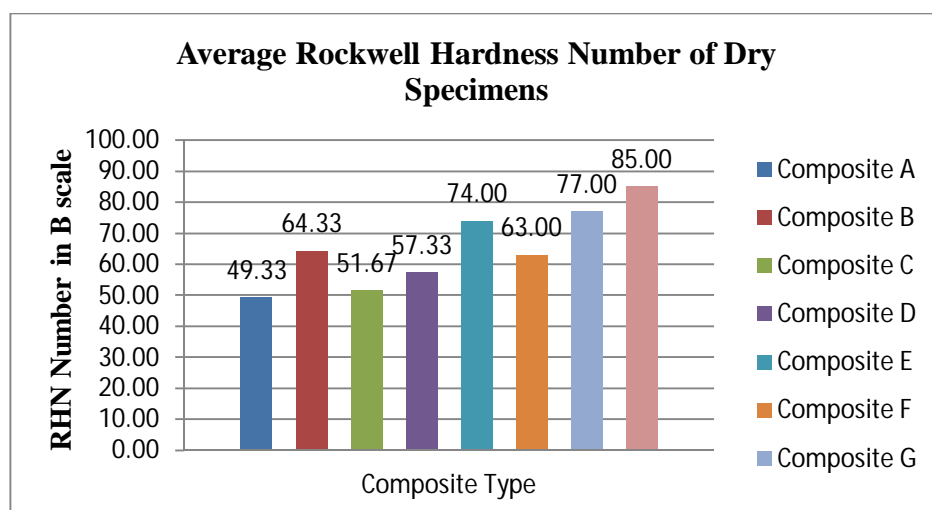


Figure 4.11 Average Rockwell Hardness Number of Dry Specimens

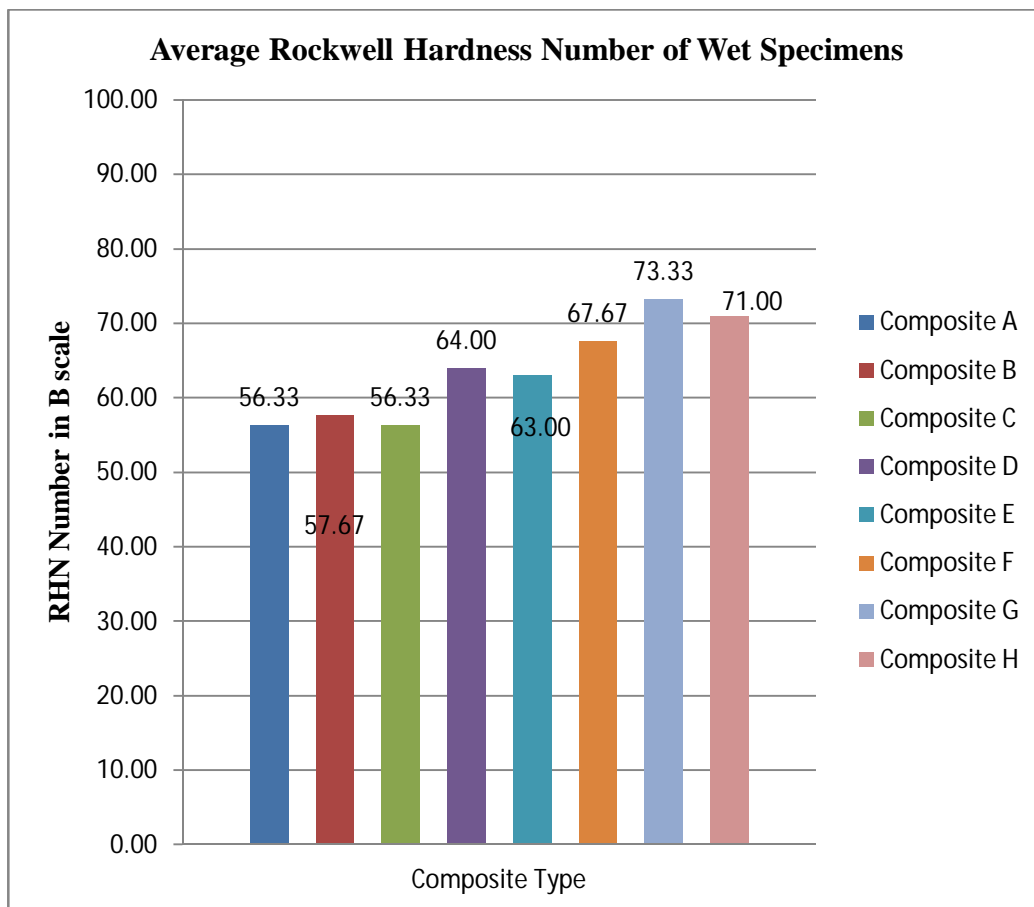


Figure 4.12 Average Rockwell Hardness Number of Dry Specimens

When equilibrium has been reached, an indicating device, which follows the movements of the indenter and so responds to changes in depth of penetration of the indenter, is set to a datum position. The permanent increase in depth of penetration, resulting from the application and removal of the additional major load is used to calculate the Rockwell hardness number.

From result the obtained hardness values exhibits around 50 to 90. The variations are due to the higher matrix contribution at the interface and voids. The lower hardness number indicates higher resistance of the material against load.

Table 4.11 Average values of Mechanical test result of composites

| Composite | Impact Strength (Joul) | Rockwell Hardness |              | Experi-mental Density of Composite $\rho_c(g/cm^3)$ | Theoretical Density of Composites $\rho_c(g/cm^3)$ | % gain of moisture | % Increase in Weight of Composites after drying |
|-----------|------------------------|-------------------|--------------|---|--|--------------------|---|
|           |                        | Dry Specimen      | Wet Specimen |   |  |                    |   |
| A         | 2.56                   | 49.33             | 56.33        | 1.276   | 1.2605   | 0.047              | 0.049   |
| B         | 3.4                    | 64.33             | 57.67        | 1.3   | 1.26   | 0.132              | 0.357   |
| C         | 3.6                    | 51.67             | 56.33        | 1.076   | 1.2675   | 1.575              | 2.223   |
| D         | 3.9                    | 57.33             | 64.00        | 1.405   | 1.271  | 1.130              | 0.886   |
| E         | 2.7                    | 74.00             | 63.00        | 1.229   | 1.303  | 0.228              | 0.164   |
| F         | 3.4                    | 63.00             | 67.67        | 1.208   | 1.3  | 0.154              | 0.194   |
| G         | 3.9                    | 77.00             | 73.33        | 1.131   | 1.305  | 0.280              | 0.503   |
| H         | 4.1                    | 85.00             | 71.00        | 1.112   | 1.306  | 0.393              | 0.519   |



### G. Scanning Electron Microscopy

The microstructure of fractured specimens was analyzed by Scanning Electron Microscope. From Fig. 9 composite D and Fig. 10 composite H the SEM images identified that during the fabrication of composites using hand layup technique presence of vacuum inside the mould creates voids in the composites that decrease quality of properties. Fiber pull out also occurred in composite D which shows lack of adhesion between fiber and matrix during fabrication. It is evident from Fig. 11 Composite A and Fig. 12 composite E clear and uniform distribution of fiber with matrix was achieved.

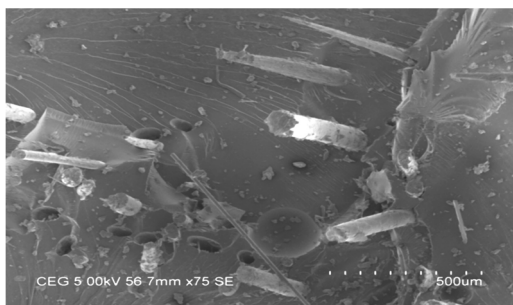


Figure 4.13 Composite with 30 % Human Hair and 70% Epoxy

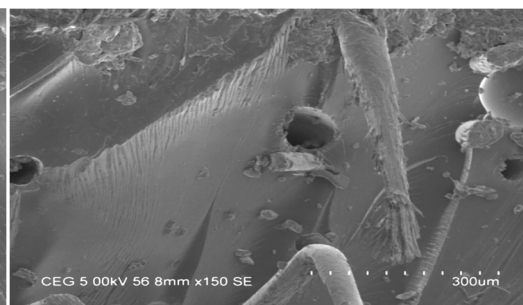


Figure 4.14 Composite with 30% Human Hair and 70% Vinylester

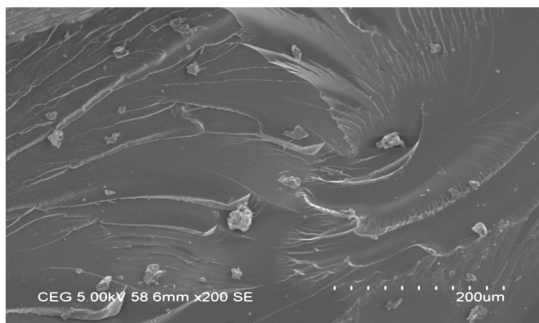


Figure 4.15 Composite with 15% Human Hair and 85 % Epoxy

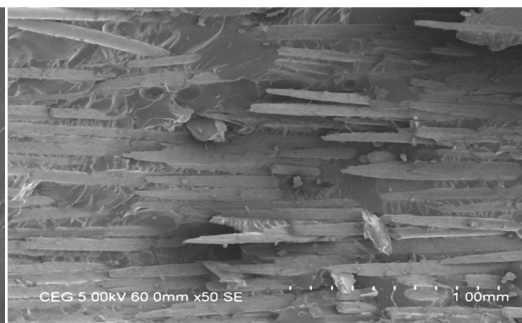


Figure 4.16 Composite with 15% Human Hair and 85% Vinylester

### H. Summary of Research Findings

From impact properties the 15% of human hair reinforced epoxy composite has lower impact strength than other composites and the 30% human hair reinforced composite has higher value of impact strength than other composite. From these it was decided that impact strength of composite are gradually increased when the volume of human hair content increased. The density obtained from experimental method shows closer to the theoretical density values. And also obtained density is lighter than the conventional materials. Percentage increase in Water absorption in all the composite specimen shows lesser in value when compared to other natural fiber reinforced composites. From Rockwell Hardness Number obtained from hardness test it was concluded that the values exhibits around 50 to 90. The variations are due to the higher matrix contribution at the interface and voids. The lower hardness number indicates higher resistance of the material against load.

## V. CONCLUSION

This work shows that successful fabrication of a human hair reinforced epoxy and vinylester composites by simple hand lay-up technique. Fabrication of composites done with four different fiber and matrix volume fraction (15:85, 20:80, 25:75 and 30:70 ratio of Human hair/ Epoxy and Human hair/ Vinylester respectively).

Mechanical and physical properties such as Impact, Rockwell Hardness, density and water absorption properties were determined. From impact result, the impact energies were found to increase with increase in human hair content in composite. The percentage moisture gain of composite increases when the human hair volume in composite increases. Composite with 15% and 20 % volume of human hair shows lower moisture gain or lower increases in percentage weight when compared to other composites. This may be due to the hydrophobic behavior of human hair that leads to the lower interaction of human hair and water.

After drying the water absorbed specimens at room temperature the weight of dried composites increases with increasing human hair content in composites. Increase in moisture absorption is lower for vinylester composite when compared to epoxy composites. The density obtained from experimental method shows values closer to the theoretical density values. Percentage error calculated from experimental density and theoretical density shows that the composite with 25 % and 30 % volume of human hair had higher variation. This may be due to the presence of voids in the composites that absorb moisture from air leads to higher variation of weight. Similarly for the composites with Vinylester as the matrix material but result shows lesser than epoxy composites. The Rockwell hardness of human hair reinforced composite exhibits around 50 to 85. The hardness number obtained from the results indicates that the human hair reinforced composites can resist loading. Vinylester composite obtained higher hardness number than epoxy composites. From result, composite with 25% human hair and 30 % human hair (Composite C,D,G & H) shows higher mechanical properties than composite with 15 % human hair and 20 % human hair (Composite A,B,E & F). But physical properties were found to be better in 15 % human hair and 20 % human hair composites and SEM image reveals that the presence of voids affects inter bonding that decreases physical properties of composites.

## REFERENCES

- [1] Das S., "Jute composite and its applications", Indian Jute Industries' Research Association, pp113, www.jute.org.
- [2] Nwigbo S. C., Atuanya C. U and Ulasi O. A., (2013), "The Study of the Mechanical Properties of Female African Human Hair Reinforced Polypropylene Composites", International Journal of Engineering and Mathematical Sciences, Volume 3, Issue – 1, pp. 103 – 114.
- [3] C. Elanchezian, B. VijayaRamnath, M. U. Sughan, K. Suseetharan V. Varun Kumar, R. Vezhavendan and R.Kaosis, (2015), "Evaluation Of Mechanical Properties of Human Hair/bombyxMori Silk Fiber Reinforced Epoxy Based Biocomposite", ARPN Journal of Engineering and Applied Sciences, Vol 10, No 13.
- [4] Sanjay Choudhry and BhawanaPandey (2012) 'Mechanical Behaviour of Polypropylene And Human Hair Fibres And Polypropylene Reinforced Polymeric Composites'. International Journal of Mech and IndustEngg (IJMIE), Vol.2, Issue.1, pp.118-121.
- [5] S.V. Joshi, L.T. Drzal, A.K. Mohanty, S. Arora "The mechanical properties of vinylester resin matrix composites reinforced with alkali-treated jute fibres" Part A 32 (2001) 119–127.
- [6] K. Rana, A. Mandal, B.C. Mitra, R. Jacobson, R. Rowell, A. N.Banerjee, (1998) "Short Jute Fiber-Reinforced Polypropylene Composites: Effect of Compatibilizer" Journal of Applied Polymer Science, Vol. 69, 329-338.
- [7] D. Ray, B.K. Sarkara, A.K. Rana, N.R. Bose, (2001) "The mechanical properties of vinylester resin matrix composites reinforced with alkali-treated jute fibres" Part A 32, pp.119–127.
- [8] Thiruchitrabalam M., Alavudeen A., Athijayamani A., Venkateshwaran N., and ElayaPerumal (2009) 'Improving Mechanical Properties of Banana/KenafPolyester Hybrid Composites Using Sodium Lauryl Sulfate Treatment'. Materials Physics and Mechanics: Vol.8, pp.165-173.
- [9] Girisha C., Sanjeevamurthy and GuntiRangaSrinivas (2012) 'Sisal/Coconut Coir Natural Fibers – Epoxy Composites: Water Absorption and Mechanical Properties'. Int.Jour of Engg and Innovative Technology (IJEIT): Vol.2, Issue.3, pp.166-170.
- [10] Sathiyamurthy S., Syed Abu Thaheer A. and Jayabal S. (2013) 'Prediction and Optimization of Mechanical Properties Of Particles Filled Coir-Polyester Composites Using ANN And RSM Algorithms'. Indian Jour of Fibers And Textile Research: Vol.38, pp.81-86.
- [11] MohiniSaxena, AsokanPappu, Anusha Sharma, RuhiHaque and SonalWankhede, "Advances in Composite Materials - Analysis of Natural and Man-Made Materials" Composite Materials from Natural Resources: Council of Scientific & Industrial Research, pp.121-163.
- [12] Vishakh.R, M.Arvind and T.Mahesh, "Human Hair Reinforced Bio-Composites Environment Friendly Advanced Light Weight Composites" International Journal For Technological Research In Engineering, Vol.1, Issue 1, 2013, pp.26-30.
- [13] M.S.Prabhu, J. Naveen Raj And G. Vignesh, "Mechanical Characterization of Kenaf-Hair Reinforced Hybrid Composite", International Journal of Engineering Research And General Science Volume 3, Issue 4, 2015, pp.235-344.
- [14] K B Jagadeeshgouda, P Ravinder Reddy And K Ishwaraprasad, "Experimental Study of Behaviour of Poultry Feather Fiber - A Reinforcing Material For Composites", IJRET: International Journal Of Research In Engineering And Technology, Volume: 03 Issue: 02, 2014, pp.362-371.
- [15] A.L. Martı́nez-Hernańdez, C. Velasco-Santos, M. de-Icaza, Victor M. Castaño, "Dynamical-mechanical and thermal analysis of polymeric composites reinforced with keratin biofibers from chicken feathers", Composites: Part B 38 (2007), pp.405–410.





10.22214/IJRASET



45.98



IMPACT FACTOR:  
7.129



IMPACT FACTOR:  
7.429



# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089  (24\*7 Support on Whatsapp)