



INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Volume: 11 Issue: IX Month of publication: September 2023

DOI: https://doi.org/10.22214/ijraset.2023.55671

www.ijraset.com

Call: © 08813907089 E-mail ID: ijraset@gmail.com

ISSN: 2321-9653; IC Value: 45.98; SJ Impact Factor: 7.538

Volume 11 Issue IX Sep 2023- Available at www.ijraset.com

Determination of Optimum Usage of Basalt in Strengthening of Concrete

Mohd Vasique Hussain¹, Satyendra Dubey²

¹Assistant Professor, Department of Civil Engineering, College of Agriculture Engineering, Jabalpur, India ²Assistant Professor, Department of Civil Engineering, G.G.C.T, Jabalpur, India

Abstract: Strength is one of the most important properties of concrete and now a days different material are being used to enhance the strength property of concrete. The research aims to study the effect of basalt fibre on strength of concrete. M30 grade of concrete was used in this experiment. Basalt fibre were added in different proportion as 0%, 0.1%, 0.2% and 0.3% by volume of concrete. Tests were conducted to determine the compressive strength, split tensile strength and bending strength of concrete. A gain in strength of concrete was observed when basalt fibre was used at 0.2% by volume of concrete.

Keywords: Concrete, Basalt, Basalt fibre, pozzolana, split tensile strength, compressive strength, bending strength.

I. INTRODUCTION

Basalt is an extrusive igneous rock. It is formed from rapid cooling of lava having low viscosity. On earth basalt is found in abundance, around 90% of volcanic rock is basalt. The richness in silica content of basalt is responsible for its low viscosity. Basalt fibre is derived from the fine fibres of basalt which has better physicomechanial properties than other fibres used in construction such as fiberglass. It is much cheaper than other fibres and is also easily available. Crushed basalt rock are melted at 1500° C and continuous filament of basalt fibres are produced having high specific strength and increased elastic modulus. Out of those fibres, the thicker one is used in the form of chopped strand for reinforcement in concrete. Several researches have been carried out to increase the strength of concrete by addition of different silicious material. The effect of basalt fibre on the strength of concrete was investigated and increase in strength property of concrete is found . The research aims to find the correct proportioning of basalt fibre for its optimum usage for enhancing the strength of concrete.

II. MATERIAL USED

For conducting experimental study following materials has been used:

- 1) Cement :OPC 53 grade cement was used for experimental purpose.
- 2) Fine aggregate: Sand conforming to zone II were used, passing from 4.75mm sieve and retained on 60 micron sieve.
- 3) Coarse aggregate: maximum 20mm size coarse aggregate were used.
- 4) Basalt fibre: basalt fibre of length 16mm were used for experimental purpose.

Table 1: Properties of basalt fibre

Length	Density	Break	Modulus of	Tensile strength	Water absorption
		elongation	elasticity		
16 mm	2.61 g/cc	3.12 %	84 Gpa	4.25 Mpa	<0.4

Table 2: Chemical composition of basalt fibre

S.No	Chemical name	Composition
1	Sio ₂	50.7 % - 57.8 %
2	Al_2O_3	14 % - 16.9 %
3	CaO	5.6 % - 8.8 %
4	MgO	3.5% - 5.8%
5	$Na_2O + K_2O$	3.9 % - 6.1%
6	TiO ₂	0.8% - 2.22%
7	$Fe_2O_3 + FeO$	9.3% - 15.6 %
8	Others	0.09% - 0.23%



ISSN: 2321-9653; IC Value: 45.98; SJ Impact Factor: 7.538

Volume 11 Issue IX Sep 2023- Available at www.ijraset.com

III. SPECIMEN DETAILS

Cubes specimen of standard size were casted for determination of compressive strength and cylinder specimen were casted for the split tensile strength. For determining bending strength molds were casted. Basalt fibre was added in different proportion as 0%, 0.1%, 0.2% and 0.3% by volume of concrete in experimental specimens. Design mix of M30 grade concrete was used and specimen were tested after 28days.

Table 3: Specimen Detail

S.no	Proportion of	Length of	Specimen	Cube specimen	Cylindrical	Specimen size
	basalt fibre	basalt fibre	quantity	size for	specimen size for	for bending
				compressive	split tensile	strength
				strength	strength	
1	0 %	-	3	150 x 150 x 150	150mm diameter	100 mm x 100
				mm		mm x 500mm
2	0.1 %	16 mm	3	150 x 150 x 150	150mm diameter	100 mm x 100
				mm		mm x 500mm
3	0.2 %	16 mm	3	150 x 150 x 150	150mm diameter	100 mm x 100
				mm		mm x 500mm
4	0.3 %	16 mm	3	150 x 150 x 150	150mm diameter	100 mm x 100
				mm		mm x 500mm

IV. EXPERIMENTAL INVESTIGATION

Specimen were casted for different proportions of basalt fibre and test were performed under standard procedure and conditions after 28 days of curing.

Table 4: Compressive strength of cube specimen

S.No	Detail of cube specimen	Number of cube sample	Average Compressive strength
1	BFRCCS 0	3	32.23 Mpa
2	BFRCCS 0.1	3	34.19 Mpa
3	BFRCCS 0.2	3	35.25 Mpa
4	BFRCCS 0.3	3	31.88 Mpa

Table 5: Split Tensile strength of cylindrical specimen

S.No	Detail of	cylindrical	Number of cylindrical sample	Average split Tensile strength
	specimen			
1	BFRCTS 0		3	2.83 Mpa
2	BFRCTS 0.1		3	3.21 Mpa
3	BFRCTS 0.2		3	3.95 Mpa
4	BFRCTS 0.3		3	3.15 Mpa

Table 6: Bending strength of concrete specimen

S.No	Detail of specimen	Number of sample	Average bending strength
1	BFRBS 0	3	4.35 Mpa
2	BFRBS 0.1	3	4.72 Mpa
3	BFRBS 0.2	3	4.98 Mpa
4	BFRBS 0.3	3	4.53 Mpa

ISSN: 2321-9653; IC Value: 45.98; SJ Impact Factor: 7.538 Volume 11 Issue IX Sep 2023- Available at www.ijraset.com

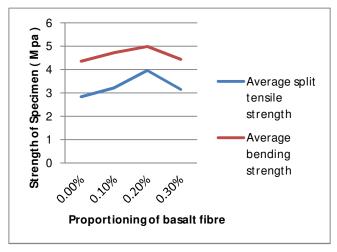


Figure 1 : Compressive strength of concrete

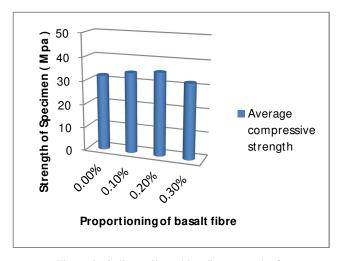


Figure 2 : Split tensile and bending strength of concrete

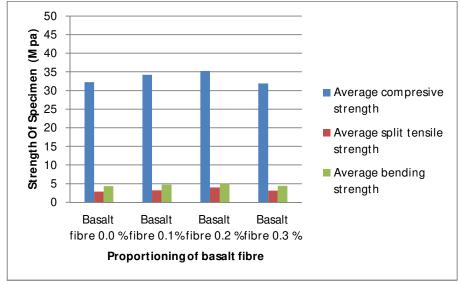


Figure 3: Comparative analysis for strength of concrete



International Journal for Research in Applied Science & Engineering Technology (IJRASET)

ISSN: 2321-9653; IC Value: 45.98; SJ Impact Factor: 7.538 Volume 11 Issue IX Sep 2023- Available at www.ijraset.com

V. RESULT AND DISCUSSION

There was an increase in strength of concrete specimen on addition of basalt fibre. The addition of basalt fibre of 0.2 % by volume of concrete provides the better result as compared to the conventional mix concrete and it was found that further increase in amount of basalt fibre tends to reduce the strength of concrete. The use of basalt fibre in low composites for concrete construction may provide better strength at lower cost of basalt fibre.

REFERENCES

- [1] Bureau of Indian Standards "Plain and Reinforced concrete code for practice "IS 456:2000
- [2] Sangmesh V Biradar, M Sai Dileep, Dr T Vijaya Gowri "Study of concrete mechanical properties with basalt fibre" IOP conference series Material science and Engineering 2020
- [3] Krishan Pareek, Dr Purnachandra Saha "Basalt fibre and its composites: An overview "COAST 2019
- [4] Navnath Raut, Urmila Kawade "Conventional concrete by using basalt fibre "IRJET vol 4, issue 7 2017
- [5] K.Sathes Kumar, K. Tamilarasan, N.Sathish Kumar, "Analysis of basalt fibre in concrete "IJCR, 2017
- [6] Maria Wlodarczyka, Igor Jedrejewskia "Concrete slab strengthened with basalt fibre "Experimental tesr results Procedia Engineering 153 (2016) 866-873
- [7] Elshafie, S. and Whittleston. G. "A review of the effect of baalt fibre length and proportion on the mechanical properties of concrete, IJRET VOI 4, Issue 1-2015
- [8] GAuvin F., Cousin P. and Robert M. "Improvement of interphase between basalt fibres and vinylester by nano reinforced post sizing "2015
- [9] Mr Gore Ketan R, Suhasinu M Kulkarni "The performance of basalt fibre in high strength concrete" journal of information, Knowledge and research in civil engineering, vol 2, issue 2 2013
- [10] A. Tabsheer, A. Abid, Experimental study on mechanical properties of basalt fibre reinforced concreten. IJSR 2013









45.98



IMPACT FACTOR: 7.129



IMPACT FACTOR: 7.429



INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call: 08813907089 🕓 (24*7 Support on Whatsapp)