



# IJRASET

International Journal For Research in  
Applied Science and Engineering Technology



---

# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

---

**Volume:** 13    **Issue:** IV    **Month of publication:** April 2025

**DOI:** <https://doi.org/10.22214/ijraset.2025.69913>

[www.ijraset.com](http://www.ijraset.com)

Call:  08813907089

E-mail ID: [ijraset@gmail.com](mailto:ijraset@gmail.com)

# Influence of Fibres on Concrete

Sanket J Agham<sup>1</sup>, Yash R Deore<sup>2</sup>, Tanmay Metangale<sup>3</sup>, Prerna Sharma<sup>4</sup>, Dr. S. N. Khante<sup>5</sup>

<sup>1, 2, 3, 4</sup> Civil Engineering, Government College Of Engineering, Nagpur, India

<sup>5</sup> Associate Professor, Government College Of Engineering, Nagpur, India

**Abstract:** Concrete is the most widely used construction material, but its compressive strength can be limited by its brittle nature and susceptibility to cracking. This study investigates the effects of hybrid fiber reinforcement on the compressive strength of concrete by incorporating different types of fibers, such as steel, polypropylene, and glass, in varying proportions. A comparative analysis was conducted to assess the influence of hybrid fibers on strength development over time. Experimental results indicate that hybrid fiber-reinforced concrete (HFRC) exhibits significantly higher compressive strength compared to conventional concrete. The synergistic effect of multiple fiber types enhances load distribution and resistance to failure under compressive loads. This research highlights the potential of HFRC for high-performance structural applications, recommending further studies on optimizing fiber proportions for maximum compressive strength.

**Keywords:** Concrete, Hybrid Fiber, Compressive Strength, Steel Fiber, Polypropylene Fiber, Glass Fiber.

## I. INTRODUCTION

Concrete is pivotal to modern infrastructure, owing to its excellent compressive strength, durability, and economic feasibility. It is extensively employed in bridges, tall structures, pavements, and other load-intensive applications. Nonetheless, traditional concrete suffers from brittleness and crack susceptibility, especially under high loads, leading to reduced durability and potential structural failures over time.

To overcome these limitations, fiber reinforcement has emerged as a prominent solution. Fibers act to bridge cracks, redistribute stress, and enhance the overall structural integrity of concrete. Particularly, Hybrid Fiber-Reinforced Concrete (HFRC)—which integrates multiple fiber types such as steel, polypropylene, and glass—has shown superior performance compared to single-fiber reinforcement. Each fiber type offers distinct advantages: steel fibers improve strength and toughness, while synthetic fibers like polypropylene control shrinkage cracking and enhance ductility.

Past research has consistently demonstrated that hybrid reinforcement strategies can notably augment compressive strength and durability. However, the effectiveness of HFRC largely depends on fiber selection, proportioning, and distribution. This study focuses on analyzing the influence of hybrid fiber combinations on compressive strength, aiming to develop an optimized fiber-reinforced concrete for sustainable and resilient construction.

## II. METHODOLOGY

Concrete mixes were designed for M25 and M30 grades. The quantities for M25 and M30 are shown in table below. Standard procedures were followed, where cement (OPC), fine aggregates, coarse aggregates, and potable water were used. Concrete cubes of dimensions 150 mm × 150 mm × 150 mm were cast.

Table A.1 Material Quantity for M25 and M30

| Materials        | Quantity( M25) | Cost Rs/(1m <sup>3</sup> ) (M25) | Quantity (M30) | Cost Rs/(1m <sup>3</sup> ) (M30) |
|------------------|----------------|----------------------------------|----------------|----------------------------------|
| Cement           | 350.38kg       | 2452.45/-                        | 366.35kg       | 2564.45/-                        |
| Water            | 164.68kg       | 0                                | 164.86kg       | 0                                |
| Coarse Aggregate | 986.26kg       | 1007.95/-                        | 989.22kg       | 1010.98/-                        |
| Fine Aggregate   | 716.50kg       | 1528.29/-                        | 697.88kg       | 1488.51/-                        |
| Plasticizer      | 0.70kg         | 70/-                             | 1.097kg        | 109.7/-                          |
| Total            |                | 5173.64/-                        |                | 5058.69/-                        |

Cube moulds were cleaned, oiled, and assembled prior to casting. Mixing was performed mechanically for at least 3 minutes, followed by placing the mix in moulds in three layers with each layer compacted by tamping 25 times.

Post 24-hour casting, specimens were demoulded, labeled, and cured in water tanks for periods of 3, 7, and 28 days.

*Fiber Types and Dosages*

Concrete was reinforced with different fibers:

- a. Glass fibers at 0.33%, 0.67%, and 1% by volume
- b. Steel hooked fibers at 0.2%, 0.4%, and 0.7% by volume
- c. Steel plain fibers at 0.2%, 0.4%, and 0.7% by volume
- d. Polypropylene Macro fibre at 0.2%, 0.4%, and 0.6% by volume
- e. Polypropylene Micro fibre at 0.2%, 0.4%, and 0.6% by volume

Hybrid fiber combinations were also cast:

- a. Steel plain (0.25%) + Steel hooked (0.25%) + Glass fiber (0.5%)
- b. Polypropylene macro (0.25%) + Polypropylene micro (0.25%) + Glass fiber (0.5%)
- c. Steel plain (0.25%) + Steel hooked (0.25%) + Polypropylene macro (0.25%) + Polypropylene micro (0.25%)
- d. Steel hooked (0.5%) + Glass fiber (0.5%)
- e. Polypropylene macro (0.5%) + Steel hooked (0.5%)
- f. Steel plain (0.5%) + Glass fiber (0.5%)

*Testing Procedures*

At the end of the curing periods, compressive strength tests were conducted on a Compression Testing Machine (CTM). The average compressive strength was calculated for each set of three cubes.

**III. RESULTS AND DISCUSSIONS**

The test results from compression test for control cube, single fibre specimen and hybrid fibres are given in table 4.1, table 4.2 and table 4.3 and results are discussed below.

Table A.2 Results of Control Specimens

| Grade of concrete mix | Days | Cube 1 (Mpa) | Cube 2 (Mpa) | Cube 3 (Mpa) | Average Compressive Strength (MPa) |
|-----------------------|------|--------------|--------------|--------------|------------------------------------|
| M25                   | 3    | 14.40        | 14.38        | 14.36        | 14.38                              |
| M25                   | 7    | 21.56        | 23.42        | 21.86        | 22.28                              |
| M25                   | 28   | 32.22        | 31.32        | 32.04        | 31.86                              |
| M30                   | 3    | 18.21        | 17.07        | 16.38        | 17.22                              |
| M30                   | 7    | 25.97        | 27.24        | 27.12        | 26.77                              |
| M30                   | 28   | 38.72        | 38.46        | 37.64        | 38.27                              |

Table A.3 Results of Individual Fibres Specimen

| Fibre and their percent | Days | Cube 1 (Mpa) | Cube 2 (Mpa) | Cube 3 (Mpa) | Average Compressive Strength (MPa) | Percent increase in compressive strength (%) |
|-------------------------|------|--------------|--------------|--------------|------------------------------------|--|
| Glass fibre (0.33%)     | 3    | 16.42        | 17.46        | 18.42        | 17.43                              | 21.02  |
| Glass fibre (0.33%)     | 7    | 26.66        | 27.46        | 26.62        | 26.91                              | 20.78  |
| Glass fibre (0.33%)     | 28   | 37.33        | 42.40        | 37.91        | 38.21                              | 19.93  |
| Glass fibre (0.67%)     | 3    | 17.36        | 18.06        | 18.12        | 17.84                              | 24.06  |

|                                   |    |       |       |       |        |       |
|-----------------------------------|----|-------|-------|-------|--------|-------|
| Glass fibre (0.67%)               | 7  | 25.15 | 25.86 | 26.75 | 25.92  | 16.33 |
| Glass fibre (0.67%)               | 28 | 39.33 | 38.22 | 38.46 | 38.67  | 21.37 |
| Glass fibre (1%)                  | 3  | 18.44 | 18.16 | 19.64 | 18.90  | 31.43 |
| Glass fibre (1%)                  | 7  | 27.25 | 27.55 | 27.73 | 27.50  | 23.42 |
| Glass fibre (1%)                  | 28 | 38.00 | 39.68 | 39.70 | 38.97  | 22.31 |
| Steel hooked fibre (0.2%)         | 3  | 17.42 | 17.89 | 18.13 | 17.81  | 23.85 |
| Steel hooked fibre (0.2%)         | 7  | 26.84 | 29.15 | 25.68 | 27.22  | 22.17 |
| Steel hooked fibre (0.2%)         | 28 | 38.36 | 38.56 | 38.41 | 38.44  | 20.65 |
| Steel hooked fibre (0.4%)         | 3  | 19.02 | 17.87 | 18.41 | 18.43  | 28.16 |
| Steel hooked fibre (0.4%)         | 7  | 27.11 | 27.33 | 28.08 | 27.50  | 23.42 |
| Steel hooked fibre (0.4%)         | 28 | 39.01 | 38.56 | 38.78 | 38.78  | 21.72 |
| Steel hooked fibre (0.7%)         | 3  | 19.12 | 18.48 | 20.22 | 19.27  | 34.00 |
| Steel hooked fibre (0.7%)         | 7  | 27.53 | 27.94 | 27.45 | 27.64  | 24.05 |
| Steel hooked fibre (0.7%)         | 28 | 39.33 | 38.48 | 39.22 | 39.003 | 22.41 |
| Steel plain fibre (0.2%)          | 3  | 18.12 | 17.56 | 17.47 | 17.71  | 23.15 |
| Steel plain fibre (0.2%)          | 7  | 27.42 | 26.31 | 27.12 | 26.95  | 20.96 |
| Steel plain fibre (0.2%)          | 28 | 37.87 | 38.94 | 38.12 | 38.31  | 20.24 |
| Steel plain fibre (0.4%)          | 3  | 17.92 | 18.48 | 18.77 | 18.39  | 27.88 |
| Steel plain fibre (0.4%)          | 7  | 28.04 | 26.72 | 27.36 | 27.37  | 22.84 |
| Steel plain fibre (0.4%)          | 28 | 38.19 | 39.56 | 37.97 | 38.57  | 21.06 |
| Steel plain fibre (0.7%)          | 3  | 18.48 | 19.12 | 20.11 | 19.23  | 33.72 |
| Steel plain fibre (0.7%)          | 7  | 26.92 | 27.39 | 28.66 | 27.65  | 24.10 |
| Steel plain fibre (0.7%)          | 28 | 38.77 | 39.04 | 39.87 | 39.22  | 23.10 |
| Macro Polypropylene Fibres (0.2%) | 3  | 15.23 | 16.59 | 17.24 | 16.3   | 13.35 |
| Macro Polypropylene Fibres (0.2%) | 7  | 26.68 | 26.17 | 24.86 | 25.90  | 16.24 |

|                                   |    |       |       |       |       |       |
|-----------------------------------|----|-------|-------|-------|-------|-------|
| Macro Polypropylene Fibres (0.2%) | 28 | 38.07 | 37.23 | 37.12 | 37.47 | 17.60 |
| Macro Polypropylene Fibres (0.4%) | 3  | 16.43 | 15.98 | 16.98 | 16.46 | 14.46 |
| Macro Polypropylene Fibres (0.4%) | 7  | 25.91 | 26.54 | 26.98 | 26.47 | 18.80 |
| Macro Polypropylene Fibres (0.4%) | 28 | 38.74 | 37.25 | 37.64 | 37.87 | 18.86 |
| Macro Polypropylene Fibres (0.6%) | 3  | 18.04 | 18.12 | 17.45 | 17.87 | 24.26 |
| Macro Polypropylene Fibres (0.6%) | 7  | 24.69 | 25.23 | 24.78 | 24.09 | 8.12  |
| Macro Polypropylene Fibres (0.6%) | 28 | 37.98 | 38.23 | 37.54 | 37.91 | 18.98 |
| Micro Polypropylene Fibres (0.2%) | 3  | 15.82 | 17.33 | 16.49 | 16.54 | 15.02 |
| Micro Polypropylene Fibres (0.2%) | 7  | 26.02 | 26.33 | 25.42 | 25.92 | 16.33 |
| Micro Polypropylene Fibres (0.2%) | 28 | 37.34 | 38.13 | 37.45 | 37.64 | 18.14 |
| Micro Polypropylene Fibres (0.4%) | 3  | 17.79 | 15.75 | 16.55 | 16.69 | 16.06 |
| Micro Polypropylene Fibres (0.4%) | 7  | 26.45 | 26.87 | 26.79 | 26.70 | 19.83 |
| Micro Polypropylene Fibres (0.4%) | 28 | 37.64 | 38.36 | 37.64 | 37.88 | 18.89 |
| Micro Polypropylene Fibres (0.6%) | 3  | 18.28 | 17.47 | 17.25 | 17.66 | 22.80 |
| Micro Polypropylene Fibres (0.6%) | 7  | 25.09 | 24.98 | 24.91 | 24.99 | 12.16 |
| Micro Polypropylene Fibres (0.6%) | 28 | 37.56 | 37.98 | 38.23 | 37.92 | 19.09 |

Table A.4 Results of Hybrid Fibres Specimen

| Hybrid fibre (1 % by vol in whole)   | Days | Cube 1 (Mpa) | Cube 2 (Mpa) | Cube 3 (Mpa) | Average Compressive Strength (MPa) | Percent increase in compressive strength (%) |
|--|------|--------------|--------------|--------------|------------------------------------|--|
| Steel plain (0.25%) + steel hooked (0.25%) + glass fibre (0.5%)  | 3    | 18.98        | 19.58        | 19.67        | 19.41                              | 34.97  |
| Steel plain (0.25%) + steel hooked (0.25%) + glass fibre (0.5%)  | 7    | 29.03        | 28.42        | 28.12        | 28.52                              | 28   |
| Steel plain (0.25%) + steel hooked (0.25%) + glass fibre (0.5%)  | 28   | 39.35        | 38.95        | 38.61        | 38.97                              | 22.31  |
| Polypropylene macro (0.25 %) + Polypropylene micro (0.25 %) + glass fibre (0.5%)                         | 3    | 18.42        | 19.67        | 19.13        | 19.07                              | 32.61  |
| Polypropylene macro (0.25 %) + Polypropylene micro (0.25 %) + glass fibre (0.5%)                         | 7    | 28.02        | 28.69        | 27.78        | 28.16                              | 26.39  |
| Polypropylene macro (0.25 %) + Polypropylene micro (0.25 %) + glass fibre (0.5%)                         | 28   | 38.66        | 37.98        | 37.87        | 38.17                              | 19.77  |
| Steel plain (0.25%) + steel hooked (0.25%) + Polypropylene macro (0.25 %) + Polypropylene micro (0.25 %) | 3    | 20.01        | 20.14        | 20.02        | 20.06                              | 39.49  |
| Steel plain (0.25%) + steel hooked (0.25%) + Polypropylene macro (0.25 %) + Polypropylene micro (0.25 %) | 7    | 29.87        | 29.42        | 29.11        | 29.46                              | 32.22  |
| Steel plain (0.25%) + steel hooked (0.25%) + Polypropylene   | 28   | 40.95        | 39.98        | 39.55        | 40.16                              | 26.05  |

|   |    |       |       |       |       |       |
|---|----|-------|-------|-------|-------|-------|
| macro (0.25 %) + Polypropylene micro (0.25 %)     |    |       |       |       |       |       |
| Steel hooked (0.5%) + glass fibre (0.5%)          | 3  | 19.42 | 19    | 19.31 | 19.24 | 33.79 |
| Steel hooked (0.5%) + glass fibre (0.5)           | 7  | 28.33 | 27.89 | 28.69 | 28.30 | 27.01 |
| Steel hooked (0.5%) + glass fibre (0.5)           | 28 | 38.15 | 38.22 | 39.25 | 38.54 | 20.96 |
| Polypropylene macro (0.5 %) + steel hooked (0.5%) | 3  | 19.43 | 18.22 | 18.41 | 18.69 | 29.97 |
| Polypropylene macro (0.5 %) + steel hooked (0.5%) | 7  | 27.13 | 27.58 | 27.89 | 27.53 | 23.56 |
| Polypropylene macro (0.5 %) + steel hooked (0.5%) | 28 | 38.21 | 38.74 | 37.74 | 38.23 | 20.01 |
| Steel plain (0.5%) + glass fibre (0.5%)           | 3  | 14.77 | 15.52 | 15.48 | 15.25 | 6.05  |
| Steel plain (0.5%) + glass fibre (0.5%)           | 7  | 22.41 | 21.98 | 22.78 | 22.39 | 0.49  |
| Steel plain (0.5%) + glass fibre (0.5%)           | 28 | 34.87 | 32.22 | 34.55 | 33.88 | 6.34  |

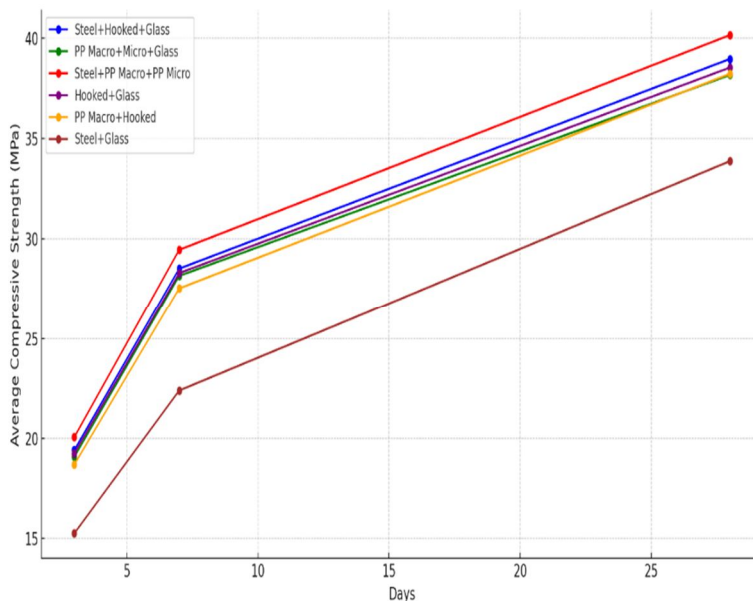


Fig.A.1 Graph of Compressive Strength vs. Curing Days for Hybrid Fibre Concrete

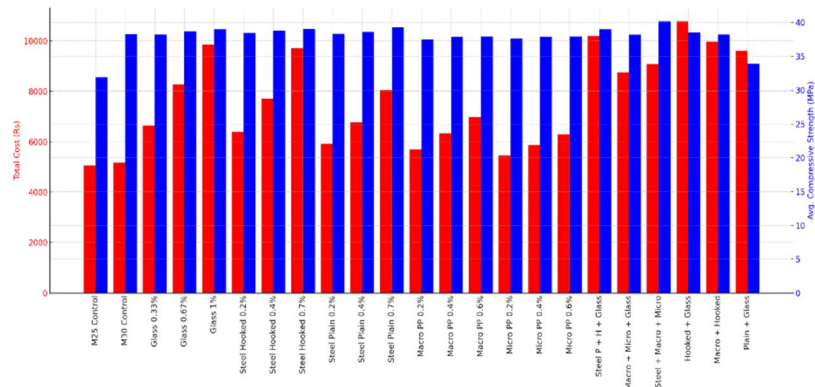


Fig.A.2 Comparison of Total Cost and Average Compressive Strength of Fibre-Reinforced Concrete Specimens

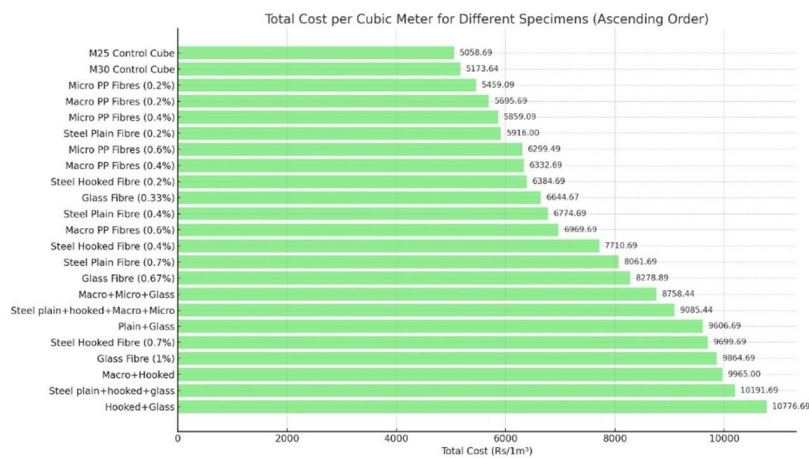


Fig.A.3 Total Cost per Cubic Meter for Different Specimens Arranged in Ascending Order

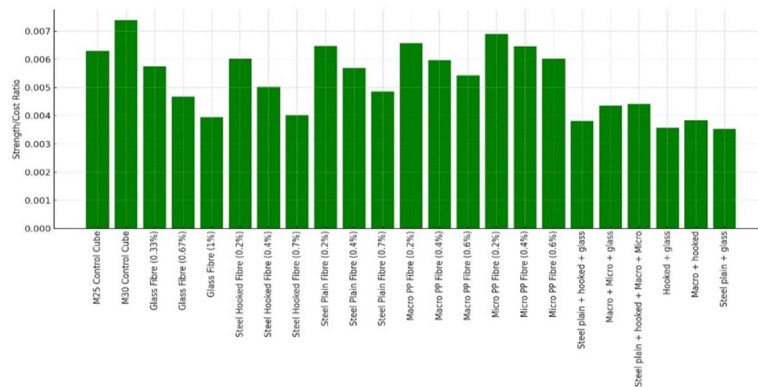


Fig.A.4 Strength-to-Cost Ratio of Concrete Specimens with Various Fibre Combinations

From the fig A.2 clearly illustrate the maximum compressive strength of 40.16 MPa was achieved using the hybrid combination of Steel plain (0.25%) + Steel hooked (0.25%) + Polypropylene macro (0.25%) + Polypropylene micro (0.25%), while the minimum compressive strength of 31.86 MPa was observed in the M25 control mix. In terms of cost, the highest cost was noted for the hybrid mix of Steel hooked (0.5%) + Glass fibre (0.5%) at ₹10,776.69 per m<sup>3</sup>, whereas the lowest cost was for the M25 control mix at ₹5,058.69 per m<sup>3</sup>. Considering both compressive strength and cost-effectiveness, the Steel Plain Fibre (0.2%) mix proved to be the most efficient, delivering a compressive strength of 38.31 MPa at a relatively low cost of ₹5,916 per m<sup>3</sup>, making it an optimal solution where high performance is needed within budget constraints.

The bar graphs in fig A.3 clearly illustrate the variation in total cost per cubic meter among different concrete specimens, both unmodified and reinforced with various fibers. The lowest costs are associated with control specimens and those containing micro or macro polypropylene fibers, indicating these options are more economical. As fiber content increases or combinations of different fibers are used, the cost tends to rise significantly. Notably, specimens combining steel hooked, steel plain, and glass fibers exhibit the highest costs, particularly the mix of steel hooked (0.5%) and glass fiber (0.5%), which tops the list. This suggests that while hybrid fiber combinations may offer enhanced mechanical properties, they come at a premium. Thus, the choice of fiber reinforcement should balance performance benefits with cost implications, depending on the specific application and budget constraints. The graph in fig .4 compares the strength-to-cost ratio of various concrete mixes, including M25 and M30 control cubes, individual fiber additions (glass, steel—plain and hooked, macro and micro polypropylene), and hybrid fiber combinations. Among all, steel hooked fiber (0.2%) show the highest cost efficiency. In terms of hybrid mixes, "Macro PP + Glass" exhibits the best strength-to-cost ratio, making it the most economical hybrid option. Overall, single-fiber mixes tend to be more cost-efficient, while hybrids offer enhanced performance with a trade-off in cost-effectiveness.

#### IV. CONCLUSION

Based on the result of test performed on the concrete specimen following conclusion can be drawn:

- 1) Hybrid fiber-reinforced concrete (HFRC) demonstrated a noticeable increase in compressive strength compared to conventional concrete, particularly at 28 days of curing.
- 2) The combination of steel hooked, steel plain, polypropylene (macro and micro), and glass fibers in optimal proportions led to improved strength performance due to the complementary behavior of each fiber type.
- 3) The best-performing hybrid mix—steel plain (0.25%) + steel hooked (0.25%) + polypropylene macro (0.25%) + polypropylene micro (0.25%)—achieved a maximum increase in compressive strength at 28 days over the control mix.
- 4) It was found that by using hybrid fibers, it is possible to achieve the compressive strength of M30 grade from an M25 grade base mix, however the cost reduction was not possible, on the contrary to some cases the cost was approximately double.
- 5) HFRC provides a sustainable construction solution, particularly by incorporating polypropylene and glass fibers, which can be derived from recycled or industrial waste materials.
- 6) Though hybrid fiber mixes are relatively costlier, they are suitable for applications where non cracking section and durability are essential. These include structures like water tanks where crack resistance is important, and industrial floors or workshop surfaces that require high abrasion resistance. In such cases, the performance benefits of hybrid fibers can justify the additional cost.
- 7) Despite improved strength, careful selection of fiber types and dosages is essential, as excessive or poorly balanced fiber content negatively impact cost.

#### REFERENCES

- [1] G.S.Sudhikumar, K.B.Prakash, M.V.Seshagiri Rao (2014) Effect of Aspect Ratio of Fibres on the Strength Characteristics of Slurry Infiltrated fibrous Ferrocement International Journal of Structural and Civil Engineering Research Vol.3,No. 2 May 2014
- [2] Komal Chawla (2013) Studies Of Glass Fiber Reinforced Concrete Composites International Journal of Structural and Civil Engineering Research Vol. 2, No. 3, August
- [3] H S Jadhav and M D Koli (2013) Flexural Behavior Of Hybrid Fiber Reinforced Concrete Beams International Journal of Structural and Civil Engineering Research Vol. 2, No. 3, August
- [4] N.Venkata Ramana, U.Raghu Babu and E.Aruna Kanthi (2021) Performance of Polyester And Polypropylene Fibres In Concrete International Journal of Scientific & Engineering Research Volume 7, Issue 4, April
- [5] Rajeev Chandak, R K Yadav and Kanhaiya Lal Thakur (2014) A Study of Strength of Steel Fiber Reinforced Concrete With Fly Ash International Journal of Structural and Civil Engineering Research Vol. 3, No. 1, February
- [6] G. Murali, A. S. Santhi and G. Mohan Ganesh (2014) Effect of Crimped and Hooked End Steel Fibres on the Impact Resistance of Concrete Journal of Applied Science and Engineering, Vol. 17, No. 3, pp. 259266S
- [7] Mohd. Gulfam Pathan Ajay Swarup (2017) A Review on Steel Fiber Reinforced Concrete International Journal of Advance Research in Science and Engineering Volume NO.6, Special Issue No (01), December
- [8] Archana P, Ashwini N Nayak, Sanjana R Nayak, Harshita Vaddar (2017) Study of Strength of Polypropylene Fiber Reinforced Concrete International Journal of Engineering Research & Technology Vol. 6 Issue 06, June
- [9] Süleyman Kamil Akın Sadrettin Sancıo glu , Saruhan Kartal , Ahmad Javid Zia, Abdullah Müsevito~ glu , Abdulkерim Ilgün Macro and micro polypropylene fiber effect on reinforced concrete beams with insufficient lap splice length Case Studies in Construction Materials
- [10] IS 10262:2019 - Concrete Mix Proportioning - Guidelines.
- [11] IS 12269: 1987 Specifications for 53 Grade of Ordinary Portland cement.
- [12] IS 2386 (Part III): 1963 Methods of Test For Aggregates For Concrete
- [13] IS 383:1970- Specification For Coarse And Fine Aggregates From Natural Sources For Concrete.



10.22214/IJRASET



45.98



IMPACT FACTOR:  
7.129



IMPACT FACTOR:  
7.429



# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089  (24\*7 Support on Whatsapp)