iJRASET
International Journal For Research in Applied Science and Engineering Technology



# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

**Volume:** 13 **Issue:** IV **Month of publication:** April 2025

**DOI:** https://doi.org/10.22214/ijraset.2025.69618

www.ijraset.com

Call: 08813907089 | E-mail ID: ijraset@gmail.com

International Journal for Research in Applied Science & Engineering Technology (IJRASET)
*ISSN: 2321-9653; IC Value: 45.98; SJ Impact Factor: 7.538*
*Volume 13 Issue IV Apr 2025- Available at www.ijraset.com*

# Study on Stabilization of Expansive Soil Using Fly Ash and Lime

Shubham Gupta[1], Shivam Mishra[2], Ankur Chaturvedi[3], Narayan Singh[4], Dr.Umank Mishra[5], Dr. Kruti Jethwa[6]

***Abstract:*** ***Expansive soil covers over 51.8 million hectares of land area in India (mainly Black Cotton soil). The basic trait of these expansive soils is that they are highly hard while dry but lose all of their strength when wet. Because of this attribute of expansive soils, these soils provide issues all around the world that geotechnical engineers must address. Soil stabilization, which is frequently utilised in foundation and road pavement constructions, is one of the most significant features for construction purposes; this is because such a stabilization regime increases engineering qualities of the soil, such as volume stability, strength, and durability. The problematic soil is removed or replaced throughout this operation is completed;The current study attempts to stabilise black cotton soil from Shivnath River Pulgaon Durg Bhilai utilizing fly ash sourced from JayPee Cement Limited Bhilai . Expansive soils are stabilized using different quantities of this Mixture, such as 10%, 20%, 25% . Because fly ash has no plastic characteristic, the plasticity index (P.I.) of clay-fly ash mixtures decreases in value as the fly ash component increases. Finally, the addition of fly ash reduces the flexibility of the expanding soil while increasing its workability by modifying its grain size and colloidal response. 3 trials of different composition are prepared and tested.***

## I. INTRODUCTION

The foundation is critical for any land-based project and must be strong enough to sustain the whole structure. The soil around the foundation is crucial to the foundation's strength. So, in order to work with soils, we must first understand their qualities and the variables that influence their behavior. The soil stabilization procedure aids in achieving the desired qualities of a soil for building operations. The need to improve soil qualities has been recognized since the outset of building activity. Soil stabilization was achieved in this study by using Fly ash and lime in various proportions and then performing several tests to proof soil stabilization.

## II. LITERATURE REVIEW

Hakari1 ,Udayashankar D2 has discussed in Indian geotechnical conference. (Dec-2010) has studied a use of fly ash for improves the property of black cotton soils of HubliDharwar region. The liquid limit decreases from 63% to 46%, plastic limit from 28.9% to 23.1% and the plasticity index from 34.1% to 22.9%; for the corresponding increase in the addition of DFA from 10% to 50% respectively. The shrinkage limit increases from 17.3% to 37% for increasing in the addition of DFA from 10% to 50% respectively the optimum moisture content decreases from 24.3% for M-10 mix to21.3% for M-50 mix. The CBR value Increases from0.77% for M-10 mix to 2.64% for M-50 mix.

S. Bhuvaneshwari ¹, R. G. Robinson ², S. R. Gandhi³ (FAUP), TIFAC, DST, New Delhi (2005) has also discussed the stabilization of expansive Soils using fly ash extensive laboratory / field trials have been carried Out by out to check the improvements in the properties of expansive soil with fly ash in varying percentages.

Sharma et al. (1992), using mixtures of fly ash, blast furnace slag and gypsum, studied stabilization. He found that when fly ash, gypsum and blast furnace slag are used in proportions of 6:12:18, the swelling pressure decreases from 248 KN/$m$2 to 17 KN/$m$2 , whereas an increase by 300% was observed in case of unconfined compressive strength.

Satyanarayana et al. (2004) aimed to study the mutual effect of addition of lime and fly ash on the engineering properties of the expansive soil. He found out that 70%, 26% and 4% were the optimum percent mixture of the ingredients for the construction of roads and embankment

## III. MATERIALS AND METHODOLOGY

### *A. Material*

#### *1) Expansive Soil*

Expansive soils, also known as swell-shrink soils, have a tendency to shrink and swell in response to changes in moisture content. As a result of this soil variance, considerable Distress begins in the soil, which is followed by harm to the underlying structure. These soils absorb water during periods of high rainfall, such as monsoons.

©IJRASET: All Rights are Reserved 

Swell; as a result, they become mushy and their water-holding capacity decreases. in contrast In addition, during drier seasons, such as summers, these soils lose the moisture they have stored. Evaporation, causing them to become tougher Typically found in semi-arid and dry climates.

*2) Fly Ash.*

Fly ash is a waste substance collected from the gases emitted by coal-fired furnaces, often at a thermal power station. One of the most common uses of volcanic ashes in ancient times was as hydraulic cements, and fly ash is quite similar to these 5 volcanic ashes. These ashes were thought to be one of the greatest pozzolans (binding agents) available in and around the world.

Because of the rising urbanisation and industrialisation, the need for electricity supply has increased tremendously. As a result of this expansion, the number of power providing thermal power plants that use coal as a burning fuel to generate electricity has increased.

*3) Lime*

The application of lime can significantly improve the engineering properties of soil. There are essentially two forms of improvement: soil modification and soil stabilization. The use of lime can modify almost all fine-grained soils to some extent, but the most dramatic improvement occurs in clay soils of moderate to high plasticity. Modification occurs primarily due to the exchange of calcium cations supplied by the hydrated lime for the normally present cation adsorbed on the surface of the clay mineral. Modification is also caused by the hydrated lime reacting with the clay mineral surface in a high-pH environment: the clay surface mineralogy is altered as it reacts with the calcium ions to form cementitious products. The results are plasticity and swelling reduction, reduced moisture-holding capacity and improved stability.

*B. Methodolgy*

- Mechanical method of Stabilization In this procedure, soils of different gradations are mixed together to obtain the desired property in the soil. This may be done at the site or at some other place from where it can be transported easily. The final mixture is then compacted by the usual methods to get the required density.
- Additive method of stabilization It refers to the addition of manufactured products into the soil, which in proper quantities enhances the quality of the soil. Materials such as cement, lime, bitumen, fly ash etc. are used as chemical additives. Sometimes different fibers are also used as reinforcements in the soil. The addition of these fibers takes place by two method.

*1) Collection of soil sample*

Expansive Soil sample is collected from the bank of shivnath River located near Pulgaon Chowk Durg.




*2) Tests Performed.*

To assess the effect of fly ash as a soil stabiliser, a series of tests were conducted in which the amount of fly ash in the soil was adjusted from 10% to 15% by weight of the total quantity collected and also lime is added in varying proportions which are as follows:-

- Test of original soil sample

- Test of mixture of 10% lime and 90% soil sample
- Test of mixture of 10% lime 10% Fly Ash and 80% soil sample
- Test of mixture of 10% lime 15% Fly Ash and 75% soil sample

During the process, the Indian Standard codes were followed. Carrying out the following experiments:
IS: 2720 (FOLLOWED) to perform the required tests :-
IS 2386 (Part 1) – Sieve Analysis Test
IS 2720 (Part 5) – Liquid and Plastic Limit Test – 1985
IS: 2720 (Part 8) – 1983 Modified proctor test
IS: 2720 (Part 16) – 1987 California bearing ratio (CBR) test

## IV. RESULT


### A. *Sieve Analysis Test.*

Source :- Shivnath River
Pulgaon Chowk (Durg)
Wt. of Sample:- 10kg

Table 1 : Sieve Analysis Test of Soil Sample

| Sieve size (mm) | Wt. retained (gm) | % weight retained | Cum % weight retained | % passing | Specific limit zones - II |
|---|---|---|---|---|---|
| 10 | 000 | 000 | 000 | 100 | 100 |
| 4.75 | 490 | 4.9 | 4.9 | 95.10 | 90-100 |
| 2.36 | 589 | 5.89 | 10.79 | 89.21 | 75-100 |
| 1.15 | 2800 | 28.00 | 38.79 | 61.21 | 55-90 |
| 0.600 | 2069 | 20.69 | 59.48 | 40.52 | 35-59 |
| 0.300 | 2631 | 26.31 | 85.79 | 14.21 | 8-30 |
| 0.123 | 1310 | 13.10 | 98.89 | 1.11 | 0-10 |
| Pan | FML 2.986% | | | | |

PASSED

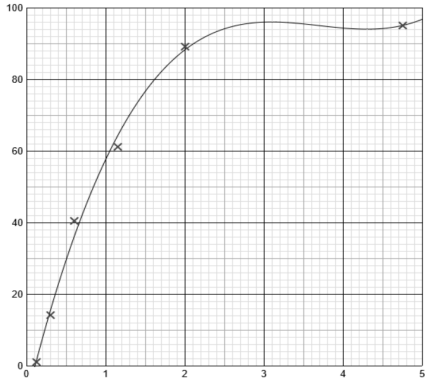




Graph showing variation in sieve size and percentage Passing

### B. *Atterberg Limit Test*


Table 2 : Atterberg limit Test for liquid and Plastic limit of sample soil

| Description | unit | Liquid limit | | | | Plastic limit | |
|---|---|---|---|---|---|---|---|
| | | 1 | 2 | 3 | 4 | 1 | 2 |
| No. of Blow | N | 17 | 22 | 27 | 32 | _ | _ |
| Container | No. | 6 | 8 | 7 | 1 | 3 | 5 |
| Wt. of Container + wet soil | Gm | 29.91 | 31.15 | 28.68 | 24.81 | 23.63 | 23.07 |

©IJRASET: All Rights are Reserved 

| | | | | | | | |
|---|---|---|---|---|---|---|---|
| Wt. of Container + dry soil | Gm | 25.86 | 26.93 | 24.76 | 21.54 | 23.57 | 21.43 |
| Wt. of Container | Gm | 14 | 14 | 12 | 10 | 14 | 14 |
| Wt. of water | Gm | 4.05 | 4.22 | 3.85 | 3.27 | 2.06 | 1.64 |
| Wt. of dry soil | Gm | 11.86 | 12.93 | 12.76 | 11.54 | 9.57 | 7.43 |
| Moisture content | % | 34.14 | 32.63 | 30.17 | 28.33 | 21.52 | 22.07 |

Average PL :21.79%
(General PL is near 23%)

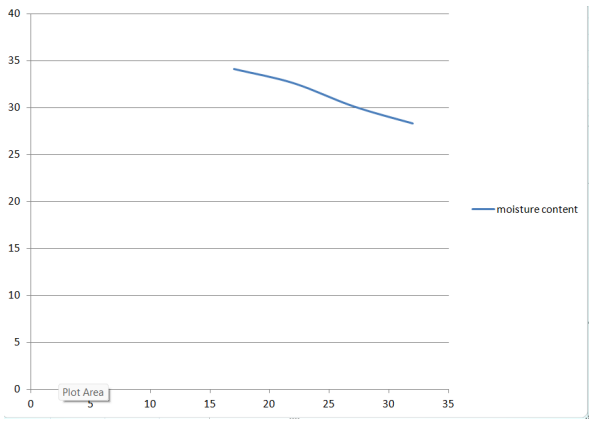


*C. Modified proctor Test*

Weight of mould = 6110gms
Volume of mould = 2250 cc
Metal rammer weight = 4.9 kg
Height of fall = 450mm
No. of Blow / layer = 55
No. of Layer =5




Table 3 : Modified proctor test of original soil sample

| Description | unit | Wt of Mould (A) = 6110 gms | | | | Mould no. (B) - 01 | |
|---|---|---|---|---|---|---|---|
| Trail with Moisture | % | 4% | 6% | 8% | 10% | 12% | |
| Volume of Mould | Cc | 2250 | 2250 | 2250 | 2250 | 2250 | 2250 |
| Wt. of wet soil + mould | gms | 10825 | 11152 | 11558 | 11668 | 11244 | |

©IJRASET: All Rights are Reserved | SJ Impact Factor 7.538 | ISRA Journal Impact Factor 7.894 |

| | | | | | | | |
|---|---|---|---|---|---|---|---|
| Wt of wet soil(E=D-A) | gms | 4715 | 5042 | 5448 | 5558 | 5134 | |
| Wet Density of soil (F= e/v) | g/cc | 2.096 | 2.241 | 2.421 | 2.470 | 2.281 | |
| Container no. | gms | 11 | 12 | 13 | 14 | 18 | |
| Wt. of container | gms | 50 | 54.0 | 53 | 54 | 54 | |
| Wt. of wet soil + container | gms | 171.71 | 178.90 | 173.39 | 185.68 | 193.33 | |
| Wt of dry soil + Cont. | gms | 167.15 | 173.31 | 166.46 | 173.71 | 178.63 | |
| Wt. of water ( L= J-K) | gms | 4.56 | 5.59 | 6.93 | 11.97 | 14.70 | |
| Wt. of dry soil (M = K – H) | gms | 117.15 | 119.31 | 113.46 | 119.71 | 124.63 | |
| Water content [ N = 100 x (L/M )] | % | 3.90 | 4.69 | 6.11 | 10 | 11.80 | |
| Dry density [P = 100 x( F/{100 +N))] | g/cc | 2.017 | 2.140 | 2.281 | 2.245 | 2.040 | |
| | | | | Method used = Modified | | | |

This test was conducted on the original soil sample. The following results were obtained:-Maximum Dry Density =2.34 g/cm3 Optimum Moisture Content = 8.0%

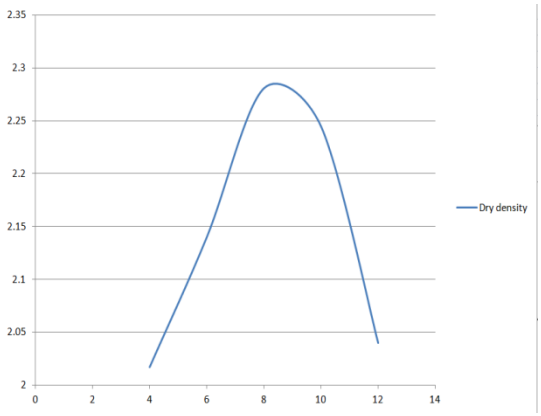



Modified proctor test of mixture of 10% lime and 90% soil sample

| Description | unit | Wt of Mould (A) = 6110 gms | | | | Mould no. (B) - 01 | |
|---|---|---|---|---|---|---|---|
| Trail with Moisture | % | 5% | 6% | 8% | 10% | 12% | |
| Volume of Mould | Cc | 2250 | 2250 | 2250 | 2250 | 2250 | 2250 |
| Wt. of wet soil + mould | gms | 10882 | 11282 | 11665 | 11730 | 11267 | |
| Wt of wet soil(E=D-A) | gms | 4772 | 5172 | 5555 | 5620 | 5157 | |
| Wet Density of soil (F= e/v) | g/cc | 2.121 | 2.299 | 2.469 | 2.498 | 2.292 | |
| Container no. | gms | 13 | 15 | 11 | 18 | 12 | |
| Wt. of container | gms | 53 | 50 | 50 | 54 | 54 | |
| Wt. of wet soil + container | gms | 173.94 | 174.32 | 174.59 | 187.12 | 187.71 | |
| Wt of dry soil + Cont. | gms | 170.31 | 169.49 | 168.09 | 175.25 | 174.23 | |
| Wt. of water ( L= J-K) | gms | 3.63 | 4.83 | 6.50 | 11.87 | 13.48 | |
| Wt. of dry soil (M = K – H) | gms | 117.31 | 119.49 | 118.09 | 121.25 | 120.23 | |
| Water content [ N = 100 x (L/M )] | % | 3.1 | 4.05 | 5.51 | 9.79 | 11.22 | |
| Dry density [P = 100 x( F/{100 +N))] | g/cc | 2.057 | 2.20 | 2.340 | 2.275 | 2.060 | |
| | | | | Method used = Modified | | | |

©IJRASET: All Rights are Reserved | SJ Impact Factor 7.538 | ISRA Journal Impact Factor 7.894 |

This test was conducted on the original soil sample. The following results were obtained:-Maximum Dry Density =2.41 g/cm3
Optimum Moisture Content = 7.5%

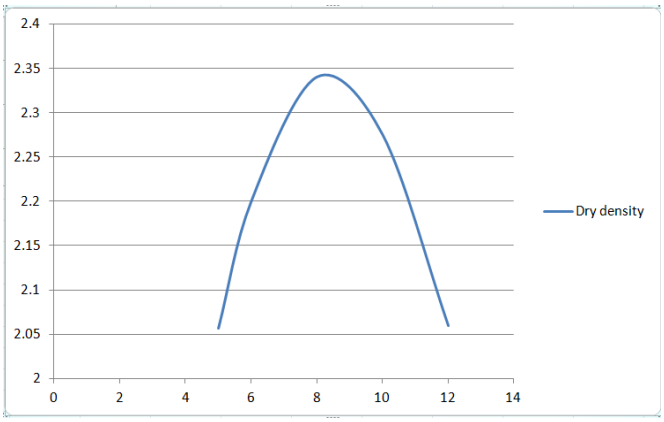


Graph Between Moisture content and Dry density

Table 5: Modified proctor test of mixture of 10% lime 15% Fly Ash and 75% soil sample

| Description | unit | Wt of Mould (A) = 6110 gms | | | | Mould no. (B) - 01 | |
|---|---|---|---|---|---|---|---|
| Trail with Moisture | % | 5% | 6% | 8% | 10% | 12% | |
| Volume of Mould | Cc | 2250 | 2250 | 2250 | 2250 | 2250 | 2250 |
| Wt. of wet soil + mould | gms | 10781 | 11316 | 11669 | 11656 | 11172 | |
| Wt of wet soil(E=D-A) | gms | 4671 | 5206 | 5559 | 5546 | 5062 | |
| Wet Density of soil (F= e/v) | g/cc | 2.076 | 2.314 | 2.471 | 2.665 | 2.250 | |
| Container no. | gms | 08 | 09 | 10 | 11 | 12 | |
| Wt. of container | gms | 54 | 50 | 52 | 50 | 54 | |
| Wt. of wet soil + container | gms | 177.16 | 175.56 | 180.74 | 180.83 | 184.20 | |
| Wt of dry soil + Cont. | gms | 173.87 | 170.56 | 173.73 | 169.48 | 171.20 | |
| Wt. of water ( L= J-K) | gms | 3.29 | 5 | 7.01 | 11.35 | 13 | |
| Wt. of dry soil (M = K – H) | gms | 119.87 | 120.56 | 121.73 | 119.48 | 117.20 | |
| Water content [ N = 100 x (L/M )] | % | 2.75 | 4.15 | 5.76 | 9.50 | 11.10 | |
| Dry density [P = 100 x( F/{100 +N))] | g/cc | 2.020 | 2.221 | 2.336 | 2.251 | 2.025 | |
| | | | | Method used = Modified | | | |

This test was conducted on the original soil sample. The following results were obtained:-Maximum Dry Density =2.37g/cm3
Optimum Moisture Content = 7%


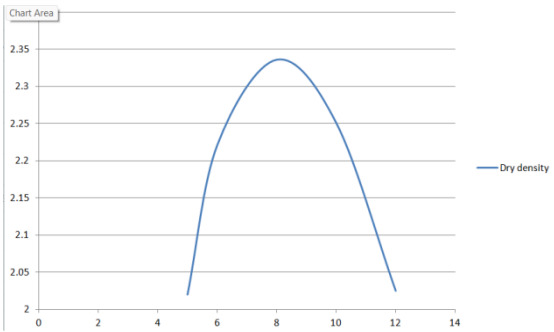


Table 6: Modified proctor test of mixture of 10% lime 25% Fly Ash and 65% soil sample

| Description | unit | Wt of Mould (A) = 6110 gms | | | | Mould no. (B) - 01 | |
|---|---|---|---|---|---|---|---|
| Trail with Moisture | % | 5% | 6% | 8% | 10% | 12% | |
| Volume of Mould | Cc | 2250 | 2250 | 2250 | 2250 | 2250 | 2250 |
| Wt. of wet soil + mould | gms | 10666 | 11197 | 11620 | 11361 | 11053 | |
| Wt of wet soil(E=D-A) | gms | 4556 | 5087 | 5510 | 5251 | 4943 | |
| Wet Density of soil (F= e/v) | g/cc | 2.025 | 2.261 | 2.449 | 2.334 | 2.197 | |
| Container no. | gms | 1 | 2 | 3 | 4 | 5 | |
| Wt. of container | gms | 54 | 54 | 52 | 50 | 50 | |
| Wt. of wet soil + container | gms | 176.04 | 178.34 | 179.59 | 178.71 | 180.58 | |
| Wt of dry soil + Cont. | gms | 172.82 | 117.91 | 173.36 | 168.09 | 163.74 | |
| Wt. of water ( L= J-K) | gms | 3.22 | 4.33 | 6.23 | 10.62 | 12.84 | |
| Wt. of dry soil (M = K – H) | gms | 118.82 | 119.91 | 121.36 | 118.09 | 117.74 | |
| Water content [ N = 100 x (L/M )] | % | 2.71 | 3.70 | 5.16 | 9 | 10.91 | |
| Dry density [P = 100 x( F/{100 +N))] | g/cc | 1.971 | 2.180 | 2.329 | 2.141 | 1.980 | |
| | | | | Method used = Modified | | | |

This test was conducted on the original soil sample. The following results were obtained:-Maximum Dry Density =2.370g/cm3 , Optimum Moisture Content = 6.5%

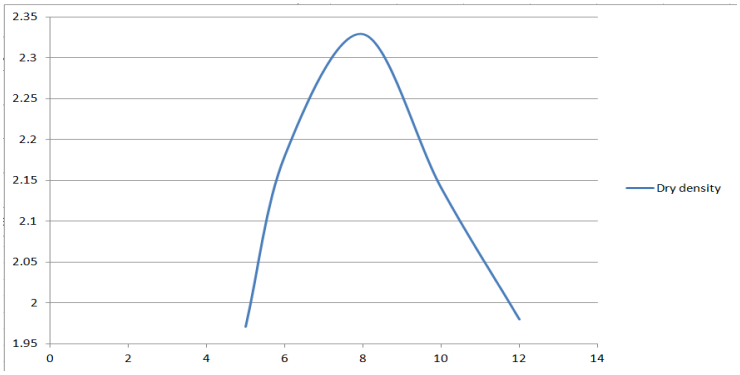


Graph b/w Moisture Content and Dry Density

Hence by performing modified proctor test We Can conclude mixture of 10% lime 15% Fly Ash and 75% soil sample is best composition to stabilize this expansive soil and for this composition we will determine the Extent upto which the CBR value increases.

*D. California Bearing Ratio (CBR) test for soil – fly ash mixture*


The California Bearing Ratio (CBR) is a measure of the strength of a road's subgrade and the materials used in its construction. The ratio is calculated using a standardised penetration test designed for highway engineering by the California Division of Highways

Table 7: CBR test For Original Soil Sample

| 1st Trail | | | | 2nd Trail | | | | 3rd Trail | | | |
|---|---|---|---|---|---|---|---|---|---|---|---|
| Penetration Reading in Dail | Proving Ring Divition | Load in Kg | CBR Value % | Penetration Reading in Dail | Proving Ring Divition | Load in Kg | CBR Value % | Penetration Reading in Dail | Proving Ring Divition | Load in Kg | CBR Value % |
| 0 | 0 | 0 | | 0 | 0 | 0 | | 0 | 0 | 0 | |
| 0.5 | 16 | 66.08 | | 0.5 | 17 | 66.5 | | 0.5 | 19 | 66.4 | |

| | | | | | | | | | | | |
|---|---|---|---|---|---|---|---|---|---|---|---|
| 1 | 19 | 78.87 | | 1 | 20 | 76.75 | | 1 | 23 | 78.5 | |
| 1.5 | 22 | 90.86 | | 1.5 | 21 | 87.56 | | 1.5 | 24 | 90.4 | |
| 2 | 25 | 103.25 | | 2 | 25 | 101.12 | | 2 | 26 | 102 | |
| 2.5 | 30 | 113.05 | 8.25 | 2.5 | 27 | 111.51 | 8.13 | 2.5 | 29 | 112 | 8.74 |
| 3 | 32 | 128.03 | | 3 | 32 | 125.0 | | 3 | 31 | 119.78 | |
| 4 | 37 | 152.81 | | 4 | 37 | 150.4 | | 4 | 37 | 127.64 | |
| 5 | 42 | 173.46 | 8.44 | 5 | 42 | 173.46 | 8.44 | 5 | 42 | 161.07 | 7.83 |
| 7.5 | 44 | 181.72 | | 7.5 | 47 | 194.50 | | 7.5 | 47 | 180.83 | |
| 10 | 47 | 194.11 | | 10 | 52 | 214.76 | | 10 | 52 | 194 | |
| 12.5 | 51 | 210.63 | | 12.5 | 56 | 231.28 | | 12.5 | 56 | 209.92 | |

Trial 3 sample should be taken because the CBR value here at 2.5 is greater than the CBR at 5 mm penetration. Hence CBR = 8.74%

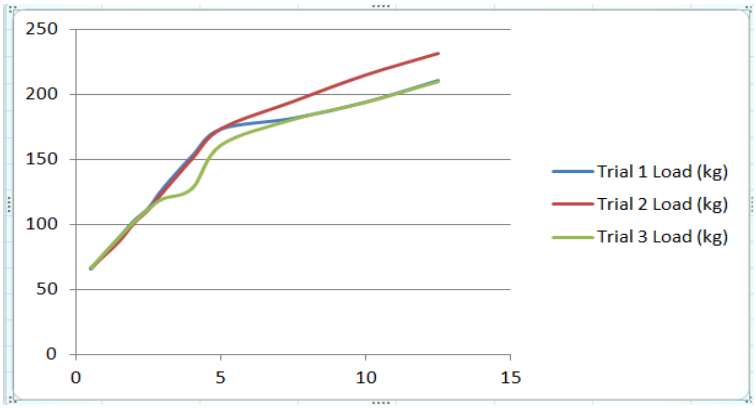


Curve Between penetration in mm and Load in Kg of original soil sample



Figure 8 CBR Machine


Table 8: CBR test for mixture of 10% lime 25% Fly Ash and 65% soil sample

| 1st Trail | | | | 2nd Trail | | | | 3rd Trail | | | |
|---|---|---|---|---|---|---|---|---|---|---|---|
| Penetration Reading in Dail | Proving Ring Divition | Load in Kg | CBR Value % | Penetration Reading in Dail | Proving Ring Divition | Load in Kg | CBR Value % | Penetration Reading in Dail | Proving Ring Divition | Load in Kg | CBR Value % |

| | | | | | | | | | | | |
|---|---|---|---|---|---|---|---|---|---|---|---|
| 0 | 0 | 0 | | 0 | 0 | 0 | | 0 | 0 | 0 | |
| 0.5 | 52 | 212.3 | | 0.5 | 51 | 210.6 | | 0.5 | 54 | 21.463 | |
| 1 | 58 | 232.8 | | 1 | 57 | 236.12 | | 1 | 60 | 239.73 | |
| 1.5 | 65 | 261.3 | | 1.5 | 65 | 269.3 | | 1.5 | 66 | 272.43 | |
| 2 | 71 | 287.79 | | 2 | 73 | 289.12 | | 2 | 75 | 291,76 | |
| 2.5 | 78 | 311.03 | 22.7 | 2.5 | 80 | 324.65 | 23.69 | 2.5 | 82 | 327.39 | 23.89 |
| 3 | 85 | 336.71 | | 3 | 86 | 343.01 | | 3 | 88 | 346.12 | |
| 4 | 91 | 364.85 | | 4 | 91 | 363.57 | | 4 | 93 | 369.46 | |
| 5 | 96 | 385.17 | 18.74 | 5 | 97 | 392.2 | 19.08 | 5 | 97 | 387.16 | 18.83 |
| 7.5 | 103 | 412.61 | | 7.5 | 104 | 418.65 | | 7.5 | 107 | 416.91 | |
| 10 | 109 | 437 | | 10 | 110 | 441.25 | | 10 | 113 | 444.53 | |
| 12.5 | 114 | 456.89 | | 12.5 | 116 | 468.74 | | 12.5 | 117 | 471.25 | |

Improved CBR of Mixed Composition = 22.7%

As our CBR value of original soil sample is increasing hense we can conclude that this soil of composition mixture of 10% lime 25% Fly Ash and 65% soil sample is stable and good for relevant construction.

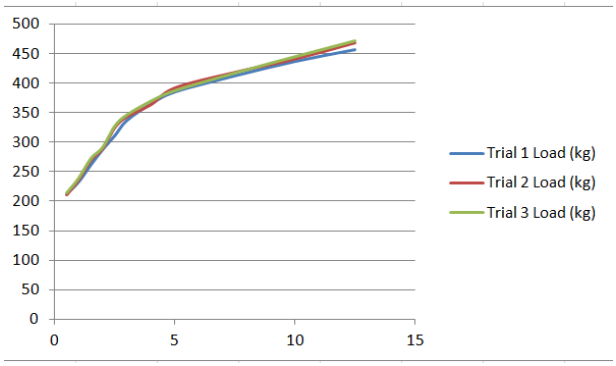


Curve Between penetration in mm and Load in Kg of mixed soil sample

## V. CONCLUSION

Based on the results obtained and comparisons made in the present study, the following conclusions can be drawn:

*1)* The addition of fly ash initially reduced the Maximum Dry Density (MDD) value of the black cotton soil. It then increased as the fly ash concentration in the soil-fly ash combination increased. The highest MDD value was found in a soil combination with 15% fly ash content by weight that is 2.41 gm/cm3. Following that, the MDD levels constantly declined.

*2)* In un-soaked California Bearing Ratio (CBR) tests of soil with varied fly ash content, the CBR steadily climbed with the rise in fly ash content until its value reached 20% by weight of the overall mixture; it then declined.

*3)* For CBR 3 trials are performed and the CBR of that trial is taken whose CBR% at 2.5 mm penetration is greater than 5mm penetration.

*4)* CBR value of original soil sample is increasing hense we can conclude that this soil of composition mixture of 10% lime 25% Fly Ash and 65% soil sample is stable and good for relevant construction.

As a result, using fly ash and lime as an addition reduces swelling while increasing the strength of the black cotton soil.

## REFERENCES


[1] Bose, B. (2012), "Geo-engineering Properties of Expansive Soil Stabilized with Fly Ash", Electronic Journal of Geotechnical Engineering, Vol. 17, pp. 1339-1353. .

[2] Kumar, A., Walia, B.S., and Bajaj, A. (2007), "Influence of Fly Ash, Lime and Polyester Fibers on Compaction and Strength Properties of Expansive Soil", Journal of Materials in Civil Engineering, Vol. 19, Issue 3, pp. 242-248.

[3] Malik, A., and Thapliyal, A. (2009), "Eco-friendly Fly Ash Utilization: Potential for Land Application", Critical Reviews in Environmental Science and Technology, Vol. 39, Issue 4, pp. 333-366.

[4] Misra, A., Biswas, D., and Upadhyaya, S. (2005), "Physico-mechanical behavior of self-cementing class C fly ash-clay minerals", J. Fuel, Vol. 84, pp. 1410-1422.
[5] Nath., P., and Sarker, P. (2011), "Effect of Fly Ash on the Durability Properties of High Strength Concrete", Procedia Engineering, Vol. 14, pp. 1149-1156.
[6] Phanikumar, B.R. and Sharma, R. S. (2004), "Effect of Fly Ash on Engineering Properties of Expansive Soil", Journal of Geotechnical and Geoenvironmental Engineering. Vol. 130, Issue 7, pp. 764-767.
[7] Nikumar, B.R., and Sharma, R. (2007), "Volume Change Behavior of Fly AshStabilized Clays", Journal of Materials in Civil Engineering, Vol. 19, SPECIAL ISSUE: Geochemical Aspects of Stabilized Materials, pp. 67–74.

©IJRASET: All Rights are Reserved | SJ Impact Factor 7.538 | ISRA Journal Impact Factor 7.894 |

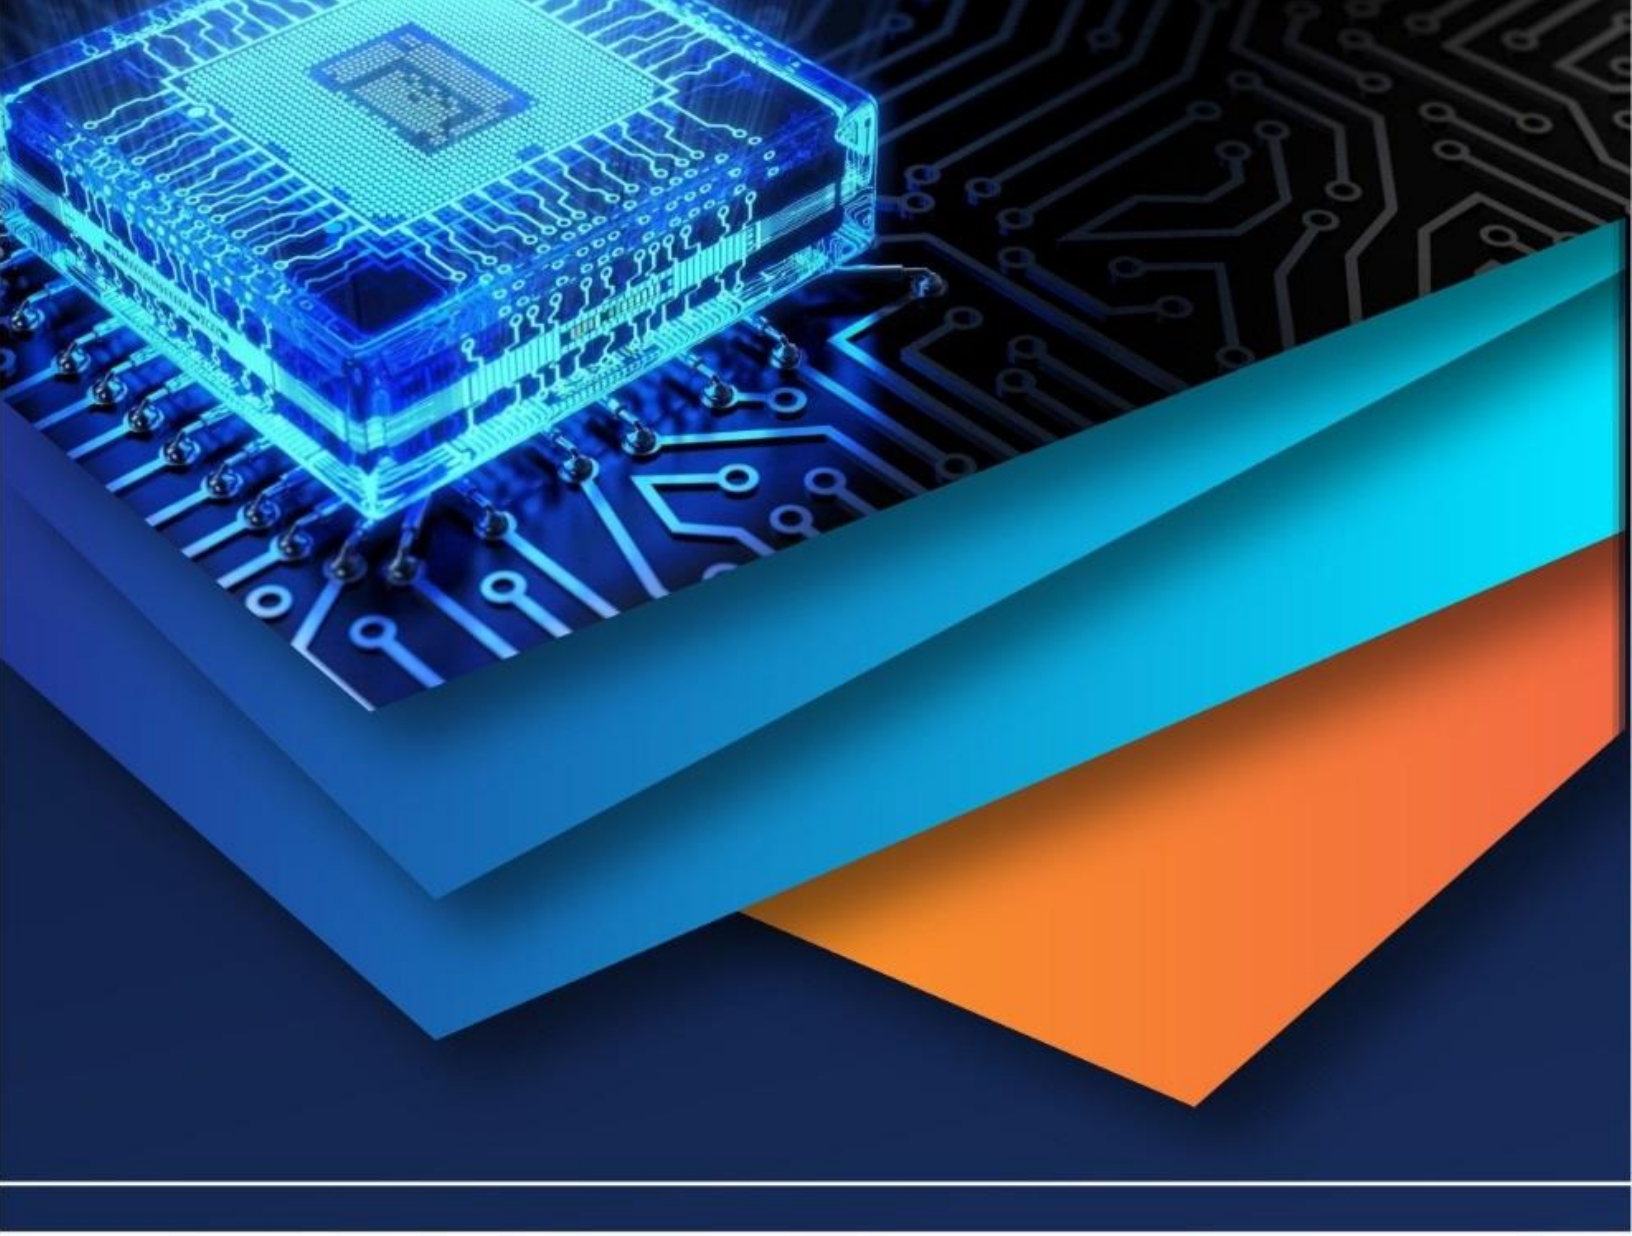

10.22214/IJRASET

45.98

IMPACT FACTOR: 7.129

IMPACT FACTOR: 7.429

# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089 (24*7 Support on Whatsapp)