



# **iJRASET**

International Journal For Research in  
Applied Science and Engineering Technology



---

# **INTERNATIONAL JOURNAL FOR RESEARCH**

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

---

**Volume: 6      Issue: I      Month of publication: January 2018**

**DOI: <http://doi.org/10.22214/ijraset.2018.1221>**

**[www.ijraset.com](http://www.ijraset.com)**

**Call: ☎ 08813907089**

**E-mail ID: [ijraset@gmail.com](mailto:ijraset@gmail.com)**

# Experimental Analysis of Tribological Properties of Hbn Nanoparticles Additive in Castor & Mahua Oil Blend

Mr. Naik Ashish Umaji<sup>1</sup>, Prof. Galhe D.S<sup>2</sup>

<sup>1</sup>PG Student, Jaihind College Of Engineering Kuran..

<sup>2</sup> Associate Professor, Jaihind College Of Engineering Kuran.

**Abstract:** *castor oil having competent lubrication properties are going to be present during this work with blends of mahua oil and antiwear characteristics with comparison against fossil oil lubricant for tribological properties. Analysis on bio lubricant within the field of automotive applications with experimentation on four ball tester for antiwear characteristics with numerous blends of castor and mahua oil are studied during this work. During this Paper result of addition with the nanoparticle hexagonal boron nitrate (hBN) in Castor and Mahua oil mix for improve the tribological properties of lubricants. These nano particle were added in blended oil at totally different proportions (0.5%,1%, and 2% wt. %). This investigation is beneficial for comparing the result of additives on bio lubricants properties like wear, coefficient of friction with commercial lubricant SAE 10W30 engine oil. The analysis of tribological properties take a look at was calculated on a four ball oil testing machine per ASTM D 4172 B. Result show that the every set of Nanoparticle considerably reduces the friction coefficient and wear of friction pairs. The damage surfaces were analyses by scanning microscope (SEM).*

**Keywords:** *Hbn nanoparticles, Castor and Mahua oil, Antiwear.*

## I. INTRODUCTION

Today, vegetable oils are being thought-about for their suitability as industrial lubricating substance. one in every of the most issues of vegetable oils is to envision performance once operating traditional operational conditions. During this paper, the performance of vegetable oils castor and mahua oil blends as a lubricant was tested employing a four ball tribometer under normal wear rate conditions that conforms to ASTM D4172. The test lubricants Castor and mahua oil mix with addition of 1.5 $\mu$  hBN nanoparticles, commercial lubricant were SAE 10W30 engine oil, business engine oil. The traditional load used for this take a look at was 192N.. The results showed that vegetable oils have a low friction coefficient compared to oil. Also, the damage scars created by vegetable oil is below those produced by oil. It are often concluded that vegetable oils have potential as lubricants.<sup>[10]</sup> Over the past decade the landscape of the lubrication marketplace has considerably modified thanks to a combination of environmental, health, economic and performance challenges. To handle these challenges it's essential to develop and use lubricants that come back from natural resources. Environment friendly or "Green" lubricants are renewable and frequently made up of vegetable oils e.g. rapeseed, canola, corn, oil, artificial esters and severely hydro treated crude primarily based oils. Compared to mineral and artificial oils, vegetable oils have variety of distinct benefits as well as considerably higher lubricity and viscousness, lower volatility and better shear stability. With higher biodegradable and toxicity properties than typical crude primarily based product, vegetable oils have tremendous potential to be used within the industrial sector.<sup>[16]</sup> The last word motivation is to analysis and develops a unique green lubricant which will be employed introducing process in industry method ability. The harm mechanisms beneath extreme environment are mentioned. Additionally, the longer term developing directions of h-BN and h-BN matrix composite ceramics are acknowledged. Use of Castor and mahua oil blends as base oil and h-BN nanoparticles as additives is studied during this paper.<sup>[2]</sup>

## II. MATERIALS AND MEHOD

### A. Base Oil

Castor oil is obtained from the seeds of castor plant and it is non-edible vegetable oil. The botanical name is ricinus communis and castor plant is from euphorbiaceae family.

### B. Blending Oil

Mahua oil has high flash point and high viscosity index properties. as bio lubricant

Castor oil 65% and mahua oil 35% blend is formed and testing for standard wear test is performed with four ball tester apparatus as per ASTM D4172 standard.

### C. Additive Nanoparticle

Hbn nanoparticles with 1.5 $\mu$  size are mixed with carbon and mahua oil blends in 0.55, 1% & 2% wt% of blended oil.

### D. Testing Apparatus

Ducom Four Ball Tester The Ducom four ball testers is use as the industry standard for conducting EP and AW property test of lubricants. Ducom four ball testers experimentally evaluate lubricants for their wear preventive, extreme pressure frictional properties all in one machine.

Table No.1 Properties of h-BN additive

Properties	Specifications
Formula	H-bn
Colour	White
Crystallie Form	Hexagonal
Melting Point ( $^{\circ}$ C)	1185
Density (kg/m <sup>3</sup> )	5.06

## III. EXPERIMENTAL ANALYSIS

### A. Design of Experiment

Table No. 2 Design of Experiment

Sample No	% of Mahua oil in Castor oil	hBN size ( $\mu$ )	hBN %
1	35% Mahua blend oil	1.5	0
2	35% Mahua blend oil	1.5	0.5
3	35% Mahua blend oil	1.5	1
4	35% Mahua blend oil	1.5	2

Before starting the experiment, all balls and their parts were cleaned with acetone and wiped. The tests were carried out as per the American Society for Testing Materials (ASTM) condition and usage of ASTM D 4172 method for tests.

Conditions: Temperature: (75  $\pm$  2)  $^{\circ}$ C,

Speed: (1200  $\pm$  60) rpm,

Time: (60  $\pm$  1) minute,

Load: (392  $\pm$  2) N.

## IV. RESULTS AND DISCUSSION

Performing experiments over Ducom four ball tester for an hour for each sample gives output of COF over frictional torque vs Time graph and WSD of four ball under high resolution image acquisition system of four ball tester

After comparing all samples frictional torque vs Time graph resulted comparison graph of 0.5%, 1% & 2% h-BN Nano particles of 1.5 $\mu$  with Mahua oil 35% + castor oil 65% is represented in Fig. No. 1

Comparison graph of Frictional torque vs Time for 0.5%, 1% & 2% h-BN Nano particles of 1.5 $\mu$  with Mahua oil 35% + castor oil 65% particles of 1.5 $\mu$  with Mahua oil 35% + castor oil 65%

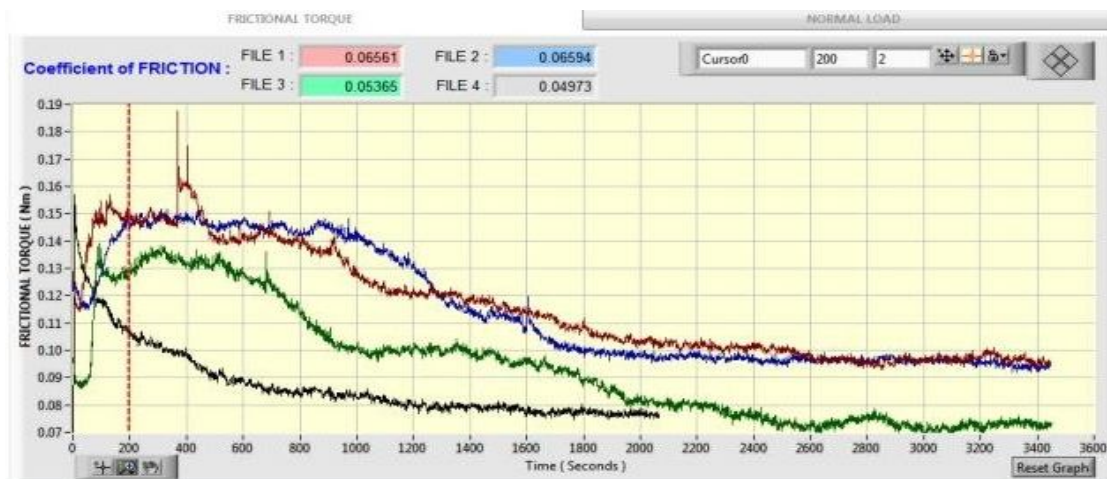


Fig. No. 1 Comparison graph of Frictional torque vs Time for 0.5%, 1% & 2% h-BN Nano particles of 1.5μ with Mahua oil 35% + castor oil 65%

## B. Result Table

Table No. 4 Result table for for 1.5 μ hBN nanoparticle Wear Data

Sr. No.	Sample Name	hBN 1.5 μ %	Readings				COF
			Major Wear scar dia. (mm)	Min. Wear scar dia (mm)	Avg. Wear scar dia. (mm)	Area (mm <sup>2</sup> )	
1	Mahau oil 35% + castor oil 65%	0%	220	207	214	0.036	0.06561
2	Mahau oil 35% + castor oil 65% + hBN 1.5 μ	0.5%	248	231	240	0.045	0.06554
3		1%	224	202	213	0.036	0.05365
4		2%	230	198	214	0.036	0.04973

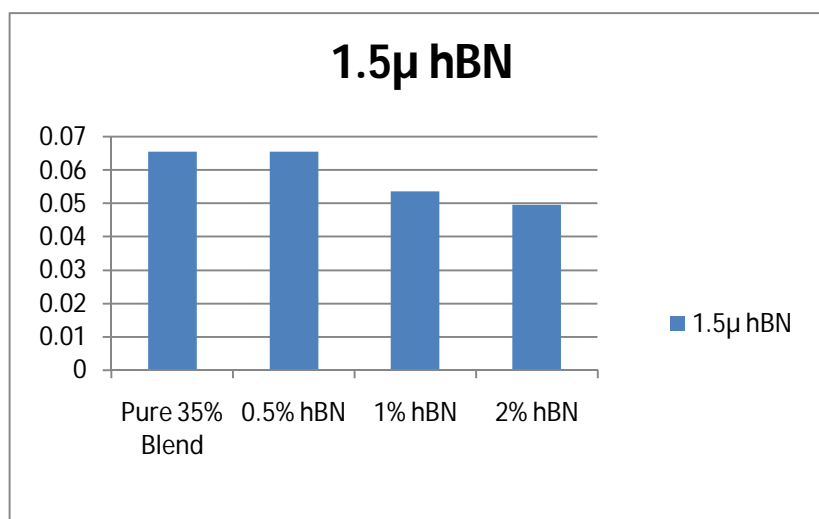


Fig. No. 2 Chart of COF of 1.5μ size & 0%, 0.5%, 1% & 2% wt% hBN



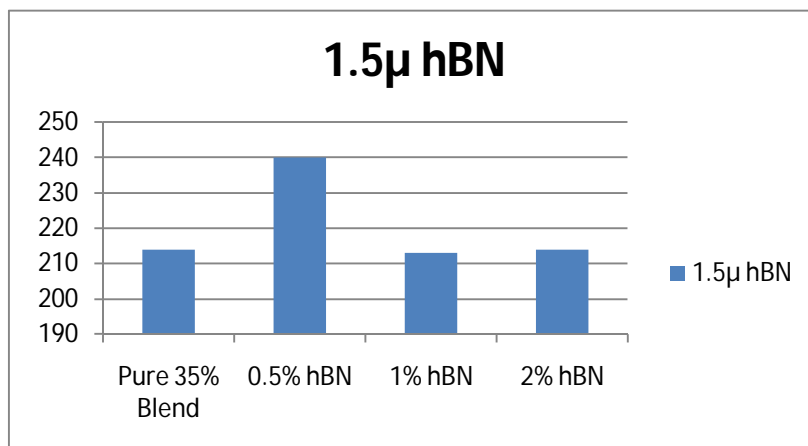


Fig. no. 3 Chart of WSD of 1.5μ size & 0%, 0.5%, 1% & 2% wt% hBN

From Table No.4 it is observed that with hBN nanoparticle size 1.5 μ when added in weight percentage of 0.5%, 1% & 2% in Castor and Mahua oil Blends hBN

Shows coefficient of friction drops from 0.06561 to 0.04973 when compared to SAE 10W30 OIL finds 49% lower.

WSD of the 0.5 wt% hBN is 240 Highest among other wt% of hBN and remaining 3 samples shows WSD in between 213 & 214 when compared with SAE 10W30 OIL finds 62% lower.

## V. CONCLUSION

Castor and mahua oil blends are showing lower value of COF and WSD than commercial engine oil.

hBN nanoparticles when added with castor and mahua oil blend shows improvement in antiwear properties of base oil.

1% wt% of hBN nanoparticles concentration in base oil finds optimum wear resistant properties however 0.5% wt% hBN concentration slightly increase WSD of balls.

## VI. ACKNOWLEDGMENT

I like to thank my guide Prof. Galhe D.S. for their valuable guidance and support in the research work. I am also thankful for all the staffs and friends for their support.

## REFERENCES

- [1] E. Prakash, R. Raja Raman, Dr. K. Sivakumar "Tribological Studies On Nano-Caco3 Additive Mixed Lubricant" e-ISSN: 2278-1684, p-ISSN: 2320-334X PP 68-7
- [2] Muhammad Ilman Hakimi Chua Abdullah, et al "Optimization of Tribological Performance of hBN/AL2O3 Nanoparticles Engine Oil Additives". Malaysian International Tribology Conference 2013, MITC2013
- [3] Qing ming Wan, et al "Tribological behaviour of a lubricant oil containing boron nitride Nanoparticles". The 7th World Congress on Particle Technology (WCPT7)- 2015
- [4] M. Asrul, N.W.M. Zulkiflia , H. H. Masjukia, M.A. Kalama "Tribological properties and lubricant mechanism of Nanoparticle in Engine Oil" Procedia Engineering 68 ( 2013 ) 320 – 325
- [5] Muhammad Ilman Hakimi Chua Abdullah, MohdFadzli Bin Abdollaha, HilmiAmiruddina, No reffendy Tamaldina, Nur Rashid Mat Nuria "Optimization of Tribological Performance of hBN/AL2O3Nanoparticles as Engine Oil Additives" Procedia Engineering 68 ( 2013 ) 313 – 319
- [6] Sudeep Ingole, Archana Charanpahari, AmolKakade , S.S. Umare , D.V. Bhatt , Jyoti Menghani "Tribological behavior of nanoTiO2 as an additive in base oil" Wear 301 (2013) 776–785
- [7] V .Ganachari, RavishankarBhat, Raghunandan Deshpande and Venkataraman A "Synthesis and characterization of nickel oxide nanoparticles by self-propagating low temperature combustion method" Recent Research in Science and Technology 2012, 4(4): 50-53
- [8] V. Zin1, F. Agresti1, S. Barison, L. Colla, and M. Fabrizio1 "Influence of Cu, TiO2 Nanoparticles and Carbon Nano-Horns on Tribological Properties of Engine Oil" J. Nanosci. Nanotechnol. 2015, Vol. 15, No. 51533-4880/2015/15/3590/009 doi:10.1166/jnn.2015.9839
- [9] XianbingJi, Yinxia Chen , Gaiqing Zhao Xiaobo Wang, Weimin Liu "Tribological Properties of CaCO3 Nanoparticles as an Additive in Lithium Grease" TribolLett (2011) 41:113–119 DOI 10.1007/s11249-010-9688-z
- [10] H.M. Mobarak et al, "The prospects of biolubricants as alternatives in automotive applications" Center for Energy Sciences University of Malaya, 20 February 2014.
- [11] D. Boopathi et al, "Experimental Investigation on Effect of Vegetable Oil based Lubricant for Diesel Engine" Indian Journal of Science and Technology, Vol 9(29), ISSN (Online) : 0974-5645, August 2014.
- [12] BinfaBongfa and Peter, "Comparison of lubricant properties of castor oil and commercial engine oil" JurnalTribologi 5 (2015) 1-1 pp.1-10, 28 May 2015.



- [13] ManikS.Nathe et al, “Effect of Castor Oil as Bio Lubricant on Tribological Properties of EN31 Steel” IJMTER, e-ISSN No.:2349-9745, Date: 28-30 April, 2016.
- [14] N.H. Jayadas et al, “Tribological evaluation of coconut oil as an environment- friendly lubricant” Tribology International 40 (2007) 350 – 354, 23March 2006.
- [15] Olasheu, T.I et al, “Characterization of Castor (Ricinus Communis) And Jatropha (Jatropha curcas) Oils As Alternative Base Oil For Automotive Lubricants” International Journal of Scientific & Engineering Research, Volume 5, Issue 8, ISSN 2229-5518 August-2014
- [16] Perna Singh Chauhan and Dr. V K Chhibber “Non-Edible Oil as a Source of Bio-Lubricant for Industrial Applications: A Review” International Journal of Engineering Science and Innovative Technology (IJESIT) Volume 2, Issue 1, January 2013
- [17] Standard Test Method for Measurement of Extreme-Pressure Properties of Lubricating Fluids (Four-Ball Method), An American National Standard



10.22214/IJRASET



45.98



IMPACT FACTOR:  
7.129



IMPACT FACTOR:  
7.429



# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089  (24\*7 Support on Whatsapp)