



iJRASET

International Journal For Research in
Applied Science and Engineering Technology



INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Volume: 6 Issue: III Month of publication: March 2018

DOI: <http://doi.org/10.22214/ijraset.2018.3658>

www.ijraset.com

Call:  08813907089

E-mail ID: ijraset@gmail.com

Development of Hybrid Al-MMC by an Innovative V-Process Assisted Stir Casting and Process Capability Evaluation

Swarndeeep Singh¹, Rupinder Singh², Simranpreet Singh Gill³

¹Research Scholar, IKG Punjab Technical University, Kapurthala (Pb.), India

²Dept. of Production Engineering, Guru Nanak Dev Engineering College, Ludhiana (Pb.), India

³Dept. of Mechanical Engineering, Beant College of Engineering and Technology, Gurdaspur (Pb.), India

Abstract: Aluminum based metal matrix composite (Al- MMC) are widely used due to their high strength to weight ratio, low cost and high wear resistance properties (especially in structural applications, aerospace and automobile industry). In this research work an attempt has been made to prepare Al-MMC with hybrid reinforcement (5%, 7.5% and 10% by weight) of double particle size (DPS) and triple particle size (TPS) Al_2O_3 and SiC, by using vacuum moulding (V-process) assisted stir casting process. Further process capability of the hybrid process has been evaluated in term of dimensional accuracy. The study highlights the percentage contribution of significant process parameters (particle size 9.19%, type of reinforcement 12.99%, vacuum pressure 35.18% and moulding sand grit size 28.10%) on the dimensional accuracy of hybrid Al-MMC. Finally the calculated value of process capability indices (Cpk) more than 1.3 highlighted that the developed hybrid process is statistically controlled for batch and mass production.

Keywords: Al-MMC; DPS; TPS; V-process; Process capability

I. INTRODUCTION

Aluminium metal matrix composites (Al-MMC) has become an attractive material for engineering application due to significantly improved properties like high specific strength, specific modulus, damping capacity and good wear resistance as compared to unreinforced alloys. Al-MMC's are widely used for the automobiles and aerospace industry and a variety of other applications [1] [2]. The new generation hybrid metal matrix composites (HMMC's) developed by the interaction of more than one type, shape and sizes of reinforcements have recently evoked the keen interest of the researchers due to their better tribological properties as compared to single reinforced composites [3] [4]. Hybridization gives more freedom to design a material for any specific application with less cost. In recent years, hybridization of reinforcements has gained significant importance in enhancing the properties of Metal Matrix Composites (MMCs) [5]. Gurcan & Baker [6], Wang et al. [7] and Park [8] developed hybrid Al-MMC / Al_2O_3 / SiC and observed the superior wear properties of hybrid composites. Suresha et al. [9] has also reported better wear resistance of Al-SiC-Gr hybrid composite. Therefore, hybrid MMC's are being developed to achieve high strength and superior tribological properties in comparison to the super-alloys and become the most preferred choice in the aerospace industry for structural application. The fabrication process and the type, shape, size & quantity of reinforcement governed the properties of the composites [10] [11]. However, the required properties can be attained successfully if the fabrication process is able to deliver requisite wetting, bonding, stability and homogeneous distribution of the reinforcement in the matrix [11]. Researchers have used the various techniques such as Stir Casting [11], Compocasting [12], Squeeze Casting [13], Powder Metallurgy [14] and Friction Stir Process [15] to fabricate hybrid composites. Among all these processing route, the stir casting is one of the most promising liquid metallurgy route used to fabricate Al-MMC due to its simplicity, flexibility and applicability for large scale production at comparatively low cost [16] [17]. The stir casting is a liquid state method has been widely used for the fabrication of composites, in which the reinforcement particles are uniformly mixed with a molten matrix metal by means of mechanical stirring [18]. The liquid composite material is then cast by die casting methods which need additional machining process to get exact size. The machining to get exact shape after casting of MMC component become difficult due to the abrasive nature of the reinforcement. As the complexity of part increases, exceptionally high cost and time is involved in the development, modification and repair of the dies.

The v- process/vacuum moulding (VM) was developed by Japanese in 1971 has emerged as a green technique for developing the mould of unbounded sand rigidized with vacuum (250 - 450 mm of Hg) [19]. The casting obtain from VM is free from draft allowance which further eradicate machining cost and time [20]. Apart from smooth casting with high degree of dimensional

accuracy, VM has many other advantages such as no sand moisture related defects, excellent sand permeability, no pollution due to burning of the binders to make it environment friendly, no defects like gas holes and reuse of moulding sand [19]-[23]. VM can be able to develop the mould with complex geometry in a short time which will help to eliminate the lead times for die generation. The lower solidification rate of metal in a vacuum mould also promotes the development of fine grain microstructure which further improves the mechanical properties [24][25]. Singh[26] and Boparai and Singh [27] has been suggested that vacuum moulding (VM) is a highly capable process for the development of Al- MMC and can be employed for batch/mass production activities.

Therefore, to develop near-net-shape geometries i.e. dimensional accuracy and to eliminate the shortcomings of die casting the vacuum moulding shows potential to be used for the fabrication of hybrid Al-MMC. The moulding sand size, vacuum pressure, duration of vibration and constitution and composition of composite are the crucial factors affects obviously the dimensional accuracy.

It is evident from literature that lot of research work has been reported for the fabrication of hybrid Al-MMC with stir casting [10] [11] and optimization of vacuum moulding [21] [25]-[32]. But hitherto very less work has been reported on combining vacuum moulding and stir casting (together) for the fabrication of the hybrid Al-MMC. Considering all these aspect the aim of the present study is to develop hybrid Al-MMC by innovative v-process assisted stir casting and its process capability evaluation in term of dimensional accuracy.

II. EXPERIMENTATION

A. Charged Material

Industrial pure (≥ 99.6 wt% Al) Al-6063 is used as a matrix material and detailed chemical composition is given in Table 1. Al_2O_3 and SiC of grit size 100(122 μ m), 120(102 μ m) and 150(89 μ m) are used as reinforcement and their properties are shown in Table 2. The double particle size (DPS) & triple particle size (TPS) reinforcement is obtained by mixing of 100 and 120 grit size and 100, 120 and 150 grit size in equal proportion, respectively.

TABLE 1 CHEMICAL COMPOSITION OF Al-6063

| Element | Si | Fe | Cu | Mn | Mg | Cr | Zn | Ti | Al |
|---------|---------|------|------|------|----------|------|------|------|---------|
| Wt % | 0.2-0.6 | 0.35 | 0.10 | 0.10 | 0.45-0.9 | 0.10 | 0.10 | 0.10 | Balance |

B. Fabrication Process

A disc of 50 mm diameter and 10 mm thickness was selected for this study (Fig.1) and the perforated pattern of the selected component was generated on FDM machine. The perforated pattern in placed at the center of the base plate and a preheated thin plastic sheet is drawn onto the pattern contour by imposing vacuum (300-400 mm of Hg). Then a mould box (drag) is placed on the base plate and the formed plastic sheet is fixed with the mould box. The dry un-bonded silica sand (AFS No. 50-70) fills in the mold box and get compacted with vibration (3-5 Sec.), the other open side of the mould box is sealed with second plastic sheet sealed and then vacuum is further applied to compact the sand. The vacuum of the base plate is released and the mold box is flipped off. The pattern is easily slipped out and second mould box (cope) is placed on the first mould box. The mold box is filled with dry unbounded sand and sealed with plastic sheet. The sand gets compactness with the application of vibration and vacuum. The proper gating arrangement is given in the cop. The two halves are properly sealed and the mold cavity under vacuum is ready for metal pouring. The schematic view of vacuum moulding setup is shown in Fig.2.

For the fabrication of Al-MMC, the required quantity of Al-6063 alloy was melted in a graphite crucible at 800°C and the reinforcement particles were preheated at 450°C to drive off the moisture before charging. A mild steel stirrer is immersed upto two thirds depth of the molten metal and stirred at the speed of 450 RPM. Magnesium (1wt. %) was further added during stirring to improve wetting and to reduce the agglomeration of reinforcing particles [11]. Finally, the molten metal was poured into the mould under negative pressure and get solidify. After cooling the vacuum is released and free-flowing sand drop away, leaving a clean required casting without sand lumps.

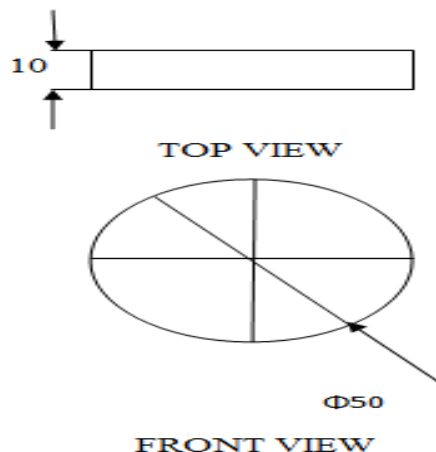


Fig. 1 Dimensions and 2D view of FDM based patterns.



Fig. 2 The schematic view of vacuum moulding.

In order to reduce the number of experiments Taguchi $L_{18} (2^1 \times 3^7)$ OA frame work has been employed for the fabrication of Al-MMC with hybrid reinforcement. It has one factor of two levels and five of three levels as given in Table 2. The other parameters like molten metal temperature; vibration frequency and plastic film thickness were kept constant. Three repetitions of experimentation at same setting have been performed in order to minimise the experimental error.

Table 2 Control Factors and Their Levels

| S.No. | Input factor | Designation | Levels | | | D.O.F. |
|-------|-----------------------------------|-------------|--------------------------------|-----|--------------------------------------|--------|
| | | | 1 | 2 | 3 | |
| 1 | Particle Size | A | DPS | TPS | - | 1 |
| 2 | Type of Reinforcement | B | Al ₂ O ₃ | SiC | Al ₂ O ₃ + SiC | 2 |
| 3 | Vacuum Pressure (mm of Hg) | C | 300 | 350 | 400 | 2 |
| 4 | Moulding Sand Grit Size (AFS No.) | D | 50 | 60 | 70 | 2 |
| 5 | Vibration Time (sec.) | E | 4 | 5 | 6 | 2 |
| 6 | Composition (%) | F | 5 | 7.5 | 10 | 2 |

III. RESULTS AND DISCUSSION

After casting, the effect of selected input parameters has been studied on the process capability of this novel process in term of dimensional accuracy. The dimension, thickness of the disc ($t=10$) was selected and dimensional deviation (Δt) of each cast component from standard dimension as per drawing (Fig. 2) was calculated by using a digital vernier caliper. As the dimension deviation represents the dimensional accuracy, therefore less (Δt) means more dimensional accuracy.

A. Analysis of S/N Ratio

The influence and variation caused by each input factor on Δt is determined with signal to noise ratio(S/N). The major benefit of using S/N ratio is that it uses a single measure, mean square deviation (MSD), which incorporates the effect of changes in mean as well as the standard deviation with equal priority [33]. The main aim of this study is to minimize ' Δt '. Therefore, S/N ratios were calculated using Eq. (1) on the basis of 'lower is better' approach for the responses.

$$S/N = -10 \log [1/r \sum Y_i^2] \quad (1)$$

Y_i = Observed value of the response characteristic; r = number of repetitions

MINITAB-17 statistical software has analyzed the experimental results [34]. The L_{18} OA frameworks with input factor and their selected levels used for the experiment; the average dimensional deviation of three repetitions and calculated S/N ratio is shown in Table 3. The higher value of S/N ratio shows the lower dimension deviation or high dimensional accuracy.

Table 3 Taguchi L_{18} Oa Provides Details Of Experiment Plan And Results

| Exp. No. | A | B | C | D | E | F | Δt (mm) | S/N Ratio |
|----------|-----|-------------------------------------|-----|----|---|-----|-----------------|-----------|
| 1 | DPS | Al ₂ O ₃ | 300 | 50 | 4 | 5 | 0.92 | 0.724243 |
| 2 | DPS | Al ₂ O ₃ | 350 | 60 | 5 | 7.5 | 0.84 | 1.480015 |
| 3 | DPS | Al ₂ O ₃ | 400 | 70 | 6 | 10 | 0.71 | 2.974833 |
| 4 | DPS | SiC | 300 | 50 | 5 | 7.5 | 0.86 | 1.27643 |
| 5 | DPS | SiC | 350 | 60 | 6 | 10 | 0.72 | 2.85335 |
| 6 | DPS | SiC | 400 | 70 | 4 | 5 | 0.68 | 3.349822 |
| 7 | DPS | Al ₂ O ₃ +SiC | 300 | 60 | 4 | 10 | 0.96 | 0.354575 |
| 8 | DPS | Al ₂ O ₃ +SiC | 350 | 70 | 5 | 5 | 0.72 | 2.85335 |
| 9 | DPS | Al ₂ O ₃ +SiC | 400 | 50 | 6 | 7.5 | 0.74 | 2.615366 |
| 10 | TPS | Al ₂ O ₃ | 300 | 70 | 6 | 7.5 | 0.70 | 3.098039 |
| 11 | TPS | Al ₂ O ₃ | 350 | 50 | 4 | 10 | 0.82 | 1.723723 |
| 12 | TPS | Al ₂ O ₃ | 400 | 60 | 5 | 5 | 0.71 | 2.974833 |
| 13 | TPS | SiC | 300 | 60 | 6 | 5 | 0.76 | 2.383728 |
| 14 | TPS | SiC | 350 | 70 | 4 | 7.5 | 0.65 | 3.741733 |
| 15 | TPS | SiC | 400 | 50 | 5 | 10 | 0.69 | 3.223018 |
| 16 | TPS | Al ₂ O ₃ +SiC | 300 | 70 | 5 | 10 | 0.79 | 2.047458 |
| 17 | TPS | Al ₂ O ₃ +SiC | 350 | 50 | 6 | 5 | 0.84 | 1.514414 |
| 18 | TPS | Al ₂ O ₃ +SiC | 400 | 60 | 4 | 7.5 | 0.72 | 2.85335 |
| Average | | | | | | | | 2.3356 |

B. Analysis of Variance (ANOVA)

Based on the observation in Table 3 analysis of variance (ANOVA) was executed on the S/N ratio of the responses to find the significance of each input factor and its percentage contribution to the desired output response, as shown in Table 4. The input factor having higher percentage contribution affects more the output response so by governing these factors the whole variation can be controlled or minimized which lead to improved process.

Table 4 Anova Results For Δt

| Source | D O F | SS | Adj.SS | Adj.MS | F-value | P-value | % Contribution |
|-----------------------------|-------|---------|--------|--------|---------|---------|----------------|
| Particle Size (A) | 1 | 1.4327 | 1.4327 | 1.4327 | 6.39 | 0.045 | 9.194 |
| Type of Reinforcement (B) | 2 | 2.0249 | 2.0249 | 1.0125 | 4.52 | 0.064 | 12.994 |
| Vacuum Pressure (C) | 2 | 5.4824 | 5.4824 | 2.7412 | 12.23 | 0.008 | 35.181 |
| Moulding Sand Grit Size (D) | 2 | 4.3798 | 4.3798 | 2.1899 | 9.77 | 0.013 | 28.106 |
| Vibration Time (E) | 2 | 0.6104 | 0.6104 | 0.3052 | 1.36 | 0.325 | 3.917 |
| Composition (F) | 2 | 0.3085 | 0.3085 | 0.1542 | 0.69 | 0.538 | 1.980 |
| Residual Error | 6 | 1.3446 | 1.3446 | 0.2241 | | | 8.628 |
| Total | 17 | 15.5833 | | | | | |

Table 5 Ranking Of Input Parameters Based Upon Sn Ratio Of Δt For Smaller Is Better.

| Level | A | B | C | D | E | F |
|-------|--------|--------|--------|--------|--------|--------|
| 1 | 2.054 | 2.163 | 1.647 | 1.846 | 2.125 | 2.300 |
| 2 | 2.618* | 2.805* | 2.361 | 2.150 | 2.309 | 2.511* |
| 3 | | 2.040 | 2.999* | 3.011* | 2.573* | 2.196 |
| Delta | 0.564 | 0.765 | 1.351 | 1.165 | 0.449 | 0.315 |
| Rank | 4 | 3 | 1 | 2 | 5 | 6 |

*Represents higher S/N

Based upon Table 4, the input factor particle size, type of reinforcement, vacuum pressure and moulding sand grit size with P-value less than 0.05 (95% confidence) are the significant model terms. The percentage contribution of all the input factors is shown in Fig.3.

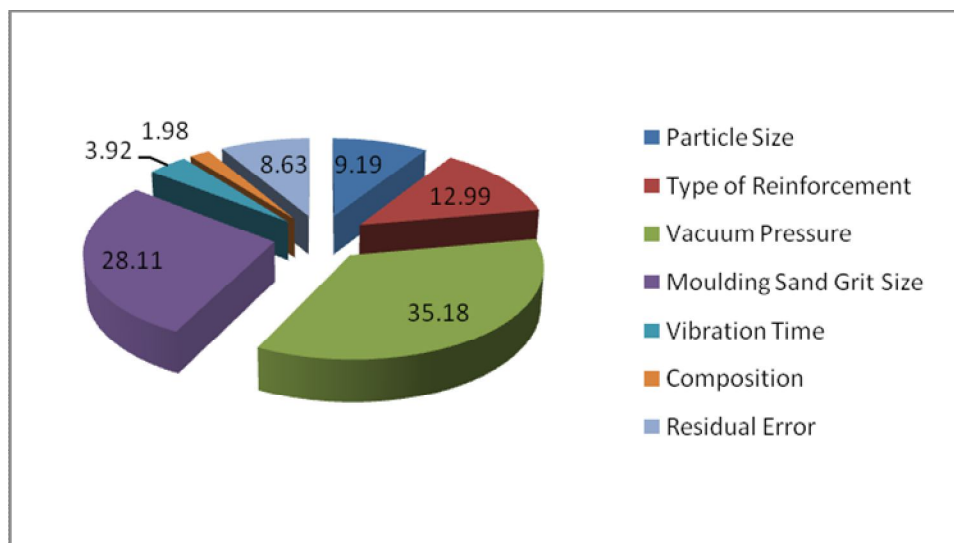


Fig. 3 Percentage Contribution Chart

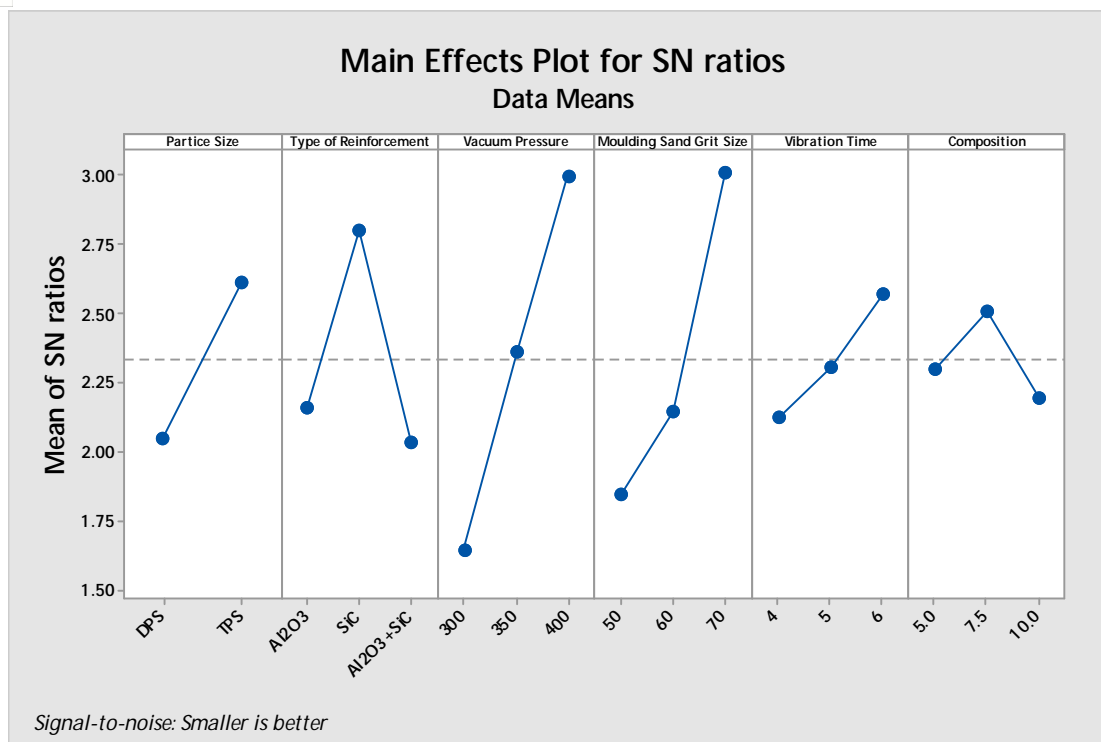


Fig. 4 Main effects plot for SN ratios

The main effect plot of various factors on Δt is shown in Fig.4, it has been found out that the reinforcement of SiC with TPS exhibit better dimensional accuracy due to excellent bonding of three different particle sizes then DPS. The TPS particles were closely packed with aluminum in the MMC results in better dimensional accuracy.

For good dimensional accuracy, vacuum pressure was best found out at 400 mm of Hg, because with increase in pressure the mould tightness increases. This tight mould, results in good dimensional accuracy in casting due to less deviation than loose mould. So, as observed in sand grain size 70 (A.F.S. No.) the dimensional accuracy was the best because of closely packed fine particles of the sand settle better under vacuum pressure and vibration. It has been also observed that the composition has no significant effect on the dimensional accuracy.

C. Optimization and Confirmation Experiments

From Table 5 the optimum levels (factor levels with highest S/N ratio) have been identified for the significant factors in order to achieve maximum dimensional accuracy as shown in Table 6.

TABLE 6 OPTIMUM LEVELS AND THEIR CORRESPONDING VALUES.

| S.No. | Input factor | Highest mean S/N ratio | Optimum level | Optimum Value |
|-------|----------------------------------|------------------------|----------------|---------------|
| 1 | Particle Size | 2.618 | A ₂ | TPS |
| 2 | Type of Reinforcement | 2.805 | B ₂ | SiC |
| 3 | Vacuum Pressure (mm of Hg) | 2.999 | C ₃ | 400 |
| 4 | Moulding Sand Grit Size(AFS No.) | 3.011 | D ₃ | 70 |
| 5 | Vibration Time (sec.) | 2.573 | E ₃ | 6 |
| 6 | Composition (%) | 2.511 | F ₂ | 7.5 |

For optimization following formula based upon Taguchi design has been used to predict optimum response in term of S/N ratio (η_{opt}) by using the mean S/N ratio of significant factors [35] [36].

$$\eta_{opt} = m + (m_{A_2} - m) + (m_{B_2} - m) + (m_{C_3} - m) + (m_{D_3} - m) \quad (2)$$

$$\eta_{opt} = 2.618 + 2.805 + 2.999 + 3.011 - 3(2.3356)$$

$$\eta_{opt} = 4.4262 \text{ dB}$$

Where 'm' is the overall mean of S/N data, m_{A2} is the mean of S/N data for A at level 1 and similarly m_{B2} , m_{C3} and m_{D3} .

By using Eq.1 predicted dimensional deviation is 0.64mm. The confirmatory experiments were performed by using the obtained set of optimum factor values. The confirmation test values of the dimensional deviation lie between 0.62 and 0.65mm, close to the predicted value.

D. Process capability

The capability of a process represents a measure for standardization of a process. The process capability is analyzed and assessed through the usage of capability indicators such as: potential index or preciseness of a process C_p (measure for process dissipation) and capability preciseness index C_{pk} (measure for process adjustment) [37]. C_p and C_{pk} is evaluated by QI Macros-2015 software on the samples cast at optimum parameter settings as shown in Fig. 5. In this work, corresponding to a C_{pk} value of 1.38 for the selected dimension, area under the normal curve is 0.999936360 and non-confirming parts per million is 63.6403. As, the C_{pk} value greater than 1.3 indicated that the proposed process is statistically controlled and can be employed for batch/mass production.

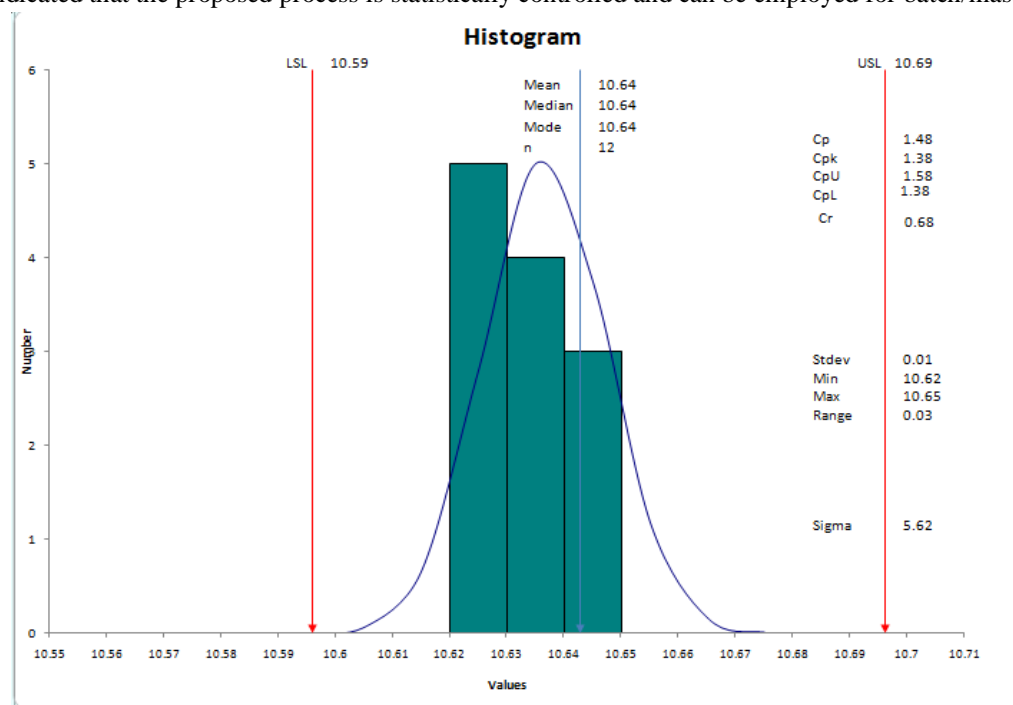


Fig. 5 Process Capability

IV. CONCLUSION

From this research work, the following conclusions have been made:

- Al-MMC with hybrid reinforcement (5%, 7.5% and 10%) of DPS and TPS Al_2O_3 and SiC has been developed successfully by using vacuum moulding (V-process) assisted stir casting technique.
- ANOVA revealed that the percentage contribution of significant process parameters particle size 9.19%, type of reinforcement 12.99%, vacuum pressure 35.18% and moulding sand grit size 28.10% on the dimensional accuracy of hybrid Al-MMC.
- The optimal dimensional accuracy is found with triple particle size (A_2), SiC (B_2), vacuum pressure 400 mm of Hg (C_3), 70 A.F.S. No. (D_3), vibration time of 6 seconds (E_6) and composition of 7.5 % by weight (F_2).
- Process capability indices (C_{pk}) more than 1.3 highlighted that the developed hybrid process is highly capable and statistically controlled for batch and mass production.

V. ACKNOWLEDGMENT

The authors are thankful to I. K.G. Punjab Technical University, Kapurthla (Pb.), India and Guru Nanak Dev Engineering College, Ludhiana (Pb.), India for providing this opportunity and support.

REFERENCES

- [1] Uvaraja V. C., Natarajan N., Comparison on Al6061 and Al7075 with SiC and B4C reinforcement hybrid metal matrix composites, IJART,2012, Vol.2, pp.1-12.
- [2] Das S, Development of Aluminium Alloy Composites for Engineering Applications, Trans. Indian Inst. Met., Vol.57, No. 4, August 2004, pp. 325-334.
- [3] Matsunaga T, Kim J K, Hard Castle S and Rohatgi P. K., Casting characteristics of aluminium alloy, fly ash composites, Transactions of AFS, 1996, vol.104: pp.1097-1102.
- [4] Hayrettin Ai, Tolga K, Ercan C. and Huseyin Ç., Wear behavior of Al/(Al₂O₃p + SiCp) hybrid composites, Tribology Int, 2006; 39; pp. 213-20.
- [5] Zhang X.X., Mechanical properties of ABOw & MWNTs/Al hybrid composites made by squeeze cast technique, Mater Letter, 2007; 61; pp 3504-6.
- [6] Gurcan A.B. and Baker T.N., Wear behavior of AA 6061 Aluminium alloy and its composite, Wear 1995;188:185-91.
- [7] Wang, Y.Q., Afsar, A.M., Jang, J.H., Han, K.S., Song, J. I., Room Temperature Dry and Lubricant Wear Behaviors of Al₂O₃/SiCp/Al Hybrid Metal Matrix Composites, Wear, 2010; vol.268, pp. 863-870.
- [8] Park H C., Wear behavior of hybrid metal matrix composite materials. Scripta Metall Mater, 1992; vol.27: pp 465-70.
- [9] Suresha, S., Sridhara, B.K., Effect of Addition of Graphite Particulates on the Wear Behavior In Aluminum-Silicon Carbide-Graphite Composites, Materials in Design, 31, pp.1804-1812.
- [10] Surappa M. K., Aluminium Matrix Composites: Challenges and Opportunities, Sadhana, 2003, vol.28 (1, 2), pp. 319.
- [11] Hashim L, Looney L, Hashmi M S J, Metal matrix composites: production by the stir casting method, Journal of Materials Processing Technology;1999,vol. 92-93,pp.1-7.
- [12] Amirkhanlou S., Niroumand B., Synthesis and characterization of 356-SiCp composites by stir casting and compocasting methods, Trans. Nonferrous Met. Soc. China , 2010, vol.20, pp788-793.
- [13] Sakip Koksai, Ferit Ficici, Ramazan Kayikci, Omer Savas, Experimental optimization of dry sliding wear behavior of in situ AlB2/Al composite based on Taguchi's method, Materials and Design,2012, vol. 42, pp 124-130.
- [14] Karamis, M.B. Alper Cerit, A.,Burhan Selc-uk, Nair, F. , The effects of different ceramics size and volume fraction on wear behavior of Al matrix composites (for automobile cam material), Wear, 2012, vol.289, pp.73-81.
- [15] Shafiei-Zarghani A, Kashani-Bozorg S.F., Zarei-Hanzaki A, Microstructures and mechanical properties of Al/Al₂O₃ surface nano-composite layer produced by friction stir processing, Materials Science and Engineering A 500, 2009, pp 84-91.
- [16] Annigeri Ulhas.K., G.B.Veeresh Kumar, Method of stir casting of Aluminum metal matrix Composite: A Review, Material Today: Proceedings, Part A; 2017; pp1140-1146.
- [17] Surappa, M.K., Microstructure Evolution during Solidification of DRMMCs: State of the Art, Journal of Materials Processing Technology, 1997, vol., 63: 325-333.
- [18] Jasmi Hashim, The production of cast metal matrix composite by a modified stir casting method., Jurnal Teknologi, 2001, 35(A) Dis.; pp. 9-20.
- [19] Bishop D., Bose S., Mechanical properties of V-process molded steel castings, Trans. Am. Foundry men's Soc. J., 1983, vol. 91, pp.441-446.
- [20] Regnet D, V-Process Reduces Lead Time, Controls Tolerances Via Zero Draft (20000408), Engineered Casting Solutions,2000, vol. 2, pp.46-49.
- [21] Barua P.B., Kumar P., Gaiandhar J.L., Quality of V-process moulds through Taguchi's technique, Int. J. Qual. Reliab. Eng 12,1996, pp. 421-427.
- [22] Grefhorst C., Muller M., Comparison between a Conventional and Vacuum Moulding Sand Preparation, Cast. Plant Technol. Int. J., 2000, vol.16 (1), pp. 4-8.
- [23] Jain C. K. and Gaiandhar, J. L., Simulating behavior of sand under vacuum in V-process", Transaction of American Foundry men's Society Journal,1986, vol. 94, pp. 86-107.
- [24] Y. Kubo, Molding Unbonded Sand With Vacuum--The V-Process, (19740295) AFS Transactions, 1973, pp.529-544.
- [25] Jain C. K. and Gaiandhar J. L., DAS, Solidification Time and Mechanical Properties of Al-11%Si Alloy V-Processed Castings (19980388) Transactions of the American Foundry men's Society, 1997, vol.104 Paper 97-09 ,pp. 635-638.
- [26] Singh, R., Singh J. and Singh Jagdev, Macro-Model for Development of Al- Al₂O₃ Metal Matrix Composite with Vacuum Moulding: Designed Experiments, J. Inst. Eng. India Ser. C, 2012, vol. 93(4), pp.325-330.
- [27] Singh R., Process Capability Analysis of Vacuum Moulding for Development of Al- Al₂O₃ MMC, J. Inst. Eng. India Ser. C., 2013, DOI 10.1007/s40032-012-0051-z.
- [28] Singh J. and Singh R., Macro-Model for Development of Al- SiC Metal Matrix Composite with Vacuum Moulding: Designed Experiments, Mat. Sc. Forum, 2013, vol.751, pp.21-26.
- [29] Boparai, K.S. & Singh R., Experimental Investigations for Statistically Controlled Vacuum Moulding Solutions of Al-Sic MMC", Applied Mechanics and Materials, 2013, vol.330, pp.91-95.
- [30] Clegg A J, The V-process Review and Current Status. Foundry Trade J.; 1985; vol.158; pp 472-86.
- [31] Gaiandhar J L, Jain C K, Subbarathnanmaiah K, Effect of Sand variables on dimensional accuracy of Al-4% Cu alloy castings produced by V-process., Trans. Am. Foundry men's Soc. J., 1985, vol. 93, pp. 303-306.
- [32] Gouwens P R, Vacuum molding (The V-Process) perspective and into the future, Trans. Am. Foundry men's Soc. J., 2005, pp. 98-174.
- [33] Kumar P., Singh R, Ahuja IPS, Investigations on dimensional accuracy of the components prepared by hybrid investment casting. J Manufacturing Processes; 2015,<http://dx.doi.org/10.1016/j.jmapro.2015.07.008>.
- [34] Kumar P, Singh R, Ahuja IPS., Experimental investigations on hardness of the biomedical implants prepared by hybrid investment casting., J Manufacturing Processes; 2016; vol.21; pp.160-71.
- [35] .Sood A K, Ohdar R K, Mahapatra S S., Improving dimensional accuracy of fused deposition modeling processed part using grey Taguchi method, Mater Des; 2009; vol.30: pp.4243-52.
- [36] Krishnaiah K, Shahabudeen P., Applied Design of Experiments and Taguchi methods., 4th ed. New Delhi: PHI Learning Pvt. Ltd; 2012. p.248.
- [37] Singh R, Singh G., Cast component hardness comparison for investment casting prepared with wax and ABS patterns., Trans Indian Inst Met 2015; vol.68; pp17-21.



10.22214/IJRASET



45.98



IMPACT FACTOR:
7.129



IMPACT FACTOR:
7.429



INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089  (24*7 Support on Whatsapp)