iJRASET
International Journal For Research in Applied Science and Engineering Technology



INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Volume: 6 **Issue:** VII **Month of publication:** July 2018

DOI: http://doi.org/10.22214/ijraset.2018.7099

www.ijraset.com

Call: 08813907089 | E-mail ID: ijraset@gmail.com

International Journal for Research in Applied Science & Engineering Technology (IJRASET)
ISSN: 2321-9653; IC Value: 45.98; SJ Impact Factor: 6.887
Volume 6 Issue VII, July 2018- Available at www.ijraset.com

Assessment of Factors Influencing the Microstructure and Porosity of PM 316L Austenitic Stainless Steel

Mahaboob Patel[1], R Muthu Vaidyanathan[2], Tsegaye Alemayehu[3], Mebratu Markos[4], Sikandar Shakil[5], Mohammad Sujayath Ali[6]
[1, 2, 3, 4]*Dept of Mechanical Engineering,* [5]*Dept of Civil Engineering,* [6] *Dept of COTM, Wolaita Sodo University, Ethiopia*

Abstract: ***Austenitic stainless steels are widely used in medical, industrial as well as in domestic applications because of its outstanding mechanical properties and corrosion resistance. Attempts are being made to use stainless steel powder in order to achieve dimensional accuracy for near net-shape part fabrication, increased productivity, to overcome loss of material and minimize energy consumption. Use of stainless steel in powder form poses certain disadvantages mainly because of the poor densification and increased porosity of the sintered compacts which limit the use of PM stainless steel for certain applications. This paper presents a brief assessment of the various factors influencing the microstructure and porosity of PM 316L austenitic stainless steel.***

Keywords: Powder metallurgy, Stainless steel, Microstructure, Porosity

I. INTRODUCTION

Stainless steels are highly resistant to corrosion (rusting) in a variety of environments, especially the ambient atmosphere. Their predominant alloying element is chromium (min 11 wt%). Corrosion resistance may also be enhanced by nickel and molybdenum addition. A wide range of mechanical properties combined with excellent corrosion resistance make stainless steels very versatile in their applicability. [1]

Powder metallurgy (PM) is a metal manufacturing process that makes semi-finished or finished components from plain or alloyed powders. This process involves the following steps: production of powder metal, metalloids, metal alloys or compounds, blending and mixing of powders, compaction, sintering, and, in some cases, repeating the operation [2, 3, 4]. PM, therefore, is the production and exploitation of metal powders. Particles whose size is less than 100 nm (1 mm) are referred to as powder [5]. Metal powder attributes depend on the following parameters: particle shape and size, particle size distribution, compressibility, apparent density, and flow rate. Notwithstanding the exceptional qualities of PM processes, porosity, production of parts with complex shape and features, and high strength are challenges [6]. There are pores in almost all of the PM parts and this has both advantages and disadvantages. One of the advantages is being able to produce self-lubricating bearings. The pores that are linked to the surface are impregnated with oil [5, 7].

Metal matrix composites (MMCs) are currently being developed as possible structural materials, offering improved elastic modulus, strength, good properties at elevated temperature and control over the coefficient of thermal expansion [8, 9]. The addition of high modulus refractory particles to a ductile metal matrix produces a material with properties intermediate between the matrix alloy and ceramic reinforcement. However, the optimum properties of metal matrix composites depends additionally on a proper selection of the metallic matrix material, the reinforcing phase, the methods of producing and the parameters of these methods [10, 11].


The 316L austenitic stainless steel is nowadays a widely used engineering material due to its excellent corrosion and oxidation resistance and good formability [12]. Powder metallurgy (PM) is a suitable technology to fabricate complex parts with net shaping capabilities, appreciable dimensional precision and high productivity [13]. PM of stainless steel components constitutes an important and growing segment of the PM industry [14]. PM stainless steel is generally used in special applications, where enhanced properties are required as compared to the low alloy steel [15]. However the wider application of PM stainless steel is limited due to their poor mechanical and corrosion properties. Therefore, there is a need to improve the corrosion resistance and mechanical properties of PM stainless steel by modifying the microstructural characteristics through the addition of second phase dispersiods or by utilizing novel sintering techniques [16] such as microwaves.

©IJRASET: All Rights are Reserved

The aim of the present investigation was to study the various ways by which the microstructure and porosity of PM 316L austenitic stainless steels (ASS) composites can be modified as compared to plain samples.

II. FACTORS INFLUENCING MICROSTRUCTURE AND POROSITY:

A. Powder Morphology

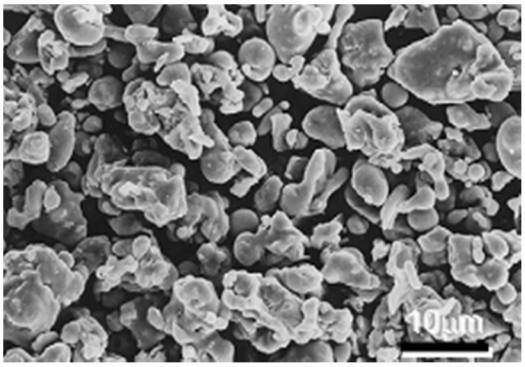(a) 

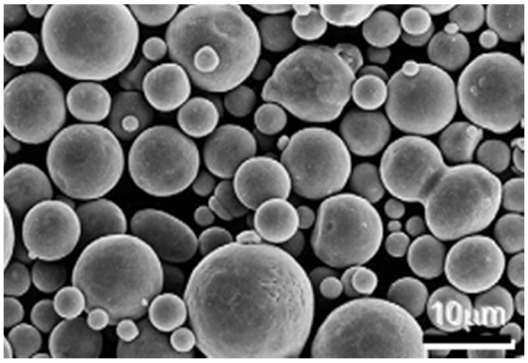
(b) 

Fig.1: SEM images of (a) water-atomized and (b) gas atomized 316L ASS powders [17].

Generally two methods are employed to produce metal powder i.e water and gas atomization. Morphology of the powders, observed using scanning electron microscopy is given in fig.1 (a) & (b). The water atomized powders are irregular in shape due to rapid cooling and the gas atomized powders are spherical, as it gets enough time to attain spherical shape due to the action of surface tension during auto cooling.

R.P. Koseski et.al [17] have tabulated various characteristics of water and gas atomized powders, some of which are enlisted below in order to understand possible reasons causing difference in microstructural features and porosity of sintered compacts made of these powders.

Table 1: Particle characteristic of stainless steel powders

Characteristics	Water atomized	Gas atomized
Shape	Irregular	Spherical
Pycnometric density (g/c^3)	7.93	7.96
Angle of repose (^{o})	50	45

The microstructural evolution of the gas-atomized powders is given in Fig.2 (a) and that of water-atomized powder is given in Fig.2 (b). The morphology of powders greatly influences the densification of plain sintered products. Experimental works have proved that compacts made of water atomized powder could be sintered to 97% of theoretical density Fig.2 (a) while compacts made of gas atomized powders could be sintered to near full density Fig.2 (b) [17].

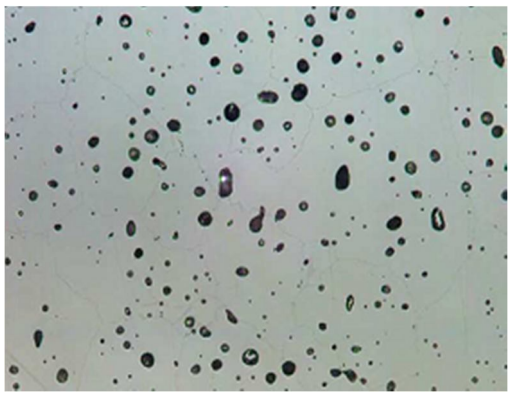
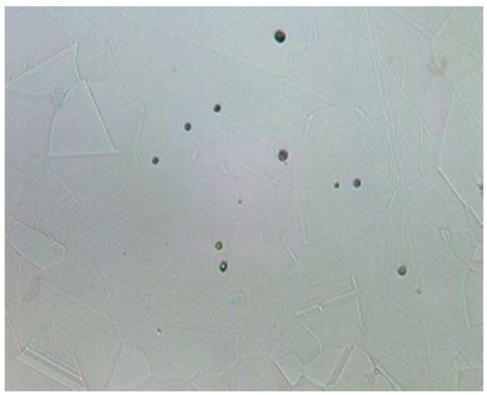
(a) 
(b) 

Fig.2: SEM images of sintered compacts (a) water-atomized, (b) gas atomized [17].

©IJRASET: All Rights are Reserved

ISSN: 2321-9653; IC Value: 45.98; SJ Impact Factor: 6.887
Volume 6 Issue VII, July 2018- Available at www.ijraset.com

Here flowability of the powder plays an important role in compaction. In table.1, the angle of repose for water and gas atomized particles is 50^{o} and 45^{o} respectively. It is obvious that smaller the angle of repose greater is the flowability of material. The change in angle of repose is mainly because of the morphology of powder particles, i.e gas atomized particles are spherical exhibits greater flowability as compared to water atomized particles having irregular shape. Therefore the compacts made of gas atomized stainless steel powders exhibit lesser porosity as compared to compacts made of water atomized stainless steel powders as seen in fig.2.

B. Powder Size

Joo Won Oh et al. [20] have analyzed compaction and sintering behavior of 316L stainless steel nano/micro bimodal powder. They used stainless steel powders of two different particle sizes i.e micro (4 μm) and nano (100 nm) as shown in below SEM images.

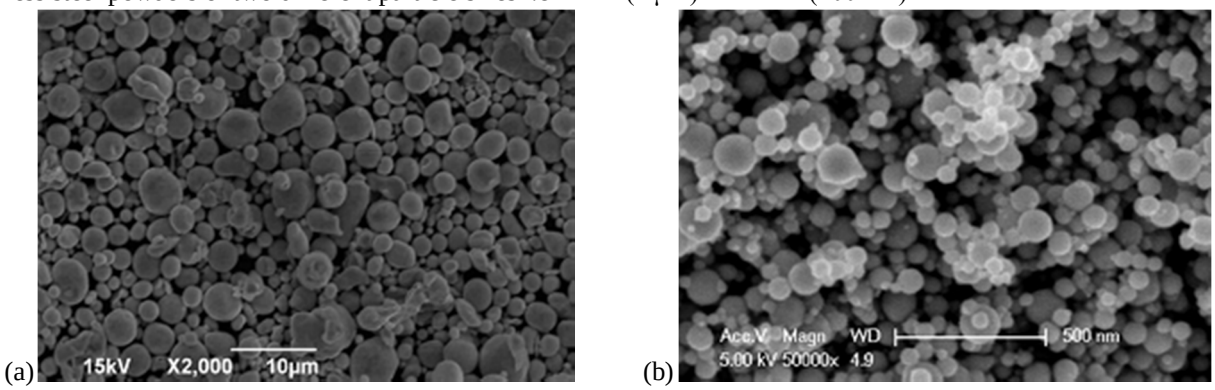


Fig.3: SEM images of 316L ASS powders: (a) micro and (b) nano [20].

The sintered compacts made from micro and nano powders reveals the difference in porosity in terms of pore size and number as shown in the optical images magnified 1000 times after polishing (fig.4). This can be attributed to number of particles in a given volume and sintering behavior the powders. Larger the particle size less is the number of particle in a unit volume and lesser is the number of pores but larger pore size in sintered compacts, whereas it is opposite in case of sintered samples nano powder.

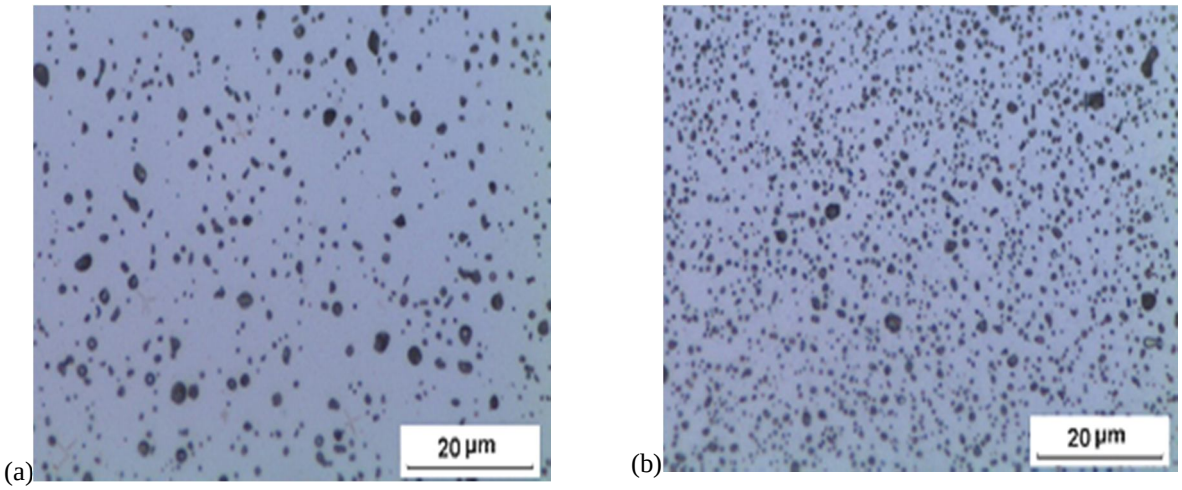


Fig.4: Optical images of sintered samples: (a) micro and (b) nano [20].

Densification of 316L ASS during sintering proceeds via lattice or volume diffusion between the adjacent particles, but this diffusion is not enough to fill the gaps between the particles, hence creates pores. Nano powders exhibit agglomeration due to their strong van der Walls force. Densification of agglomerated nano powder takes place via two mechanisms, shrinkage of intra-agglomerate pores and inter-agglomerate pores [20]. The porosity in this case is because of these two shrinkage mechanisms.

©IJRASET: All Rights are Reserved

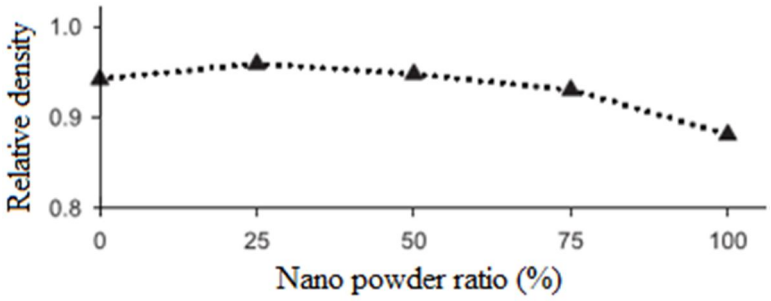


Fig.5. Average value of relative density

Shrinkage of porosity can be understood from density of the sintered samples. Joo Won Oh et al. [20] have plotted the relative densities of micro, nano and bimodal sintered samples as presented in the fig.5. The result indicated that 25:75 nano/micro bimodal powders had the highest sinter density. This is because the nano particles filled the interparticle space between the micro particles during compaction, hence indicates reduced porosity, whereas the nano samples achieved poor density, indicating highest porosity.

C. Reinforcement Powder

Microstructure and porosity of PM 316L ASS can greatly be altered by reinforcing ceramic particles like oxides, carbides, borides etc. Chemical composition of PM 316L ASS (table 2) and melting points (MP) of reinforcement particles (table 3) help us to understand microstructural evolution of these composites.


Table 2: Chemical composition of AISI 316L ASS powder


Element	C (max)	Si	Mn (max)	P (max)	S (max)	Cr	Ni	Mo	Cu (max)
Wt%	0.03	2-3	0.2	0.03	0.03	16-18	10-14	2-3	0.5

Table 3: Melting points of 316L ASS and reinforcement powders

Powder	Melting Point
316L ASS	1375-1400°C
Nb_2O_5	1512°C
Al_2O_3	2072 °C
TiB_2	2970 °C
TiC	3160 °C

Following SEM images (fig.6) reveal the pore profile of the sintered compacts reinforced with ceramic powders having different melting points, sintered at 1250°C. The microstructure of the sintered 316L ASS composites shows increased porosity for the powders with higher melting points as shown in the following SEM images.

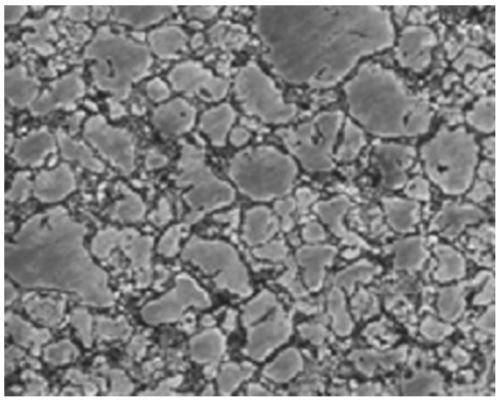(a) 

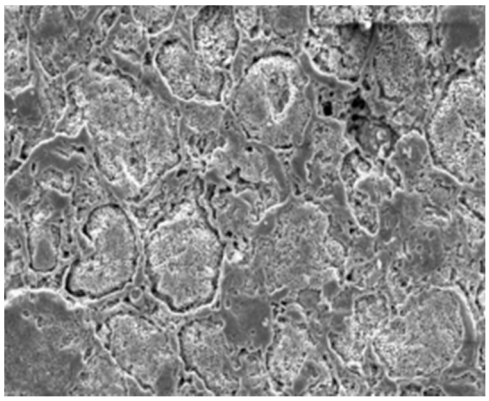(b) 

©IJRASET: All Rights are Reserved

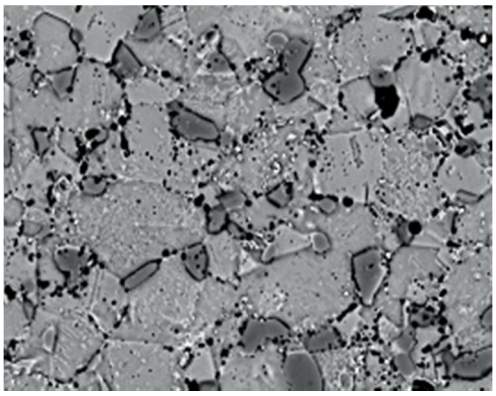
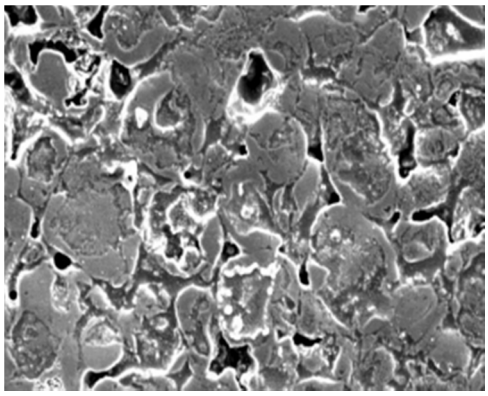
(c)  (d) 

Fig.6: SEM images of sintered PM 316L ASS composite reinforced with (a) Nb_2O_5 [18], (b) Al_2O_3 [17], (c) TiB_2 [12] and (d) TiC [17]

Among the powders used TiC has highest melting point of around 3160°C and is obvious that, it would not form a liquid phase at sintering temperature which is required to fill the interparticle spaces to reduce the porosity, instead it obstructs the joining of adjacent metal particles resulting in increased porosity of the composite (fig.6.d). Whereas Nb_2O_5 reinforced ASS shows a reduced porosity, which can be attributed to formation of semi-liquid phase at sintering temperature and thereby diffusing in the intergrannular spaces left during the sintering. Composites with Al_2O_3 and TiB_2 showed intermediate percentage of porosity and densification.

Austenitic stainless steels undergo densification via lattice (volume) diffusion during the intermediate stage of sintering [17, 21, 22]. During this regime, surface diffusion is also active. Thus, pore migration occurs by a combination of surface and lattice diffusion. At higher temperatures, lattice and grain boundary diffusion contribute to densification. These mass diffusions and densification process on the other hand depends the rate of heating during sintering. Slower heating rate favors densification.

III. CONCLUSION

With this study following conclusions are made;

A. The sintered compacts made up of spherical powder achieve reduced porosity and could be sintered to near full density.
B. The result indicated that 25:75 nano/micro bimodal powders had the highest sinter density as compared to micro and nono samples.
C. The sintered PM 316L ASS composites reinforced with ceramic particles having lower MP exhibit reduced porosity as compared to composites with high MP ceramic particles.
D. Desired porosity and densification could be achieved by controlling these factors.


REFERENCE

[1] Materials Science and Engineering an Introduction, William D. Callister, Jr, David G. Rethwisch, Eighth Edition, pp-397
[2] N. S. J. Siti, M. Faizal, M. N. Dewan, and N. B. Shah, "A Review on the Fabrication Techniques of Functionally Graded Ceramic-Metallic Materials in Advanced Composites," Scientific Research and Essays, Vol. 8, pp 828-840, 2013.
[3] S. Kateřina, K. Miroslav, and S. Ivo, Powder Metallurgy. Ostrava: University Textbook, Technical University of Ostrava, 2014.
[4] N. R. Ganesh. (n. d., 04/07/2016). Powder Metallurgy: Basics and Applications. Available: http://www.iitg.ernet.in/engfac/ganu/public_html/Powdermetallurgy.pdf
[5] B. J. W., "Powder Metallurgy Methods and Applications," in ASM Handbook, Powder Metallurgy. vol. 7, P. Samal and J. Newkirk, Eds., ed: ASM International, 2015.
[6] R. K. Rajput, Manufacturing Technology: Manufacturing Processes. New Delhi, India: Laxmi Publications, 2008.
[7] Ebhota Williams S, Akhil S. Karun a, Inambao, Freddie L, Principles and Baseline Knowledge of Functionally Graded Aluminium Matrix Materials (FGAMMs): Fabrication Techniques and Applications, International Journal of Engineering Research in Africa Submitted, ISSN: 1663-4144, Vol. 26, pp 47-67
[8] He P., Yue X., Zhang J.: Hot pressing diffsion bonding of a titanium alloy to a stainless steel with an aluminum alloy interlayer. Materials Science and Engeenering A, 486 (2008), 171–176
[9] Emadoddin E., Tajally M., Masoumi M.: Damping behavior of Al/SiCP multilayer composite manufactured by roll bonding. Materials & Design, 42 (2012), 334–338
[10] Mazahery A., Shabani M.O.: Tribological behaviour of semisolid-semisolid compocast Al–Si matrix composites reinforced with TiB2 coated B4C particulate. Ceramics International, 38 (2012), 1887–1889

©IJRASET: All Rights are Reserved

[11] Nagarajan S., Dutta B.: The effct of SiC particles on the size and morphology of eutectic silicon in cast A356/SiC composites. Composites Science and Technology, 59 (1999), 897–902
[12] Iwona Sulima, Paweł Hyjek, Tomasz Tokarski, Inflence of annealing conditions on the properties and microstructure of steel composites, Metallurgy and Foundry Engineering – Vol. 40, 2014, pp. 33–43
[13] Ingeborg Kuhn, "Ferrous PM Materials in Automotive Applications: Present and Future Potentialities", Proceedings of the powder metallurgy world congress, 3 (1998), 305-310.
[14] C. Garcia, F. Martín, P. de Tiedra, Y. Blanco, J.M. Ruz-Roman, M. Aparicio, Electrochemical reactivation methods applied to PM autenitic stainless steels sintered in nitrogen–hydrogen atmosphere, Science Direct Corr.Sci 50 (2008) 687–697.
[15] J.H. Reinshagen and A.J. Neupaver, "Fundamentals of P/M Stainless Steel", Powder Metallurgy Conference and Exhibition, San Diego, California (1989) 1-13. 527
[16] S.K. Mukherjee, G.S. Upadhyaya, Sintering of 434L ferritic stainless steel containing Al2O3 particles, Int. J. Powder Metall. Powder Tech. 19 (1983) 289.
[17] Ryan P. Koseski, Pavan Suri, Nicholas B. Earhardt, Randall M. German, Microstructural Evolution of Injection Molded Gas and Water Atomized 316L Stainless Steel Powder During Sintering, Elsevier, Materials Science and Engineering A 390 (2005) 171-177
[18] Mahaboob Patel, R Muthu Vaidyanathan, N Sivaraman, Corrosion Behaviour of Sintered 316L Austenitic Stainless Steel Composites, International Journal of Mechanical Engineering and Technology, Volume 5, Issue 10, October (2014), pp. 121-128
[19] Anand Hegde, Adarsh Patil, Vijay Tambrallimath, Corrosion Behaviour of Sintered Austenitic Stainless Steel Composites, International Journal of Engineering Research & Technology, ISSN: 2278-0181, Vol. 3 Issue 12, December-2014
[20] Joo Won Oh, Seung Kyu Ryu, Won Sik Lee, Seong Jin Park, Analysis of compaction and sintering behavior of 316L stainless steel nano/micro bimodal powder, Elsevier, Powder Technology, 322 (2017)
[21] T. Pieczonka, J. Kazior, A. Tizani, A. Molinari, J. Mater. Process Technology, 64 (1997) 327–334.
[22] R.M. German, Metall. Trans. A 7A (1976) 1879–1885.
[23] Lauren Juliet Ayers, The Hardening of type 316L Stainless Steel Welds with Thermal Aging, Bachelor Thesis, Massachusetts Institute of Technology, June 2012, pp.
[24] Li-Hui Cheng, Kuen-Shyang Hwang, Strengthening of Sintered Austenitic Stainless Steels through Low-Temperature Carburization, Materials Transactions, Vol. 53, No. 1 (2012) pp. 179 to 184

©IJRASET: All Rights are Reserved

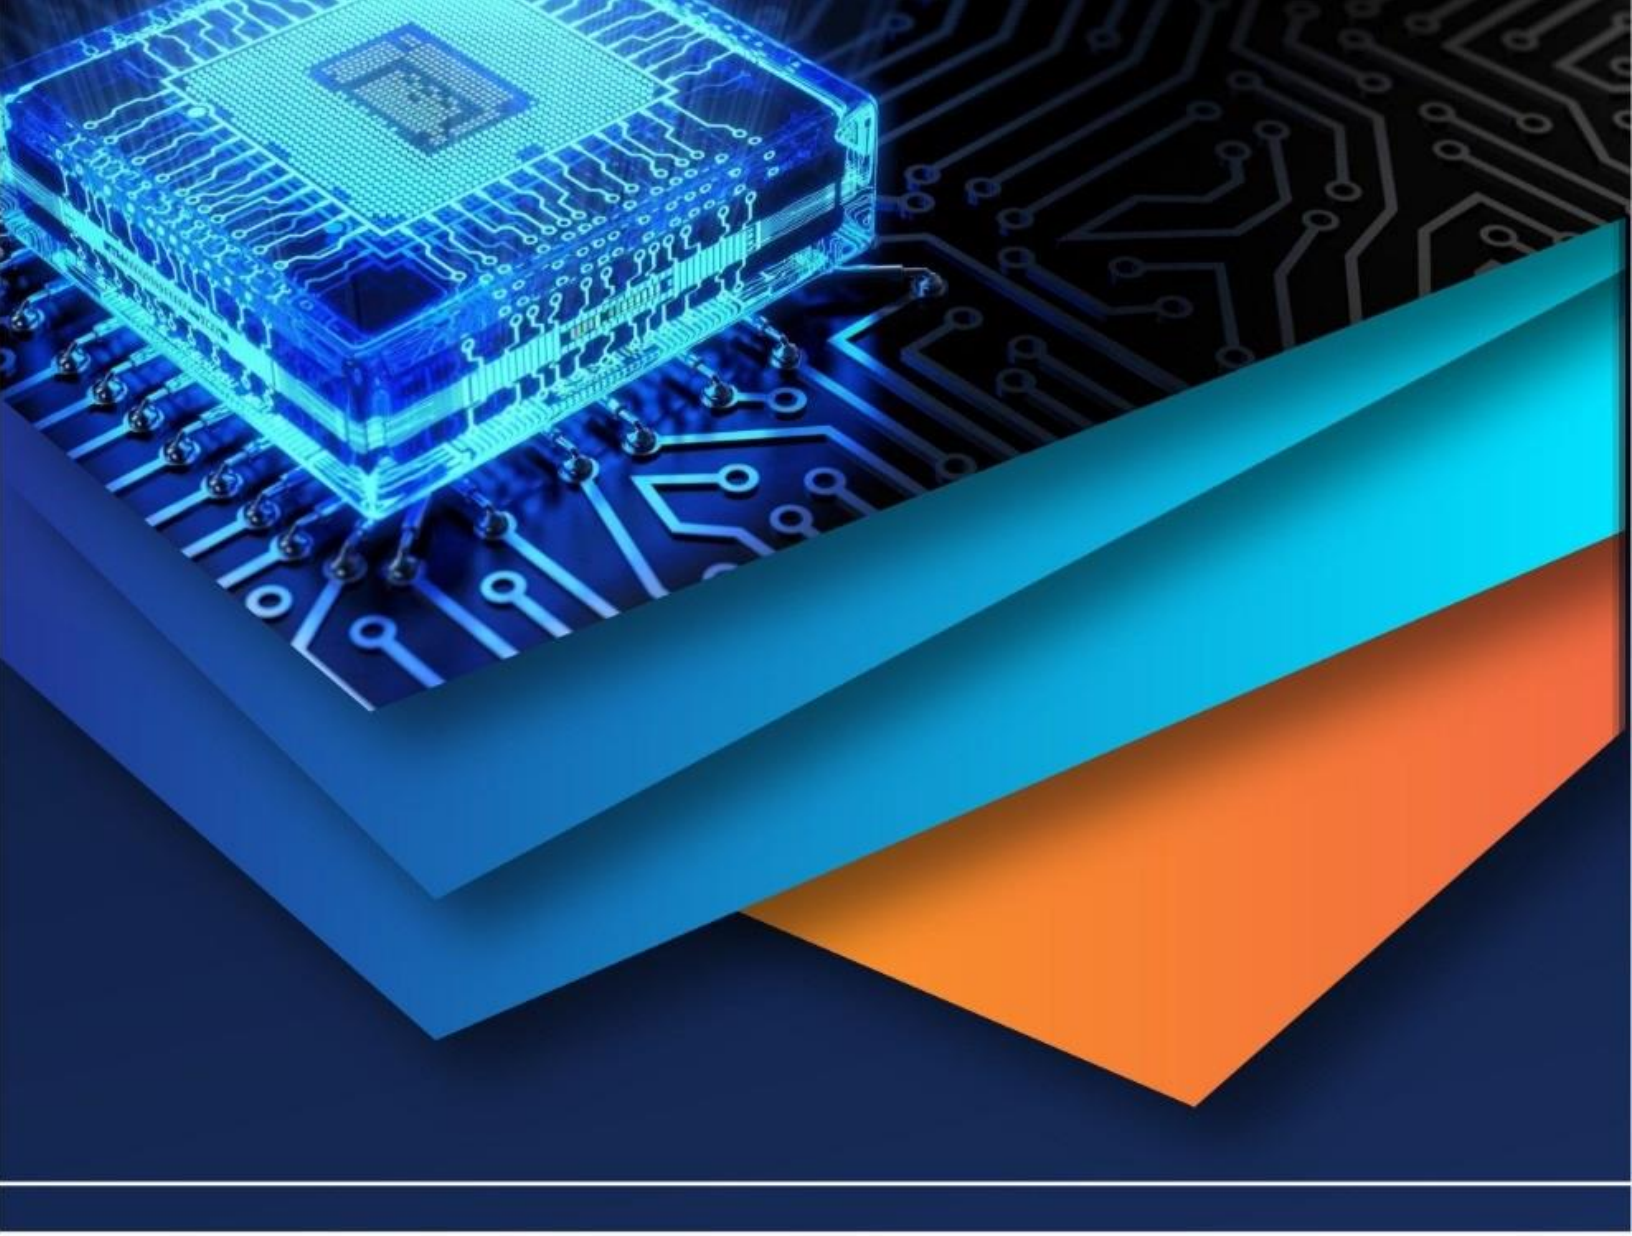

10.22214/IJRASET

45.98

IMPACT FACTOR: 7.129

IMPACT FACTOR: 7.429

INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089 (24*7 Support on Whatsapp)