



# **iJRASET**

International Journal For Research in  
Applied Science and Engineering Technology



---

# **INTERNATIONAL JOURNAL FOR RESEARCH**

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

---

**Volume: 7      Issue: IX      Month of publication: September 2019**

**DOI: <http://doi.org/10.22214/ijraset.2019.9100>**

**[www.ijraset.com](http://www.ijraset.com)**

**Call:  08813907089**

**E-mail ID: [ijraset@gmail.com](mailto:ijraset@gmail.com)**

# A Study on Durability Properties of High Strength Concrete by Effect with Mineral Admixtures in Aggressive Environment

Miss. Nagulapalli Mounika<sup>1</sup>, Miss. M. Divya Tejaswi<sup>2</sup>

<sup>1</sup>PG Scholar, Department of Civil Engineering, Aditya College of Engineering & Technology, Surampalem, Andhra Pradesh, India.

<sup>2</sup>Assistant Professor, M.tech, Department of Civil engineering, Aditya College of Engineering & Technology, Surampalem, Andhra Pradesh, India

**Abstract:** Portland cement is the most important ingredient of concrete and is a versatile and relatively high cost material. Large scale production of cement is causing environmental problems on one hand and depletion of natural resources on other hand. The main parameter investigated in this study of M100 grade concrete with partial replacement of cement by silica fume by 0, 5, 10, 15, 20, 25 and by 30% and study of M100 grade concrete with partial replacement of cement by fly ash by 0, 5, 10, 15, 20, 25, 30, 35 and by 40%. Conplast sp430 is used as super plasticizer in this project. High strength concrete can be made by using low w/c. Acidic attack is one of the world's wide problems that may cause gradual but severe damages to concrete structures. This paper presents a detailed experimental study on Compressive strength at age of 7, 28, 56, 90 and 180 days. Durability study on acid attack was also studied and percentage of weight loss is compared with normal concrete. Test results indicate that use of Silica fume in concrete has improved the performance of concrete in strength as well as in durability aspect. From these investigations we watch that 20% Micro silica and 30% Fly ash will give ideal quality for M100 review at water/cement proportion of 0.25. The impact Na<sub>2</sub>SO<sub>4</sub> on these blends is nil or very less where as HCL and H<sub>2</sub>SO<sub>4</sub> had considerable effect.

## I. INTRODUCTION

It is estimated that cement clinker manufacturing consumes an energy of approximately 850 kcal per kg of clinker and has a significant environmental impact. For each tone of cement clinker manufacturing, it emits 850 kg of carbon dioxide. It was therefore evaluated that the waste materials from different sectors were partly substituted in concrete for cement in order to decrease their efficiency. When waste products such as fly ash, silica fume, steel slag, metakaolin etc. are used as concrete substitute for cement, this results in tremendous energy savings and has significant environmental advantages.

It also achieves cost advantages through the use of these waste, as cement occupies more than 45 percent of concrete cost. Fly ash, produced as waste from thermal power plants, is one of the commonly used admixtures in concrete. Many of the past study work on fly ash has shown that fly ash concrete has the advantage of decreased hydration heat. Excellent durability results from concrete with 50 percent fly ash. Unlike fly ash, silica fume has a quality of rapid pozzolanic reaction rate, resulting in early concrete resistance growth. The reason for the decreased concrete bleeding is the presence of silica fumes.

The pozzolonic activity in silica fume powder has ultra-fine admixture size will also have a beneficial impact on concrete. Because of this research in this document, the ultra-fine size of silica fume and fly ash is used in concrete for partial substitute of cement and research has been carried out on the strength and durability features of such concrete. When powdered silica fume is used as a pozzolonic admixture in concrete, a reduction in strength was noted in early centuries. Therefore, to counteract this, a very tiny proportion of cement as a partial substitute. Therefore, to counteract this, a very tiny proportion of silica fume is also used as a partial substitute of cement and then the features of strength and durability are studied.

## II. PROPERTIES OF MATERIALS

### A. Cement

Ordinary Portland cement of 53 grade having specific gravity was 3.02 and fineness was 3200cm<sup>2</sup>/gm was used in the investigation. The Cement used has been tested for various proportions as per IS 4031-1988 and found to be confirming to various specifications of are 12269-1987.

**B. Coarse Aggregate**

Crushed angular granite metal of 10 mm size having the specific gravity of 2.65 and fineness modulus 6.05 was used in the investigation.

**C. Fine Aggregate**

River sand having the specific gravity of 2.55 and fineness modulus 2.77 was used in the investigation.

**D. Fly Ash**

Type-II fly ash confirming to I.S. 3812 – 1981 of Indian Standard Specification was used as Pozzolana Admixture.

**E. Micro Silica**

The Micro silica having the specific gravity 2.2 was used in the present investigation


**F. Conplast SP430**

Specific gravity - 1.20, the rate of addition is generally in the range of 0.6 – 1.5 liters/100 kg cement


**III. RESULT and DISCUSSION**

**A. Compressive Strength Test**

The compressive strength of the concrete samples was determined in 7 days and 28 days. The sample size 150 x 150 x 150 mm was used in this study as the largest symbolic size of the total not exceeding 20 mm. The compressive strength of the concrete samples was determined in 7 days and 28 days.

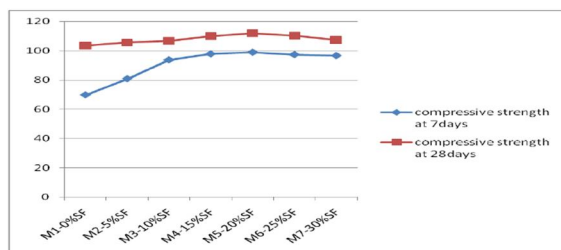


M100 with different proportions of silica fume at 7 days and 28 days compressive strength

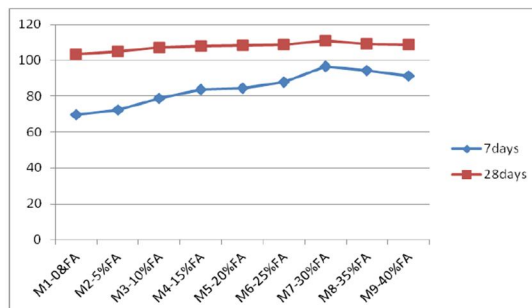

M100 with different proportions of fly ash at 7 days and 28 days compressive strength

**Compressive strength of M100 at different ages**

Grade of concrete	Compressive strength in N/mm <sup>2</sup> at different ages							
	1 day	3 days	7days	14days	28 days	56 days	90 days	180 days
M100	18.5	43.3	69.7	87.5	103.4	110.74	124.08	128.45

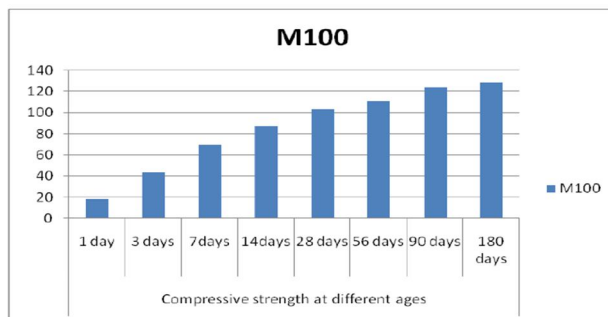

A total of 4 combinations were prepared for the present research work namely

M100 with 20% SF (SFC),

M100 with 30% FA (FAC),

M100 with 20% SF and 30% FA (FASFC),

And conventional concrete M100.

1) Test on sulphate resistance of high strength concrete using mineral admixtures

Sulphate resistance of concrete is determined by immersing test specimens of size 150 X150 X 150 mm cubes in 10% sodium sulphate. The deterioration of specimens are presented in the form of percentage reduction in weight and percentage reduction in compressive strength concrete of specimens at 28, 56, 90 and 180 days.

2) Test on acid attack of high strength concrete using mineral admixtures


Acid attack is determined by immersing test specimens of size 150 X150 X 150 mm cubes in 10% H<sub>2</sub>SO<sub>4</sub> solution and 10% HCl solution respectively. The deterioration of specimens are presented in the form of percentage reduction in weight and percentage reduction in compressive strength concrete of specimens at 28, 56, 90 and 180 days.

Weight loss of different concrete mix in acid and base curing

Grade of Concrete	10% HCl solution				10% Na <sub>2</sub> SO <sub>4</sub> solution				10% H <sub>2</sub> SO <sub>4</sub> solution			
	28 days	56 days	90 days	180 Days	28 days	56 days	90 days	180 days	28 days	56 days	90 days	180 days
Conventional	18.346	18.696	19.129	19.457	5.24	5.29	5.34	5.4	32.50	39.79	45.38	51.13
SFC	14.77	15.08	15.43	15.93	2.41	2.46	2.49	2.513	25.3	31.86	38.39	46.69
FAC	15.83	16.23	17.11	17.839	3.51	3.57	3.612	3.684	28.34	34.64	40.13	48.89
FASFC	15.29	15.55	16.18	16.67	2.89	2.916	3.233	3.493	27.3	33.11	39.62	47.13


Compressive strength loss of concrete mix in acid and base curing

Grade of Concrete	10% HCl solution				10% Na <sub>2</sub> SO <sub>4</sub> solution				10% H <sub>2</sub> SO <sub>4</sub> solution			
	28 days	56 days	90 days	180 Days	28 days	56 days	90 days	180 days	28 days	56 days	90 days	180 days
Conventional	18.346	18.696	19.129	19.457	5.24	5.29	5.34	5.4	32.50	39.79	45.38	51.13
SFC	14.77	15.08	15.43	15.93	2.41	2.46	2.49	2.513	25.3	31.86	38.39	46.69
FAC	15.83	16.23	17.11	17.839	3.51	3.57	3.612	3.684	28.34	34.64	40.13	48.89
FASFC	15.29	15.55	16.18	16.67	2.89	2.916	3.233	3.493	27.3	33.11	39.62	47.13

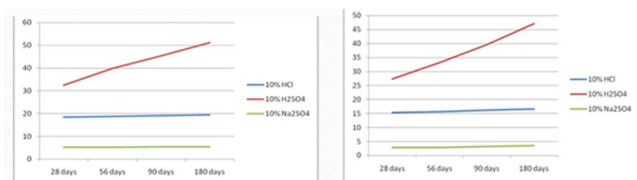

Graph 4.5. Compressive strength loss in conventional concrete


Graph 4.7. Compressive strength loss of FAC

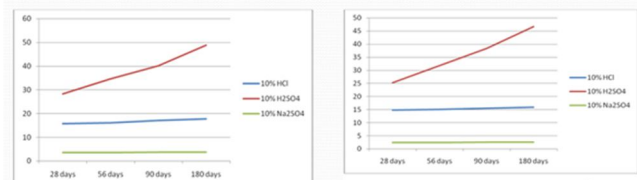

Graph 4.8. Compressive strength loss of FASFC


Graph 4.6. Compressive strength loss of SFC

### Compressive strength loss in diluted acid and base curing

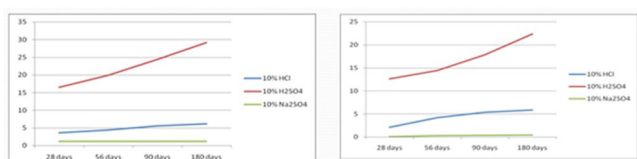

Graph 4.1. Weight loss of conventional concrete

Graph 4.2. Weight loss of SFC

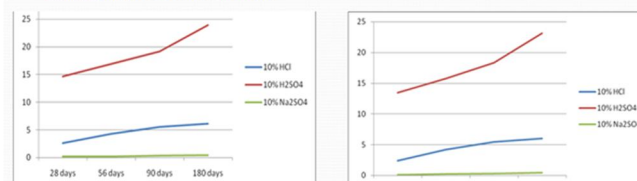

Graph 4.3. Weight loss of FAC

Graph 4.4. Weight loss in FASFC

### Weight loss in diluted acid and base curing



Cubes immersed in diluted acid and base

## IV. CONCLUSION

- A. In high strength concrete M100 Optimum results are obtained at W/C ratio 0.25.
- B. Excess amount of super-plasticizer may result in segregation of concrete and make concrete weaker.
- C. Optimum silica fume content is 20%.
- D. Optimum fly ash content is 30% .
- E. Silica fume provided better stability and good flow properties than flyash. Silica fume contribute to produce high compressive strength.
- F. With these optimum contents of silica fume and fly ash made another combination of concrete i.e FASFC. But strength values are less compared to SFC.
- G. The loss of weight and strength is more in case of immersing in 10% H<sub>2</sub>SO<sub>4</sub> compared to HCL. The loss of weight and strength is very less in Na<sub>2</sub>SO<sub>4</sub> compared Acids.

## REFERENCES

- [1] Alexander M.G., Magee B.J. 1999, Durability performance of concrete containing condensed silica fume, *Cement and Concrete Research*, 29, 917–922
- [2] Lee S.T., Moon H.Y., Swamy R.N. 2005, Sulfate attack and role of silica fume in resisting strength loss, *Cement & Concrete Composites*, 27, 65–76
- [3] Michel Mbessa, Jean Pe'ra. 2001, Durability of high-strength concrete in ammonium sulfate solution, *Cement and Concrete Research*, 31, 1227–1231.
- [4] Susanto Teng, Tze Yang Darren Lim, Bahador Sabet Divsholi. 2013, Durability and mechanical properties of high strength concrete incorporating ultra fine Ground Granulated Blast-furnace Slag, *Construction and Building Materials*, 40, 875–881.
- [5] Tamimi A.K., Abdalla J.A., Sakka Z.I. 2008, Prediction of long term chloride diffusion of concrete in harsh environment, *Construction and Building Materials*, 22, 829–836
- [6] Saravanakumar, P., Dhinakaran, G. 2014. Durability aspects of HVFA based Recycled Aggregate Concrete, *Magazine of Concrete Research*, 66(4), 186 – 195.
- [7] Topcu. 1997. Physical And Mechanical Properties Of Concretes Produced With Waste Concrete. *Cement and Concrete Research*, 27(12), 1817-1823
- [8] Saravanakumar, P., Dhinakaran, G. 2013. Strength characteristics of highvolume fly ash-based recycled aggregate concrete, *Journal of Materials in Civil Engineering*, 25(8), 1127 – 1133.
- [9] Saravanakumar, P., Dhinakaran, G. 2012. Effect of admixed recycled aggregate concrete on properties of fresh and hardened concrete, *Journal of Materials in Civil Engineering*, 24(4), 494 - 498.
- [10] Shi-cong Kou., Chi-sun Poon., Francisco Agrela. 2011. Comparisons of natural and recycled aggregate concretes prepared with the addition of different mineral admixture. *Cement and Concrete Composites*, 33, 788795.
- [11] Selvamony C. , Ravikumar M.S. , Kannan S.U. , Basil Gnanappa S., "Development of high quality self compacted self curing concrete with mineral admixtures" *International Journal on Design and Manufacturing Technologies*, Vol.3, No.2, July 2009,pp 103 - 108.
- [12] S. Venkateswara Rao, M.V. Seshagiri Rao, P. Rathish Kumar, " Effect of Size of Aggregate and Fines on Standard And High Strength Self Compacting Concrete", *Journal of Applied Sciences Research*, 6(5): 433-442, 2010.
- [13] Youjun Xie\*, Baoju Liu, Jian Yin, Shiqiong Zhou, " Optimum blend parameters of high-quality self-compacting concrete with ultrapulverized fly fiery debris", *Cement and Concrete Research* 32 (2002) 477– 480.
- [14] Paratibha Aggarwal, Rafat Siddique, Yogesh Aggarwal, Surinder M Gupta "Self-Compacting Concrete-Procedure for Mix Design" *Leonardo Electronic Journal of Practices and Technologies*, Issue 12, January-June 2008, pp 15-24.
- [15] Soo-Duck Hwang, Kamal H. Khayat, and Olivier Bonneau, " Performance-Based Specifications of Self-Consolidating Concrete Used in Structural Applications", *ACI Materials Journal/March-April 2006*, PP 121-129. [www.basf-cc.co.in](http://www.basf-cc.co.in)
- [16] IS 12269-1989, Specification for 53 review Ordinary Portland Cement.
- [17] IS 383-1970, Specification for Coarse and Fine Aggregate from Natural Sources for Concrete.
- [18] IS 456-2000, Indian Standard Plain and Reinforced Concrete-Code of Practice.
- [19] IS 516-1959, Methods of test for quality.
- [20] IS 2386-1963, Methods of Tests for Aggregates for Concrete.
- [21] IS 3812-1981, Indian Standard Specification for Fly Ash for use as a Pozzolana and Admixture.
- [22] IS 10262-2009, Concrete blend proportioning – Guidelines



10.22214/IJRASET



45.98



IMPACT FACTOR:  
7.129



IMPACT FACTOR:  
7.429



# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089  (24\*7 Support on Whatsapp)