



iJRASET

International Journal For Research in
Applied Science and Engineering Technology



INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Volume: 8

Issue: IV

Month of publication: April 2020

DOI:

www.ijraset.com

Call:  08813907089

E-mail ID: ijraset@gmail.com

Structural, Electrical and Electromagnetic Characterization of Co^{3+} Ion Substitution on Calcium Ceramics by Sol-Gel Auto Combustion Route

Suresh S. Darokar

Shivaji Scienc College, Congres Nagar Nagpur-12

Abstract: In the present work, a series of Calcium hexaferrite (M-type) substituted with Cobalt ions were successfully synthesized by sol-gel auto combustion route with general chemical formula $\text{CaFe}_{12-x}\text{Co}_x\text{O}_{19}$ ($0 \leq x \leq 4$). Structural, electrical and magnetic properties are studied and reported. The structural properties are characterized by X-ray diffractometer and SEM. The XRD data of all the samples have confirmed the formation of single-phase M-type hexagonal ferrites with the space group of P63/mmc. Also the electrical resistivity was measured by using two probe technique. Magnetic properties are studied with the help of vibrating sample magnetometer (VSM). Saturation magnetisation, remanent magnetisation, Coercive field are calculated and reported. Results of VSM studies show the increase in saturation magnetization with the substitution.

Keywords: Hexaferrite, Retentivity, Saturation Magnetization and Coercivity

I. INTRODUCTION

Hexagonal ferrites are a large family of ferrimagnetic materials. Among these, M-type hexaferrites are the most popular due to their large applications as permanent magnets. Substituted hexaferrites belong to M-Type with general formula $\text{MFe}_{12}\text{O}_{19}$ where M is usually barium, strontium, Calcium or Lead, are of the significant attractions for researchers because of their applications in the field of material science as permanent magnets, microwave devices so on and so forth (1-5). The basic structure is hexagonal with all 38 oxygen ions occupying the interstitial sites forming a close packed assembly. 24 ferric ions occupy five different locations in the unit cell such as 2a, 2b, 4f1, 4f2 and 12k, where 2a, 4f2 and 12k are octahedral, 4f1 is tetrahedral and 2b is bi-pyramidal sites. The magnetic nature of magnetoplumbites is determined by the substituted trivalent ions for ferric ions, which occupy different sites in the structure (6-10). The Fe^{3+} ions when replaced partially by other trivalent metal ions, the magnetic properties of the calcium ferrite undergo changes [11,12]. To prepare Hexagonal ferrites, various synthesis methods like chemical co-precipitation [13], hydrothermal [14], sol-gel [15,16], combustion [17] etc. have been developed. In the present work, Calcium hexaferrites substituted with trivalent Co ions synthesized by combustion method are studied and reported.

II. EXPERIMENTAL

Calcium hexaferrites substituted with trivalent Co^{3+} ions with general chemical formula $\text{CaFe}_{12-x}\text{Co}_x\text{O}_{19}$ ($0 \leq x \leq 5$) have been synthesized successfully by sol-gel auto combustion technique. Samples were prepared with AR grade calcium nitrate, iron nitrate and Cobalt nitrate. Urea ODH ($\text{C}_2\text{H}_6\text{N}_4\text{O}_2$) was used as fuel. All Samples were calcinated at 900°C for 4 hours and allowed to cool gradually at rate of 5 degree per minute.

The structural characterization of the samples was performed by Philips X-ray diffractometer with Cu-Ka radiation ($\lambda=1.5405\text{\AA}$) in the 2θ range of $10-120^\circ$, in angular steps of 0.02° . The average particle size D, was determined from line broadening of (107) reflection using Scherrer formula given by

$$D = k\lambda/h\cos\theta$$

where D is average size of the crystallites, k is Scherrer constant (0.9), λ is wavelength of radiation (1.54056\AA) and h is peak width of half height (FWHM). Values of lattice constant 'a' and 'c' and unit cell volume 'V' were calculated by using following equations and are given in table 1. The morphology and size of the particles were studied using SEM (fig. 2.) The particle size of each sample was analysed from the SEM images with the help of Image J software and the values are found to be in comparable with calculated values. The measurement of electrical conductivity by using two-terminal method was employed. The measurements were taken in the range from 150°C to 850°C . Finally graphs of $\ln \sigma$ against $1/T$ were plotted and from the slope of these graphs the activation energies for the compounds were calculated using the relation,

$$\Delta E = 8.617 \times 10^{-5} [\Delta(\ln(1/\sigma)) / \Delta(1/T)]$$

Also Seeback coefficient measurements were carried out using two-probe set up fabricated in the laboratory. The measurements were taken in the temperature range 350°K to 450°K. The type of carriers responsible for conduction was determined in each of the compound from these studies. In order to prepare pellet for the above observations the compound prepared was grounded to fine particle size in an agate mortar. The powder was mixed with 5% polyvinyl acetate solution made in A.R. grade acetone, as binder and mixed thoroughly. This mass was then transferred to a die and pressed under pressure of 5 tons per cm² using a hydraulic press. The pellets so prepared were then heated in a furnace up to 500 °C to remove the binder. After maintaining this temperature for few hours the pellets were slowly cooled to room temperature. In this way crack free pellets in the shape of a cylinder of small height were obtained. The end faces of the pellets, so prepared, were gently grounded over zero number sand paper to ensure smooth surfaces. The dimensions of the pellets were measured accurately. The smooth and flat parallel faces of the pellets were coated with uniform thin layer of silver paste to facilitate a good electrical contact with the electrodes. The silver paste was dried by heating the pellet slowly for few hours in air at 500 °C. The thin coating of silver paste thus formed was adherent and chemically inert. Pellets were stored in desiccators if found necessary. The magnetic properties were studied using vibrating sample magnetometer at room temperature. Applying the field in the range of -20K - +20K, carried out measurements. Saturation magnetization, Coercive field and Remanent magnetization were calculated and reported (Table 2).

III. RESULTS AND DISCUSSION

1) *Structural Analysis:* Investigated ferrite sample Ca Fe_{12-x}Co_xO₁₉ powder synthesized by sol-gel auto combustion technique correspond to M-type calcium hexaferrite structure as shown fig(1). X-ray diffraction pattern of Ca Fe_{12-x}Co_xO₁₉ hexagonal ferrite under investigation were obtained using X-ray diffractometer. The hexagonal M-structure with space group (P6₃/mmc) (No. 194), which confirms that phase belongs to magnetoplumbite indicating that the crystal structure were single phase hexagonal magnetoplumbite after substitution with Co³⁺ ions respectively. The lattice constant a and c of hexagonal calcium ferrite were calculated using equation (1)

$$\frac{1}{d^2} = \frac{4h^2 + k^2 + l^2}{3a^2} + \frac{l^2}{c^2}$$

Where h ,k, l are miller indices, d is interplaner distance. The lattice parameter a and c found to be 6.023 to 6.055 (Å) and 22.304 to 21.629 (Å) respectively. There is a small shift in the peak position with the increase of substituting ion. This is due to the small ionic radius of Co³⁺ (0.61 Å) compared to the ionic radius of Fe³⁺ (0.65 Å). Structural parameters of the samples are given in table 1. There is a variation in the particle size with substitution. Volume of the cell also slightly decreases with the increase in substitution.

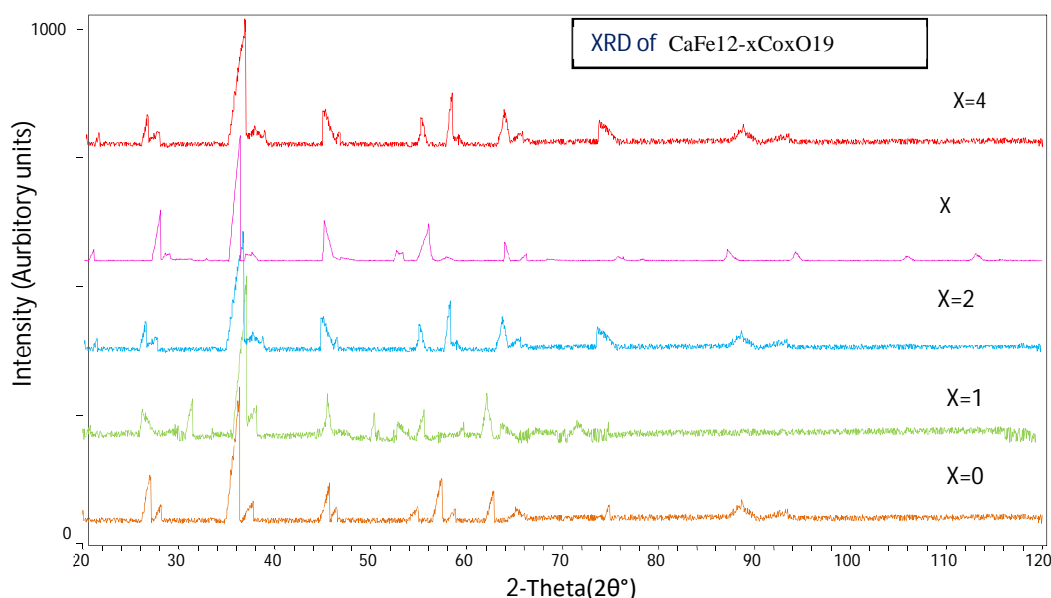
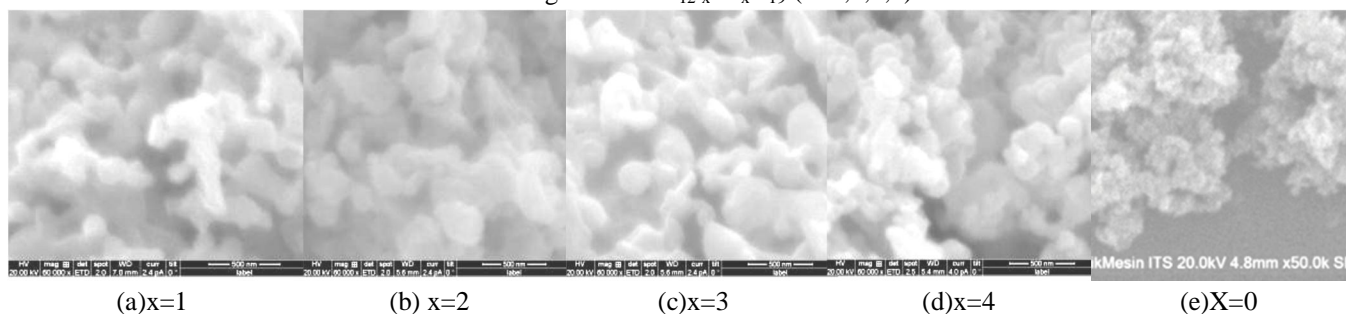


Figure. 1: XRD spectrum of Ca Fe_{12-x}Co_xO₁₉

Table 1: Structural parameters of $\text{Ca Fe}_{12-x}\text{Co}_x\text{O}_{19}$

Sample $\text{CaCo}_x\text{Fe}_{12-x}\text{O}_{19}$	D(nm)	a(Å)	c(Å)	V(Å ³)
X=0	29	6.023	22.304	699.868
X=1	27	6.036	22.096	697.687
X=2	13	6.044	21.979	695.932
X=3	17	6.050	21.724	690.378
X=4	24	6.055	21.629	686.237

- 2) *Microstructure Analysis*: The SEM images of the samples are shown in figure-2. From the figures it is evident that particles are in Nano size and almost spherical in shape.

SEM Images of $\text{Ca Fe}_{12-x}\text{Co}_x\text{O}_{19}$ (x=1,2,3,4)

Figure 2: SEM Images of $\text{Ca Fe}_{12-x}\text{Co}_x\text{O}_{19}$ (x=0,1,2,3,4)

- 3) *Electrical Studies*: In this present work, the observed value of electrical conductivity, activation energy for specimens are tabulated in table – 2

Table – 2: Electrical conductivity of $\text{Ca Fe}_{12-x}\text{Co}_x\text{O}_{19}$ ferrites

Compounds	Electrical Resistivity at room temperature(Ω cm)	Activation energy E in (ev)	Electrical Conductivity at room temperature. (Ω cm) ⁻¹
$\text{CaFe}_{12}\text{O}_{19}$	4.559×10^{11}	0.77	2.193×10^{-12}
$\text{CaFe}_{11}\text{CoO}_{19}$	3.21×10^9	0.63	3.11×10^{-10}
$\text{CaFe}_{10}\text{Co}_2\text{O}_{19}$	4.65×10^7	0.52	2.148×10^{-8}
$\text{CaFe}_9\text{Co}_3\text{O}_{19}$	6.84×10^6	0.48	1.46×10^{-7}
$\text{CaFe}_8\text{Co}_4\text{O}_{19}$	1.72×10^5	0.39	5.78×10^{-6}

The plot of $\ln \sigma$ vs $(1/T) \times 10^3$ K for the entire sample was almost linear. The electrical conductivity of these ferrites increases with increasing ferrite ion concentration. The electrical conductivity of sintered specimens varies from $2.193 \times 10^{12} \Omega^{-1} \text{cm}$ to $5.78 \times 10^{-6} \Omega^{-1} \text{cm}$ of these ferrites. The other workers have obtained a conductivity value of $2 \times 10^{-2} \Omega^{-1} \text{cm}$ for calcium ferrite that obtained is $2.3 \times 10^{-6} \Omega^{-1} \text{cm}$ [21].

The electrical conductivity value obtained for the compounds are 2.193×10^{-12} to $5.78 \times 10^{-6} \Omega^{-1} \text{cm}$. The value of the conductivity may be partly attributed to the low evaporation of calcium from the sample prepared different from these of Rozlescu et al 1974 and Venugopal Reddy 1981. The variation of activation energy with the substitutional variable parameters x -may be explain on the basis of Vewrway model [22-24], a small number of ferrous ions (Fe^{+2}) are generally developed during sintering process which lead the conductivity in ferrites suggesting the hopping mechanism according ($\text{Fe}^{+2}-\text{Fe}^{+3}+e^-$) [25]. However these transition take place for a very small interval of time and are not detectable by the ordinary method. This valence exchange mechanism of Verwey may be considered for these ferrites as general applicable to M-type ferrite.

- 4) **Magnetic Studies:** The hysteresis B-H curve measurements were carried out at room temperature, coeresivity (H_c), retentivity (R_e), saturation magnetization (M_s) and magnetic moment are calculated and listed in Table-2. The coeresivity for $\text{Ca Fe}_{12-x}\text{Co}_x\text{O}_{19}$ which linearly decreases with decreasing Co^{+3} ions doped. The continuous decreases of coeresivity, Retentivity, saturation magnetization and magnetic moment with decreasing Co contents, may be explained by assuming that Co^{3+} substitution is preferentially performed on the spin up magnetic sublattices for the composition. It is evident from the fact that Co ions is magnetic in nature. In these compounds the magnetic moment from octahedral surrounded ferric ions in the spinal blocks and those in the trigonal bipyramidal sites are opposed by a minority of ferric ions in tetrahedral sites of the spinel block along with octahedral sites. Magnetic hysteresis B-H curve of Cobalt doped calcium hexaferrites as shown in Figure 3. Hysteresis increases with the substitution and maximum for $\text{Ca Fe}_{12-x}\text{Co}_x\text{O}_{19}$. This may be due to the site preference of Cobalt. Calculated values are shown in Table 2. From the squareness ratio it is confirmed that the samples are multi domain.

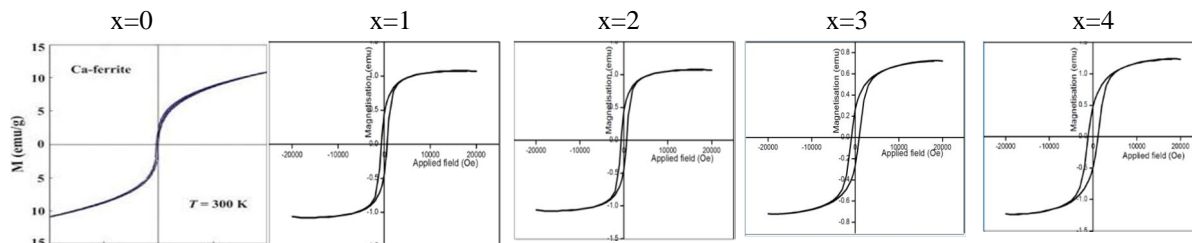

Figure 3: Hysteresis curve of $\text{Ca Fe}_{12-x}\text{Co}_x\text{O}_{19}$ ($x=0,1,2,3,4$)

Table 2: Magnetic parameters of $\text{Ca Fe}_{12-x}\text{Co}_x\text{O}_{19}$

compounds	M_s (emu/g)	M_r (emu/g)	H_c (Oe)	M_r/M_s
$\text{CaFe}_{12}\text{O}_{19}$	14.6	0.52	489.65	0.356
$\text{CaFe}_{11}\text{CoO}_{19}$	26.3	0.95	732.51	0.363
$\text{CaFe}_{10}\text{Co}_2\text{O}_{19}$	45.2	1.66	874.52	0.367
$\text{CaFe}_9\text{Co}_3\text{O}_{19}$	62.8	2.47	1141.27	0.394
$\text{CaFe}_8\text{Co}_4\text{O}_{19}$	64.6	2.68	634.14	0.415

IV. CONCLUSIONS

In this investigated series of cobalt substituted calcium hexaferrite samples with chemical formula $\text{Ca Fe}_{12-x}\text{Co}_x\text{O}_{19}$ ($x = 0, 1, 2, 3, 4$) have been prepared using solution auto combustion technique. The X-ray diffraction patterns reveal the formation of hexagonal structure with space group P63/mmc, without any trace of secondary phases. A decrease in the lattice parameter 'c' with increasing Co^{3+} substitution is due difference in ionic radii of Co^{3+} ion (0.61 \AA) and Fe^{3+} ion (0.65 \AA). Increasing the amount of Cobalt affected the morphology of the particles. Agglomeration is increased with the increase of cobalt content. From SEM it is confirmed that the particles are Nano particles. The electrical conductivity of $\text{Ca Fe}_{12-x}\text{Co}_x\text{O}_{19}$ at different concentrations substitution has been explained on the basis of the hopping mechanism of holes (Co^{2+} and Co^{3+}) and electrons (Fe^{2+} and Fe^{3+}). As evident from the change in slope of the Arrhenius plot at temperature, the variation in the dc electrical conductivity of pure $\text{Ca Fe}_{12-x}\text{Co}_x\text{O}_{19}$ ($x = 0$) and substituted Co^{3+} ions in calcium ferrite $\text{Ca Fe}_{12-x}\text{Co}_x\text{O}_{19}$ ($x = 1, 2, 3, 4$) shows a definite kink, which corresponds to ferromagnetic to paramagnetic transitions. The activation energy in the paramagnetic region is higher than the ferromagnetic region. Ferrite with the presence of Co leads to a decrease in activation energy and a decrease in conductivity because there is a significant decrease in crystallite shape area. The presence of Co in ferrites leads to disorder and hence to localization of electrons, leading to the metal-insulator transition-like properties of the Anderson model. The lattice disorder plays a significant role in determining dc conductivity behavior of such ferrites. It was found that replacement of Fe^{3+} with concentration of Co^{3+} leads to an increase in saturation magnetization, remanent magnetization and a significant increase in the coercive field. From the values of Squareness ratio it is clear that the particles are multi domain.

V. ACKNOWLEDGEMENT

Author is thankful to UGC New Delhi, INDIA for providing financial assistance to carry out this work under minor research project scheme File No 47-1345/10(WRO). Author also thankful to D.K.Kulkarni, S.B.Khasare and J.M.Khobragade to guiding me for synthesis and characterization of series of calcium mixed lanthanum hexaferrite ceramic.

REFERENCES

- [1] Lisjak D., Drofenik M. J.Eur. Ceram. Soc. 24, 1841- 1845. (2004)
- [2] Singhal S., Garg A.N, Chandra K., J.Magn. Magn. Mater. 285 193 (2005)
- [3] Robert C. Pullar. Progress in Materials Science 57 1191–1334 (2012)
- [4] Snoek, J.L., “New Developments in Ferromagnetic Materials”, Elsevier Publishing Co., Inc., New York Amsterdam (1947).
- [5] Adelskold V., Arkiv Kemi Min. Geol 1938, 12/A/29, 1.
- [6] Kulkarni D.K. and Prakash C.S. Bull Mater Sci., 17, 35 (1994).
- [7] Prakash C.S. and Kulkarni D.K., Ind J. Pure Appl Physics. 32361
- [8] DarokarSsuresh. S. et.al, J. Adv. Appl. Sci. Res, 2013, 4(1): 173-177
- [9] Darokar S.S, RewatkarK.G & Kulkarni D.K.;Mater Chem.Phys.**56** ,84-85(1998)
- [10] Prakash C.S. and Kulkarni D.K. International Journal of E-ISSN: Knowledge Engineering ISSN: 0976- 5816 & 0976-5824, Volume 3, Issue 1, (2012).
- [11] H. Kojima, K. Goto, in Proceeding of Inter Conference on Ferrites, Center for Academic publication, Japan, 198 p. 335.
- [12] P. Lubitz, C. Victoria, J. Schelleng, W.G.Maisch, J.Magn. Mater. 15145 (1980).
- [13] Ataei A. and Heshmati- Manesh S. J. European Ceram. Soc., 21, 1951- 1955 (2001).
- [14] Wang J.F., Paton C.B., Ciossinger R., Harris I.R. J. Alloys. Compd., 369,170 177 (2004).
- [15] Jotania R.B., Khomane R.B., Chauhan C.C., Menon S.K., Kulkari B.D. J. Magn. Magn. Mater. 310, 2477- 2479 (2002).
- [16] Junliang L., Yanwei Z., Cuijing C., Wei Z., European Ceram. Soc., 30, 993-997 (2010).
- [17] Huang J., Zhuang H., Li W., J. Magn. Magn. Mater. 256 390 (2003).
- [18] Albense G, Carbulichhio and Deril A J.Phys Solid State: A 23 (1974) 351.
- [19] Redrigue.Z, Obradors X, Labrata A, Tejeja.J.Pernet M. M.Solid Paul and J.Tholente, J. Phys Collog 149 (1988) 119
- [20] Verstegen J.M., D.T.J.Solid State Chem 1(1973) 468.
- [21] Verway E. J, De-Bar. J.H, Pec.Trar.Chem Pay Bull 55 (1936)531
- [22] Lamani A.R, et.al.,J.Mater.Res.Innov.(2011)15 No.3,186.
- [23] Rezlescu N., Condurachi D., Petrarju P.and Lucca E, J.A.M .Ceream Soc.57(1974)40.
- [24] Fang T. T, J.B.Hawan and F.S.Shuun, J.Mater ci Lett 11 (1992) 127.
- [25] Darokar S.S. et.al.,Indian.J.Phys.74A (2) (2000)155-157.



10.22214/IJRASET



45.98



IMPACT FACTOR:
7.129



IMPACT FACTOR:
7.429



INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089  (24*7 Support on Whatsapp)