



# IJRASET

International Journal For Research in  
Applied Science and Engineering Technology



---

# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

---

**Volume: 9      Issue: IV      Month of publication: April 2021**

**DOI: <https://doi.org/10.22214/ijraset.2021.33581>**

**[www.ijraset.com](http://www.ijraset.com)**

**Call:  08813907089**

**E-mail ID: [ijraset@gmail.com](mailto:ijraset@gmail.com)**

# Green synthesis: Synthesis and Characterization of Titanium Dioxide Nano Particles using Aloe Vera Extract

N. Kamatchi Devi<sup>1</sup>, B. Chandar Shekar<sup>2</sup>

<sup>1</sup>Department of Physics, Sri Ramakrishna Polytechnic College, Coimbatore, Tamilnadu, India.

<sup>2</sup>Department of Physics, Kongunadu Arts and Science College, Coimbatore, Tamilnadu, India.

**Abstract:** Green synthesis of nano particles aims at reducing generated waste and implementing sustainable processes. Green processes using mild reaction conditions and nontoxic precursors have been emphasized in the development of nanotechnology for promoting environmental sustainability. In the present work, nano particles of titanium dioxide were synthesized using an aqueous solution of Aloe Vera extract. Synthesized nano particles are characterized by X-ray diffraction (XRD), Scanning Electron Microscope (SEM), Energy dispersive spectroscopy (EDS), Ultra Violet Visible Spectrum Analysis (UV) and Fourier Transform Infrared Spectroscopy (FTIR).

**Keywords:** Green Synthesis; Titanium tetra isopropoxide; TiO<sub>2</sub> Nanoparticles; Aloe Vera;

## I. INTRODUCTION

A technology that measures and manipulate or incorporate materials with a critical dimension between 1-100nm. The unique physical and chemical properties are due to its high surface to volume ratio comparing with micro or bulk sized. Nanotechnology is the engineering of functional systems at the molecular scale. Nanomaterial's are of great interest because at this scale unique optical, magnetic, electrical and other properties emerge. The fabrication of nano particles with strict control size, shape, and crystalline structure has inspired the application of nanotechnology to numerous fields including catalysis, medicine and electronics.

Titanium dioxide (TiO<sub>2</sub>) has become part of our everyday lives. It is found in various consumer goods and products of daily use such as cosmetics, paints, dyes and varnishes, textiles, paper and plastics, food and drugs, and even paving stones. TiO<sub>2</sub> is a promising material due to its photo-stability, chemical structure, physical, optical, electrical properties, low cost and excellent degradation of organic pollutants. Green synthesis is one of the newly introduced or recently developed non conventional methods to produce nanoparticles. In this method a number of biological systems which include plant extracts, green algae, micro organisms, such as fungi and bacteria are used to synthesis the nanoparticles. Nanoparticles produced by plants are more stable.

This method reduces the use of hazardous substances in the design, manufacture and application of chemical product. The main methods of nano particle production by chemical and physical method are costly and potentially harmful to the environment. It is desirable for biomedical applications such as drug carriers, cosmetics, and filling the material. Green synthesis of nanoparticles is an innovative branch of nanoscience

The objective of the present work is to prepare TiO<sub>2</sub> nanoparticles by green synthesis method using Aloe Vera extract.

## II. EXPERIMENTAL METHOD

In the present work, the experimental procedure comprises of two stages. First, the preparations of plant extract and secondly the preparation of titanium dioxide nanoparticles using the prepared plant extract.

### A. Preparation Of Plant Extract

The leaves of aloe Vera were separated from plant, which were thoroughly washed and cut into small pieces. For extract preparation 25g of the leaves in 100ml distilled water is taken and boiled for 2hrs at 90°C. The extract was filtered using what man filter paper. The filtrate was stored for the synthesis of nano particles.

### B. Preparation Of Tio<sub>2</sub> Nano Particles

To 0.1M of titanium tetra iso propoxide the aloe Vera plant extract was added drop wise under constant stirring to achieve a solution of pH 7. The mixture is subjected to stirring for 4hrs continuously. In this process, nanoparticles were formed and are separated using filter paper. The particles were washed with double distilled water repeatedly to remove the by-products if any. The nano particles were dried at 100°C overnight and calcinated at 450°C for 4hrs

The characterizations of prepared titanium dioxide were done by using X-ray diffraction (XRD), Scanning Electron Microscope (SEM), Energy Dispersive X- Ray Analysis (EDAX) , Ultra Violet Visible Spectrum Analysis (UV) and Fourier Transform Infrared Spectroscopy (FTIR). Flow chart depicting the green synthesis of Nano crystalline TiO<sub>2</sub> is shown in figure 2.2.1

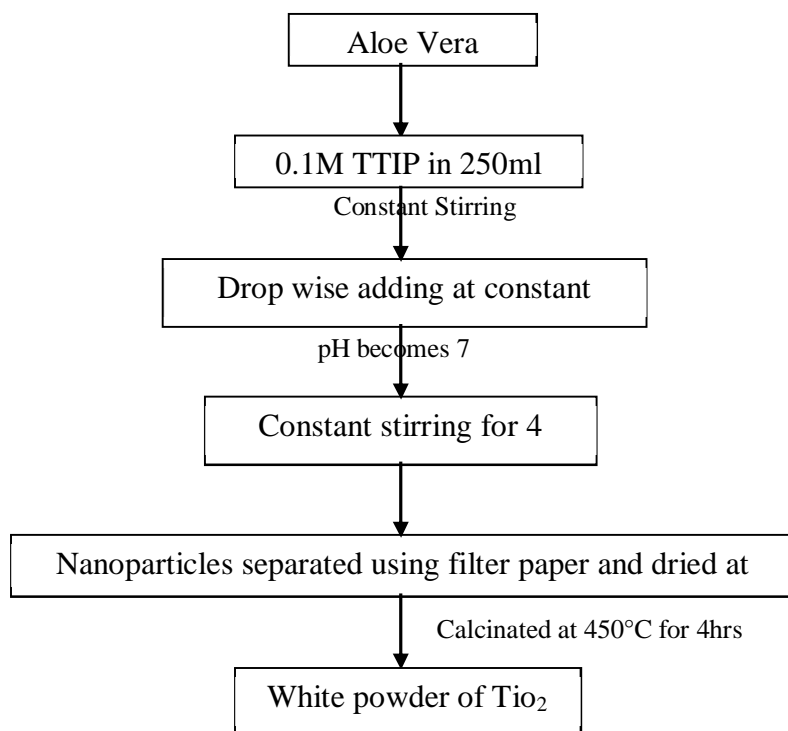


Fig 2.2.1 Flow chart for the green synthesis of TiO<sub>2</sub> Nanoparticles

### III. RESULT AND DISCUSSION

#### A. X-Ray Diffraction Analysis

X-ray Powder Diffraction (XRD) is an efficient analytical technique used determination of grain size, composition of solid solution, lattice constants, and degree of crystalline in a mixture of amorphous and crystalline substances. It is a general technique for the study of crystal structures, atomic spacing, crystallite sizes, stress analysis, lattice parameters, and quantitative phase analysis and can provide details on unit cell dimensions.

This information is important for relating the production of a material to its structure and hence its properties. For this reason, in order to investigate the phase formation and micro structure studies, the XRD analysis was carried out on the prepared TiO<sub>2</sub> nanoparticles using plant extract.

The XRD pattern of Titanium dioxide nano particle prepared using green synthesis method is shown in figure (3.1). The average crystalline size was calculated by using the data from X-ray diffraction pattern with the Debye-Scherrer formula.

The Debye-Scherrer equation is,

$$D = k\lambda / \beta \cos\theta$$

Where,

D = crystallite size

$\lambda$  = wave length of the filament used in XRD machine (1.5418 Å)

$\beta$  = Full Width Half Maximum (FWHM)

$\theta$  = angle of the corresponding peak

k = shape factor (0.94)

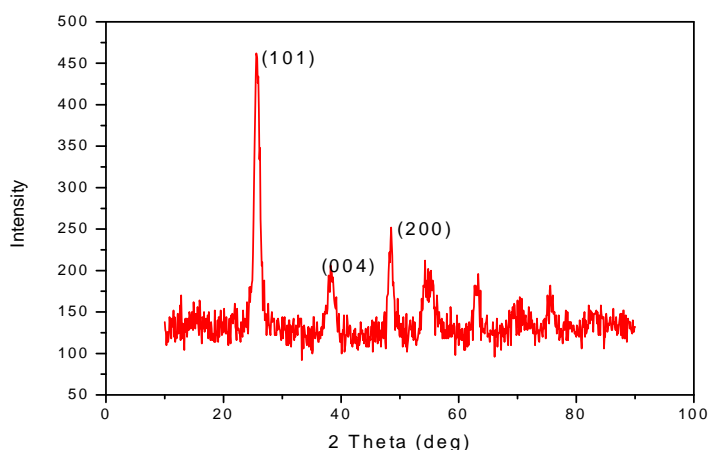


Fig 3.1.1 XRD pattern of TiO<sub>2</sub> nano particles.

The XRD spectrum showed peaks around 25<sup>o</sup>, 38<sup>o</sup>, 48<sup>o</sup>, 54<sup>o</sup>, 62<sup>o</sup> and 75<sup>o</sup>. The most intense peaks observed around at 2θ = 25.68°, 48.43°, 38.25° indexed the planes (101), (004), (200) respectively. The diffraction data were in good agreement with JCPDS card no 21- 1272. The observed peaks indicate the nature of TiO<sub>2</sub> nanoparticles. The average crystalline size was found to be in the range of 5-8 nm. The TiO<sub>2</sub> sample possessed evident diffraction peaks characteristics of anatase, which indicates that the TiO<sub>2</sub> nanoparticles prepared are predominantly of the anatase crystal phase. The peak details of the TiO<sub>2</sub> nanoparticles are listed below in the table 3.1.1

Table 3.1.1 – The peak details of the TiO<sub>2</sub> nanoparticles.

Sample	2θ(degree)	Phase and orientation (hkl)	FWHM (deg)	Crystallite size(nm)	d <sub>hkl</sub>
TiO <sub>2</sub> Nanoparticles	25.68	(101)	1.1214	7.265	3.46
	48.43	(004)	0.9700	8.979	1.87
	38.25	(200)	1.4500	5.798	2.35

**B. Scanning Electron Microscope (FESEM)**

The grain size, shape and surface properties like morphology of the prepared titanium dioxide nanoparticles were investigated by SEM analysis. The SEM image was observed within the magnification of 0.5µm. TiO<sub>2</sub> nanoparticles showed irregular agglomerated particle structure. The size was found to be 50 nm. The magnified image of titanium dioxide nanoparticles is shown in figure (3.2.1).

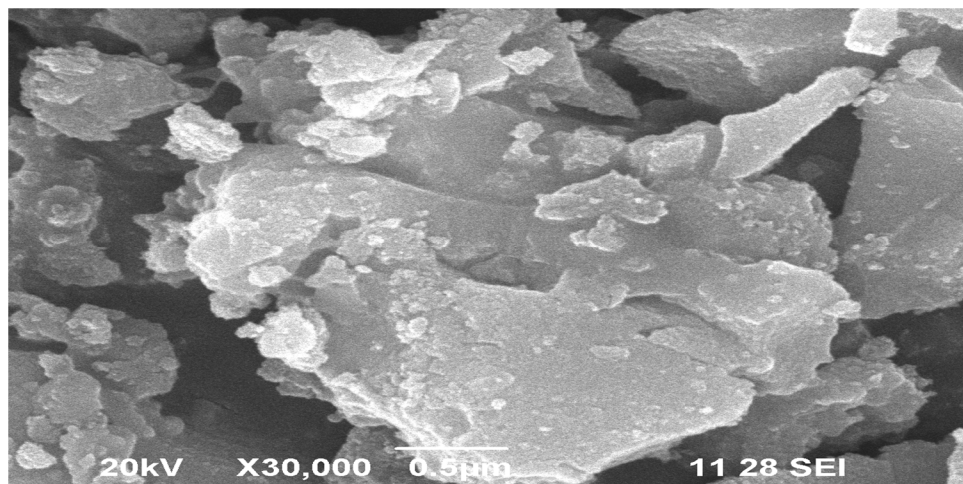


Fig 3.2.1 SEM image of TiO<sub>2</sub> nanoparticles

**C. Energy Dispersive X-Ray Analysis**

The EDAX spectrums of Titanium dioxide nanoparticles prepared using Aloe Vera extract is shown in figure (3.3.1). The EDAX spectrum revealed the presence of titanium and oxygen in the prepared samples. The EDAX analysis confirmed the formation of titanium dioxide nanoparticles. It also indicates the absence of any impurities in the prepared sample.

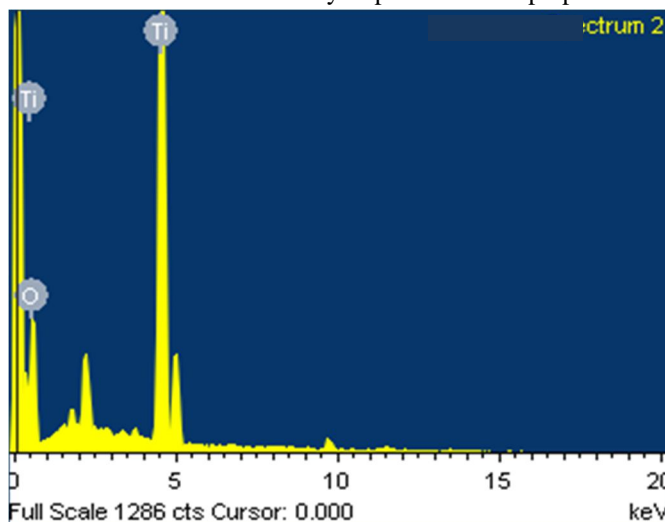


Fig 3.3.1 EDAX spectrum of TiO<sub>2</sub> nanoparticles.

**D. UV - Visible Spectroscopy**

The energy band gap value was determined based on the mathematical derivative of the optical absorption coefficient. The fundamental absorption method corresponds to band to band transitions by using energy relation. The absorption spectrum of TiO<sub>2</sub> nanoparticles exhibits a strong absorption at 410 nm. The energy band gap was determined to be 3.02 eV by using the energy relation.

$$E_g = 1240/\lambda_g$$

The UV-VIS spectrum of TiO<sub>2</sub> nanoparticles is shown in fig. (3.4.1).

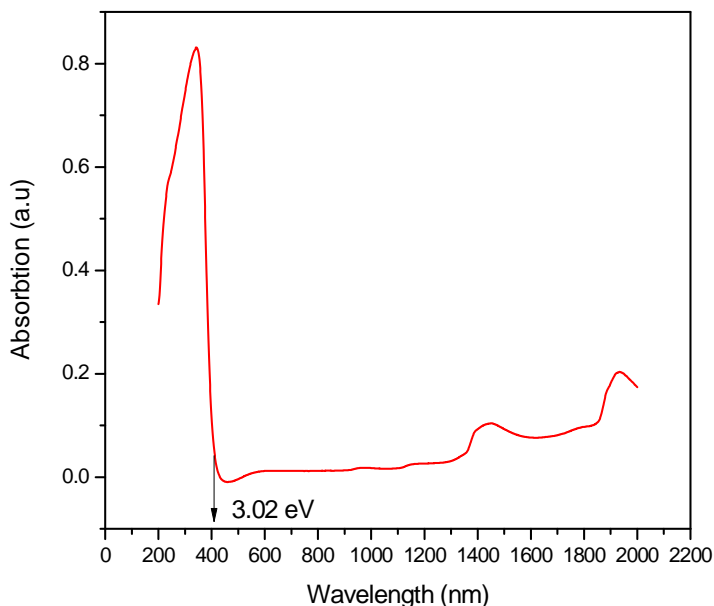


Fig 3.4.1 Absorbance spectrum of TiO<sub>2</sub> nanoparticles.

### E. Fourier Transform Infrared Spectroscopy

The FTIR spectrum of TiO<sub>2</sub> nanoparticles calcinated at 450°C for 4 hours is shown in figure. The diffraction peaks corresponding to the broad band centered at 447 cm<sup>-1</sup> which is the characteristic of Ti-O Skeletal vibration.

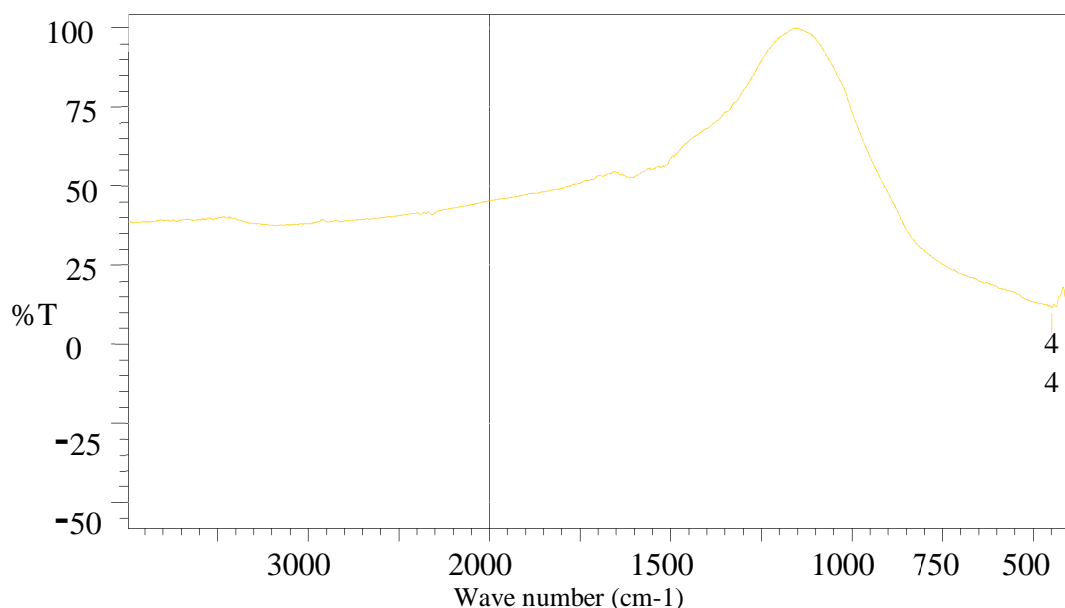


Fig. 3.5.1 FTIR spectrum of TiO<sub>2</sub> nanoparticles

## IV. CONCLUSION

The Titanium dioxide nanoparticles were synthesized by Green synthesis method using Aloe Vera extract. The prepared sample was analyzed using various characterization techniques such as XRD, SEM, EDAX, UV/VISIBLE spectrum and FTIR. The XRD pattern shows a strong diffraction peaks at  $2\theta = 25.68^\circ, 48.43^\circ$  and  $38.25^\circ$  and the peak values were in good agreement with the JCPDS card No.21-1272 representing a tetragonal structure. The particle size ranges from 5nm to 8 nm. The optical absorption UV spectrum is analysed for the TiO<sub>2</sub> nanoparticles. The band gap energy is calculated as 3.43eV and the increase in band gap is due to the defects level present in the sample as the sample contains some by-products of Aloe Vera. The SEM image shows the irregular particle structure and the size obtained as 50nm. The EDAX spectrum shows the presence of Ti and O in the prepared sample. The FTIR analysis shows the skeletal mode of vibration for the peak with wavelength of 447nm.

## REFERENCES

- [1] K.Ganapathi Rao, et-al, 2015, Green synthesis of TiO<sub>2</sub> nanoparticles using aloe Vera extract, "International journal of advanced research in physical science". Vol:2, ISSN 2349-7874.
- [2] Abdul Kadar, et-al, 2015, Synthesis and characterization of controlled size TiO<sub>2</sub> nanoparticles via green route, "International journal of science and research". ISSN: 2319-7064.
- [3] Renu sankar, et-al, Photo catalytic activity of neem engineered TiO<sub>2</sub> nanoparticles, "applied nanoscience". ISSN: 731-736.
- [4] Nithya, et-al, 2013, TiO<sub>2</sub>nanoparticles synthesis using aloe Vera gel extract, "scientific voyage". Vol:1
- [5] G.V, Khade, et-al, green synthesis of TiO<sub>2</sub> nanoparticles and its photo catalytic activity, "material science".
- [6] Anbalagan krishnasamy, et-al, 2015, Nanosized titanium using leaf extract of neem, "International journal of chemtech research". ISSN: 0974-4290. Vol:8
- [7] Saikat maitra, et-al, 2015, green synthesis of titanium dioxide nanoparticles using neem extract, "scientific voyage". Vol:1
- [8] K.Ganapathi Rao, et-al, 2015, green synthesis of titanium dioxide nanoparticles using hibiscus flower extract, "International conference on emerging technologies in mechanical sciences". Vol: 2.
- [9] A. Niyhya, et-al, 2013, Bio synthesis, characterization and application of titanium dioxide nanoparticles, "nano vision". ISSN: 2231-2579, Vol: 3.
- [10] Kumar, et-al, 2014, structural properties of TiO<sub>2</sub> nanoparticles: synthesized by Green synthesis method, "International Journal of Science and Research"; vol: 2.
- [11] Thirunavukkarasu Santhoshkumar, et-al, 2014, Green synthesis of titanium dioxide nanoparticles using neem extract; "Asian Pacific Journal of Tropical Medicine" IF: 0.926.
- [12] Rao, et-al, 2015, Green synthesis of TiO<sub>2</sub> nanoparticles using aqueous extract of orange pill as reducing agent ; "Scientific voyage", vol: 1
- [13] Jayaselan, et-al, 2013 Biosynthesis of titanium dioxide nanoparticles ; "Scientific voyage", vol: 1.
- [14] M.Sundarrajan, et-al, 2011 Green synthesis of TiO<sub>2</sub> nanoparticles by Nyctanthes Arbor-Tristis leaves; "Industrial chemistry", vol: 8.
- [15] Thirunavukkarasu, et-al, 2014 Green synthesis of Titanium dioxide nanoparticles using Psidium guajava extract and its antibacterial and antioxidant properties; "Asian pacific Journal of Tropical medicine", vol: 1.



10.22214/IJRASET



45.98



IMPACT FACTOR:  
7.129



IMPACT FACTOR:  
7.429



# INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089  (24\*7 Support on Whatsapp)