



iJRASET

International Journal For Research in
Applied Science and Engineering Technology



INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Volume: 5 Issue: VII Month of publication: July 2017

DOI:

www.ijraset.com

Call: ☎ 08813907089

E-mail ID: ijraset@gmail.com

Application of Response Surface Methodology for Element Transfer in Submerged Arc Welding using Recycled Slag

Deepanjali Nimker¹, Devender Kumar²

^{1,2}Department of Mechanical, production and industrial Engineering, Delhi Technological University

Abstract: Submerged arc welding process is a process used for manufacturing pipes and pressure vessels of varying diameter and lengths. Challenge faced during the process is the appropriation of an optimal condition of input parameters for achieving the most favourable quality of the weld. This paper attempts to embark the usage of response surface methodology for five level central composite design matrix having four factors as input variables. In this investigation, mathematical models were elaborated to analyse the performance of process variables i.e., wire feed rate, voltage, travel speed and nozzle to plate distance on element transfer of C, Mn, Si, S and P using recycled slag. They help in selecting optimum process parameters for obtaining quality desired and optimize the process.

Key words: submerged arc welding, response surface methodology, central composite design, wire feed rate, travel speed, nozzle to plate distance, recycled slag.

I. INTRODUCTION

Submerged arc welding is a diverse welding process which involves workpieces to be welded by covering it with a layer of granular flux. This Flux converts into slag after welding and due to its non-biodegradable behaviour is disposed off as a waste. This slag is recycled to be used as flux (www.paton.kiew.ua,2015 ; Beck and Jackson,1996). In order to avoid the problem of slag disposal, recycling technology has been developed to recycle fused slag (Singh and Pandey, 2009). Further, a comparison between flux and slag has been performed by evaluating weld qualification tests as well as bead geometry relationship (Singh et al., 2005; 2006).

Slag once reclaimed proves reliable as it contributes equivalent to that of virgin flux. Few researchers proposed a theory to determine the extent of Mn and Si transfer amid slag metal equilibrium (Chai & Eagar, 1982). It was observed that between slag and weld pool, transfer of Mn and Si takes place along with Cr, P, S, C, Ni and Mo. (Mitra & Eagar, 1984). Study the impact of parameters and flux basicity index on element transfer of Mn, Si, S and P, and have reported the satisfactory result.(Pandey et al., 1994).

The concept of recycling and processing of flux after welding i.e. slag has been investigated so far by few researchers. As to achieve desired features of weldment, parametric optimization is applied. They include multiple regression analysis, response surface methodology (Datta et al., 2008a; 2008b). In another study, welding parameters and flux mixture influence the weld metal configuration and mechanical properties by employing rotatable design based on statistical analysis (Kanjilal et al., 2007).

Response surface technology is an approach to conduct and elucidate the cause and effect relationship of variables influencing the output responses as a two or three-dimensional surface (Chandel, 1998). Careful conception and execution of the experimental method result in adequate and effective experimental procedure (Montgomery, 2006). RSM proves reliable in predicting the weld bead characteristics and achieving optimal process variables (Gunuraj and Murugan, 1997; 1999). This paper deals with developing a mathematical model and drawing a conclusion in graphical form by relating input parameters to the output parameters through the formulation of RSM.

II. EXPERIMENTAL SETUP

The research was executed at Delhi Technological University, Delhi. They have modern SAW facility with details given below:

Model: QSW800

Current Range: 100 – 800 A

Polarity: Pulsed AC

Input Supply: 200-400 A, 3 phase, 50 Hz supply

The weld specimen is anchored at a specific position, and electrode holder moves back and forth along the guideways, which runs through lateral lane. SAW machine operates at 200 V rated input voltage, filler wire EL-8 having 3.15 mm diameter with flux type F7AZ which generates slag after welding. The flux hopper is adjusted along with the spool holding device.

III. METHODOLOGY

The research work involves following steps to be carried out

- A. Reclamation of slag.
- B. Identify the input parameters.
- C. Deciding the working range of the process control variables, viz. wire feed rate (F), voltage (V), travel speed (S) and nozzle to plate distance (N).
- D. Developing the design matrix.
- E. Executing the experiments as per the design matrix.
- F. Observing the responses viz. Element transfer of C, Mn, Si, S and P across molten weld pool.
- G. Development of mathematical models.
- H. Analysing the adequacy of the models.
- I. Finding the significance of co-efficient.
- J. Developing the final proposed models.
- K. Graphical representation of process parameters with their main and interaction effects.
- L. Analysis of results.

IV. RECLAMATION OF SLAG

Slag once generated as a scrap is collected from the dump yard of welding laboratory of Delhi Technological University for processing. Once collected, it is crushed and sieved to achieve the granular size equivalent to fresh flux. Welding is carried out using fresh flux and pure slag, and chemical composition of weld metal deposited is compared using spectroscopy. On the basis of composition achieved, slag is modified by first crushing it to powder form in ball mill then mixing it with deoxidisers and solution of potassium silicate as a binder. This mixture then pass through 10- 15 mesh size sieve and convert into pellets which are air dried and then baked for 2 hours at 850°C. This baked slag is now crushed to the desired size and termed as reclaimed slag. Reclaimed slag is repeatedly examined for chemical composition with the help of spectroscopy till the acceptable weld metal chemistry has not achieved as per AWS standards.

A. Identify the Input Parameters

Wire feed rate (F), voltage (V), travel speed (S) and nozzle to plate distance (N) were identified as input process parameters.

B. Deciding the Working Range of the Process Control Variables

Based on the trial runs where varying one parameter and keeping others at a constant value. The upper and lower limit was coded as +2 and -2, the code value calculated as given below:

$$X_i = \frac{2\{2X - (X_{\max} + X_{\min})\}}{(X_{\max} - X_{\min})}$$

Where X_i is the code value of variable X,

X is the value for any process variable varying from $X_{\min}$ to $X_{\max}$.

Table 1 shows the selected parameters with their limits, units and notations.

Parameters	Units	Notation	limits				
			-2	-1	0	+1	+2
Wire feed rate	mm/min	F	90	107.5	125	142.5	160

Voltage	Volts	V	25	28.7	32.5	36.2	40
Travelspeed	mm/min	S	250	275	300	325	350
Nozzle to plate distance	mm	N	20	22.5	25	27.5	30

C. Developing the Design Matrix

Design matrix selected on the basis of central composite rotatable factorial consist of 31 runs is shown in table 2. It consists of full replication of 2^4 (=16) runs with seven central points and eight star points. These experimental runs allowed the approximation of varying interactive effects on element transfer.

Table 2. Design Matrix with observed values of response parameters

S.No	Design Matrix				C	Mn	Si	S	P
1	-1	-1	-1	-1	0.056	0.813	0.153	0.0185	0.0181
2	1	-1	-1	-1	0.061	0.816	0.252	0.0252	0.0252
3	-1	1	-1	-1	0.058	0.824	0.153	0.0244	0.0240
4	1	1	-1	-1	0.069	0.817	0.251	0.0289	0.0288
5	-1	-1	1	-1	0.052	0.812	0.150	0.0173	0.0172
6	1	-1	1	-1	0.053	0.824	0.151	0.0245	0.0247
7	-1	1	1	-1	0.058	0.821	0.149	0.0208	0.0207
8	1	1	1	-1	0.062	0.814	0.223	0.0297	0.0296
9	-1	-1	-1	1	0.052	0.821	0.139	0.0153	0.0154
10	1	-1	-1	1	0.058	0.814	0.234	0.0222	0.0221
11	-1	1	-1	1	0.056	0.833	0.139	0.019	0.0187
12	1	1	-1	1	0.089	0.826	0.234	0.0257	0.0259
13	-1	-1	1	1	0.055	0.817	0.135	0.0143	0.0140
14	1	-1	1	1	0.054	0.820	0.146	0.0185	0.0186
15	-1	1	1	1	0.061	0.828	0.136	0.0179	0.0178
16	1	1	1	1	0.063	0.820	0.135	0.0234	0.0235
17	-2	0	0	0	0.048	0.823	0.125	0.0203	0.0202
18	2	0	0	0	0.057	0.817	0.153	0.0314	0.0313
19	0	-2	0	0	0.058	0.812	0.149	0.0126	0.0127
20	0	2	0	0	0.074	0.827	0.150	0.0223	0.0220
21	0	0	-2	0	0.061	0.824	0.225	0.0210	0.0209
22	0	0	2	0	0.055	0.816	0.173	0.0190	0.0190
23	0	0	0	-2	0.062	0.812	0.148	0.0256	0.0258
24	0	0	0	2	0.057	0.827	0.150	0.0170	0.0168
25	0	0	0	0	0.060	0.821	0.153	0.0213	0.0212
26	0	0	0	0	0.057	0.820	0.173	0.0215	0.0215
27	0	0	0	0	0.059	0.819	0.145	0.0211	0.0213
28	0	0	0	0	0.062	0.820	0.152	0.0212	0.0214
29	0	0	0	0	0.058	0.823	0.149	0.0214	0.0212
30	0	0	0	0	0.058	0.819	0.151	0.0213	0.0210
31	0	0	0	0	0.057	0.821	0.150	0.0252	0.0255

D. Executing the Experimentation as per the Design Matrix

The experiments were executed as per design matrix in order to avoid the chances of systematic errors within the system.

E. Observing the Responses

Mild steel plates were cross-sectioned from middle to obtain two transverse specimens. The observed values of responses i.e., C, Mn, Si, S and P, were given in table 2.

F. Development of Mathematical Models

$Y = f(F, V, S, N)$ expresses the response function for defined mathematical model. The relationship for second degree response surface is expressed as:

$$Y = b_0 + b_1F + b_2V + b_3S + b_4N + b_{11}F^2 + b_{22}V^2 + b_{33}S^2 + b_{44}N^2 + b_{12}FV + b_{13}FS + b_{14}FN + b_{23}VS + b_{24}VN + b_{34}SN$$

G. Analysing the Adequacy of the Models

Analysis of variance technique (ANOVA) was used to test the adequacy of model and according to this technique []:

- 1) For 95 % level of confidence the value of F ratio_{calculated} < the value of F ratio_{tabulated}.
- 2) For the same level of confidence, the model may be considered adequate if value of R ratio_{calculated} > value of R ratio_{tabulated}.

It was found that the models are adequate as inferred from table 4.

Element transfer%	First order terms		Second order terms		Lack of fit		Error terms		F ratio	F tab.	Model adequate
	S.S	DF	S.S	DF	S.S	DF	S.S	DF		4.09	Yes
C	0.0000 473	4	0.0000 242	10	0.000 242	10	0.000 0194	6	2.88	4.09	Yes
Mn	0.0000 048	4	0.0000 0727	10	0.000 0727	10	0.000 0117	6	0.09 0	4.09	Yes
Si	0.0014 24	4	0.0006 76	10	0.006 75	10	0.000 493	6	3.14	4.09	Yes
S	0.0001 88	4	0.0000 0104	10	0.000 004	10	0.000 0131	6	2.7	4.09	Yes
P	0.0000 188	4	0.0000 0104	10	0.000 0104	10	0.000 0131	6	0.47	4.09	Yes

H. Finding the Significance of Co-Efficient

Appraise of regression coefficient gives us a notion of how the control variables affect the responses significantly. It is clearly evident, without sacrificing much of accuracy and reducing mathematical labor the coefficients can be eliminated. For this student's t-test is used and as per this test,

- 1) Analogous to a coefficient the calculated value of t is compared with tabulated value of t at a specific level of probability.
- 2) If $t_{\text{calculated}} > t_{\text{tabulated}}$ then at the corresponding level of probability, the coefficient is said to be significant.

I. Developing the Final Proposed Models

The proposed mathematical model is developed on the basis of 't' test. The developed models are given below:

V. RESULTS & DISCUSSIONS

Figure 1 described the variation in carbon percentage with respect to voltage and wire feed rate it has been seen that carbon percentage is maximum, i.e. 0.07% at wire feed rate 142.5mm/min and 36.2volts. Figure 2 shows the manganese percentage variations with respect to wire feed rate and voltage. Maximum value of manganese percentage found to be around 0.826% at wire feed rate 107.5mm/min and 36.2volts. Figure 3 shows the silicon percentage variations with respect to wire feed rate and voltage. It has been observed that highest silicon percentage is 0.18% at wire feed rate 142.5mm/min and 36.2volts. Figure 4 illustrates the variation in sulphur percentage 0.027% at wire feed rate 142.5mm/min and 36.2volts. Figure 5 demonstrates the variation in percentage of phosphorous with respect to wire feed rate and wire feed rate. It has been found that 0.027% phosphorous percentage with respect to wire feed rate 142.5mm/min and 36.2volts. at the desirability of 0.874 the optimized value of carbon percentage is 0.083%, manganese percentage is 0.865%, silicon percentage is 0.194%, sulphur percentage is 0.0284%, and phosphorous percentage is 0.0293% with the optimized parameters 36.8volts and 143.6mm/min.

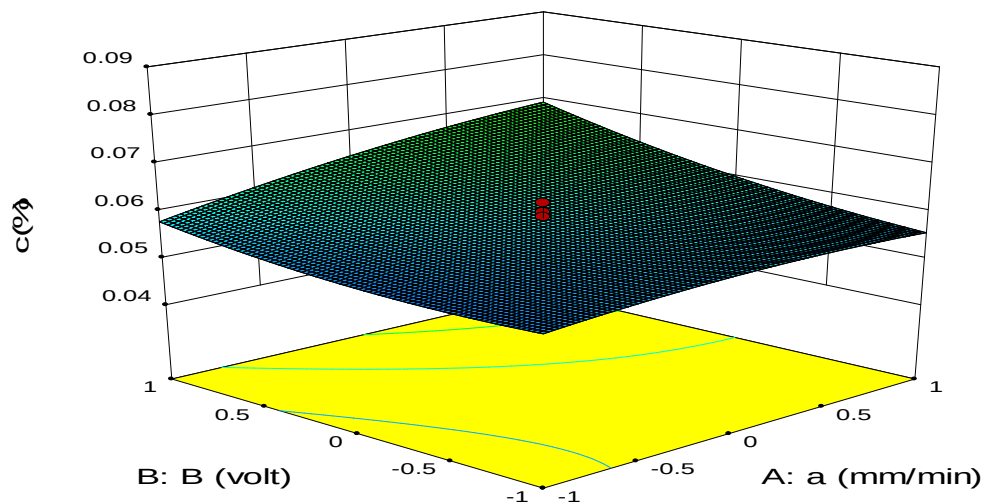


Figure 1. Variation in carbon percentage with voltage and feed rate

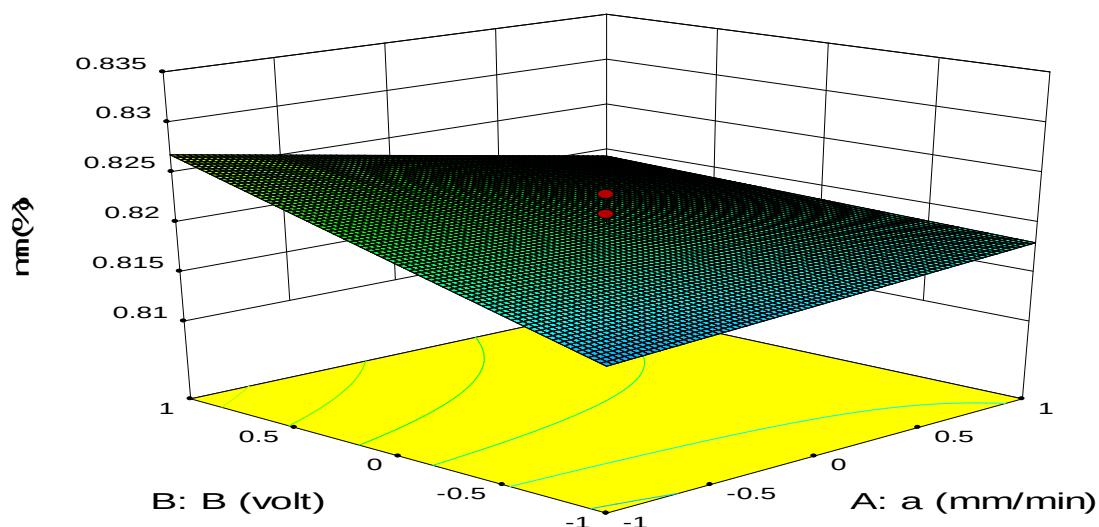


Figure 2 Variation in manganese percentage with voltage and feed rate

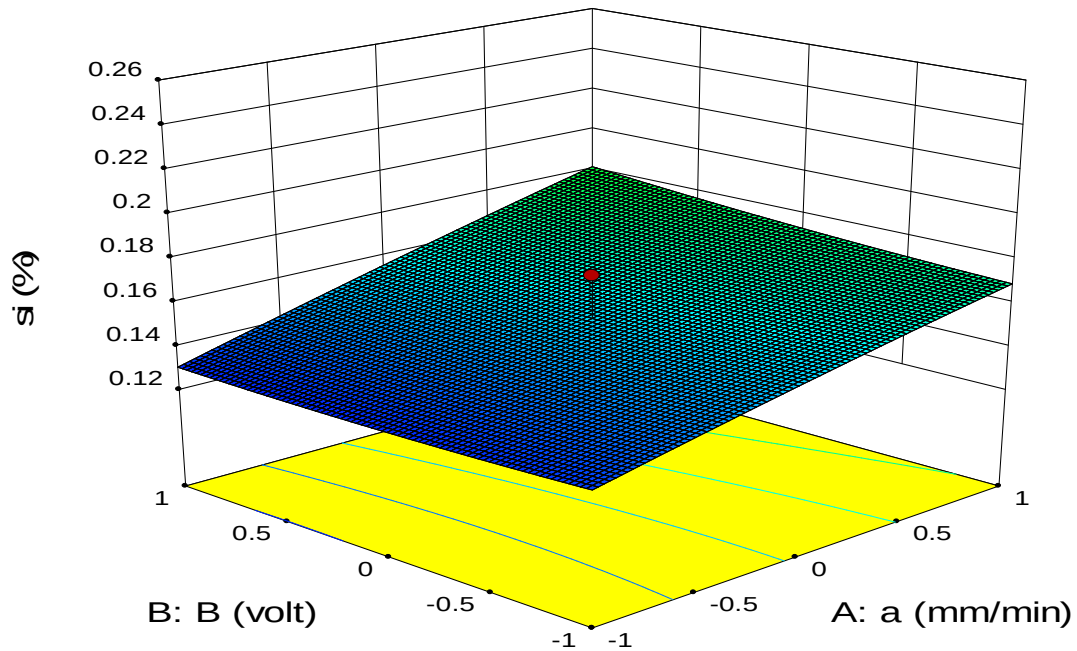


Figure 3 Variation in silicon percentage with voltage and wire feed rate

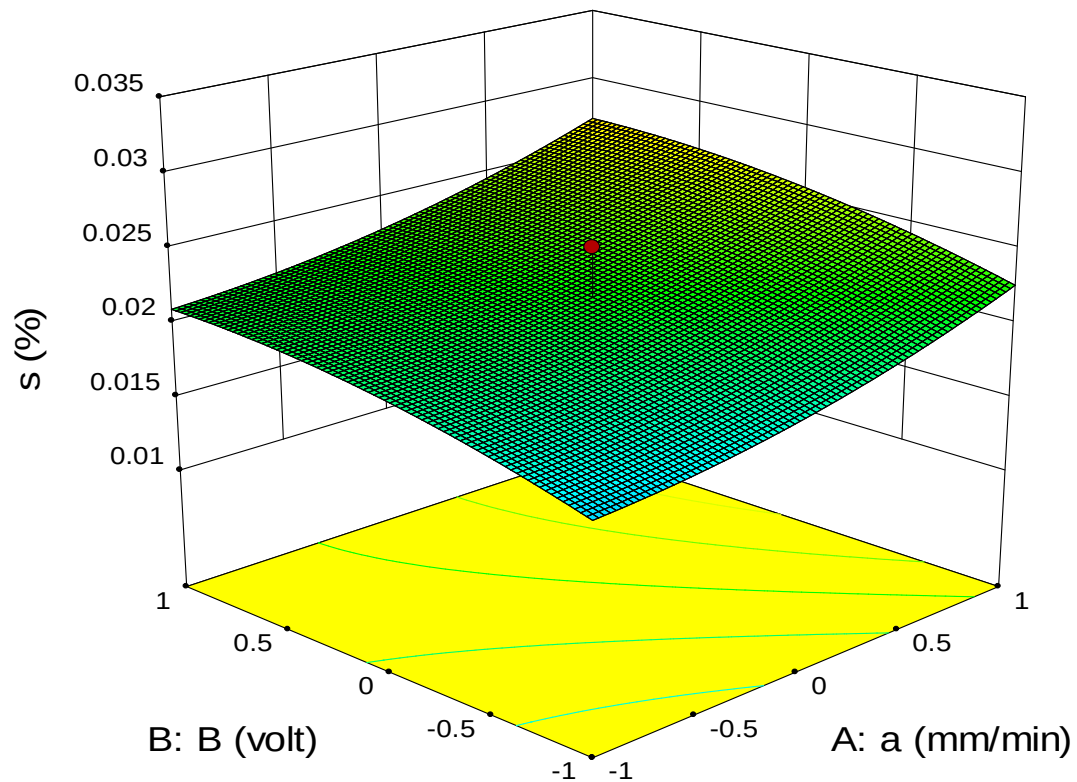


Figure 4 Variation in sulphur percentage with voltage and wire feed rate

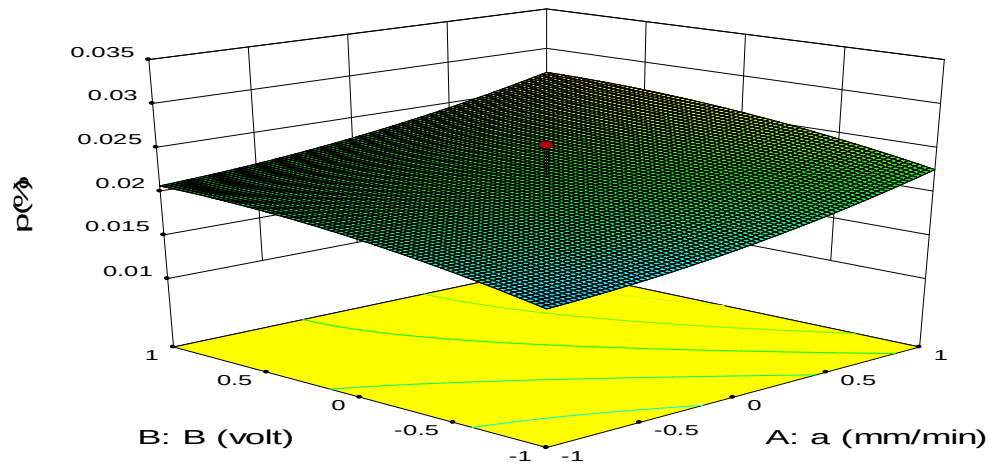


Figure 5 Variation in phosphorous with the volt and mm/min

VI. CONCLUSIONS

Following conclusions were drawn from the research work


- A. Element transfer can be predicted within controllable working parameters by implementing five factorial technique for developing mathematical models.
- B. RSM can be efficiently used in investigating the cause and effect of process variables on response parameters. RSM shows the interaction effect of different input parameter through contour graphs for various output responses.
- C. Maximum value of responses, i.e C, Mn, Si, S, and P are found to be 0.07%, 0.826%, 0.18%, 0.027%, and 0.027%, respectively.

VII. ACKNOWLEDGEMENT

The authors acknowledge the support provide by Delhi Technological University for the project on Application of Response surface methodology for element transfer in submerged arc welding using recycled slag. The authors would also like to thanks, Prof. Sunil Pandey for his guidance in accomplishing the project.

REFERENCES

- [1] <http://www.paton.kiew.ua>, browsed on 20 November 2015.
- [2] Beck, H.P. & Jackson, A.R. 1996. Recycling of SAW Slag Proves Reliable and Repeatable. Welding Journal, 75(66): 51-54.
- [3] Singh, K., Pandey, S. 2009. Recycling of slag to act as a flux in submerged arc welding. Resources, Conservation and Recycling 53: 552-558.
- [4] Singh, K., Pandey, S. & Arul Mani, R. 2005. Effect of Recycled Slag on Bead Geometry in Submerged Arc Welding. Proceedings of International Conference on Mechanical Engineering in Knowledge Age, December 12-14, Delhi College of Engineering, Delhi
- [5] Singh, K., Pandey, S. & Arul Mani, R. 2006. Recycling of Submerged Welding Slag. Australasian Welding Journal, 51(2): 34-38.
- [6] Chai, C. S. & Eagar, T. W. 1982. Slag-Metal Reactions in Binary CaF_2 - Metal Oxide Welding Fluxes. Welding Research Supplement, July: 229s-232s
- [7] Mitra, U. and Eagar, T. W. 1984. Slag metal reactions during submerged arc welding of alloy steels. Metallurgical Transactions A, Vol. 15A, pp. 217-227.
- [8] Pandey, S., Bharti, N.D., Arul Mani, R. & Gupta, S.R. 1994. Effect of submerged arc welding parameters and fluxes on element transfer behaviour and weld-metal chemistry. Journal of Materials Processing Technology, 40: 195-211
- [9] Datta, S., Bandyopadhyay, A. & Pal, P.K. 2008. Modelling and Optimization of features of bead geometry including percentage Dilution in Submerged Arc Welding Consuming Mixture of Fresh Flux and Fused Slag. International Journal of Advanced Manufacturing Technology, 36: 1080-1090.
- [10] Datta, S., Bandyopadhyay, A. & Pal, P.K. 2008. Application of Taguchi Philosophy for Parametric Optimization of Bead Geometry and HAZ Width in Submerged Arc Welding Using Mixture of Fresh Flux and Fused Slag, International Journal of Advanced Manufacturing Technology. vol. 36, pp. 689-698.
- [11] Kanjilal, P., Pal, T.K. & Majumdar, S.K. 2007. Prediction of Element Transfer in Submerged arc Welding. Welding Research Journal (86): 135-146.
- [12] Chandel, R.S. 1998. The Effect of Process Variables on the Flux Consumption in submerged arc welding. Materials and Manufacturing process, 13(2): 181-188
- [13] Montgomery, D.C. 2006. Design and analysis of Experiments. Wiley-INDIA edition, New Delhi.
- [14] Gunuraj, V. & Murugan, N. 1997. Application of response surface methodology for predicting weld bead quality in submerged arc welding of pipes. Journal of Material Processing Technology, 88:266-275.
- [15] Gunaraj V, Murugan N. 2000. Prediction and optimization of weld bead volume for the submerged arc process-Part-1. Welding Research Supplement. 286-294

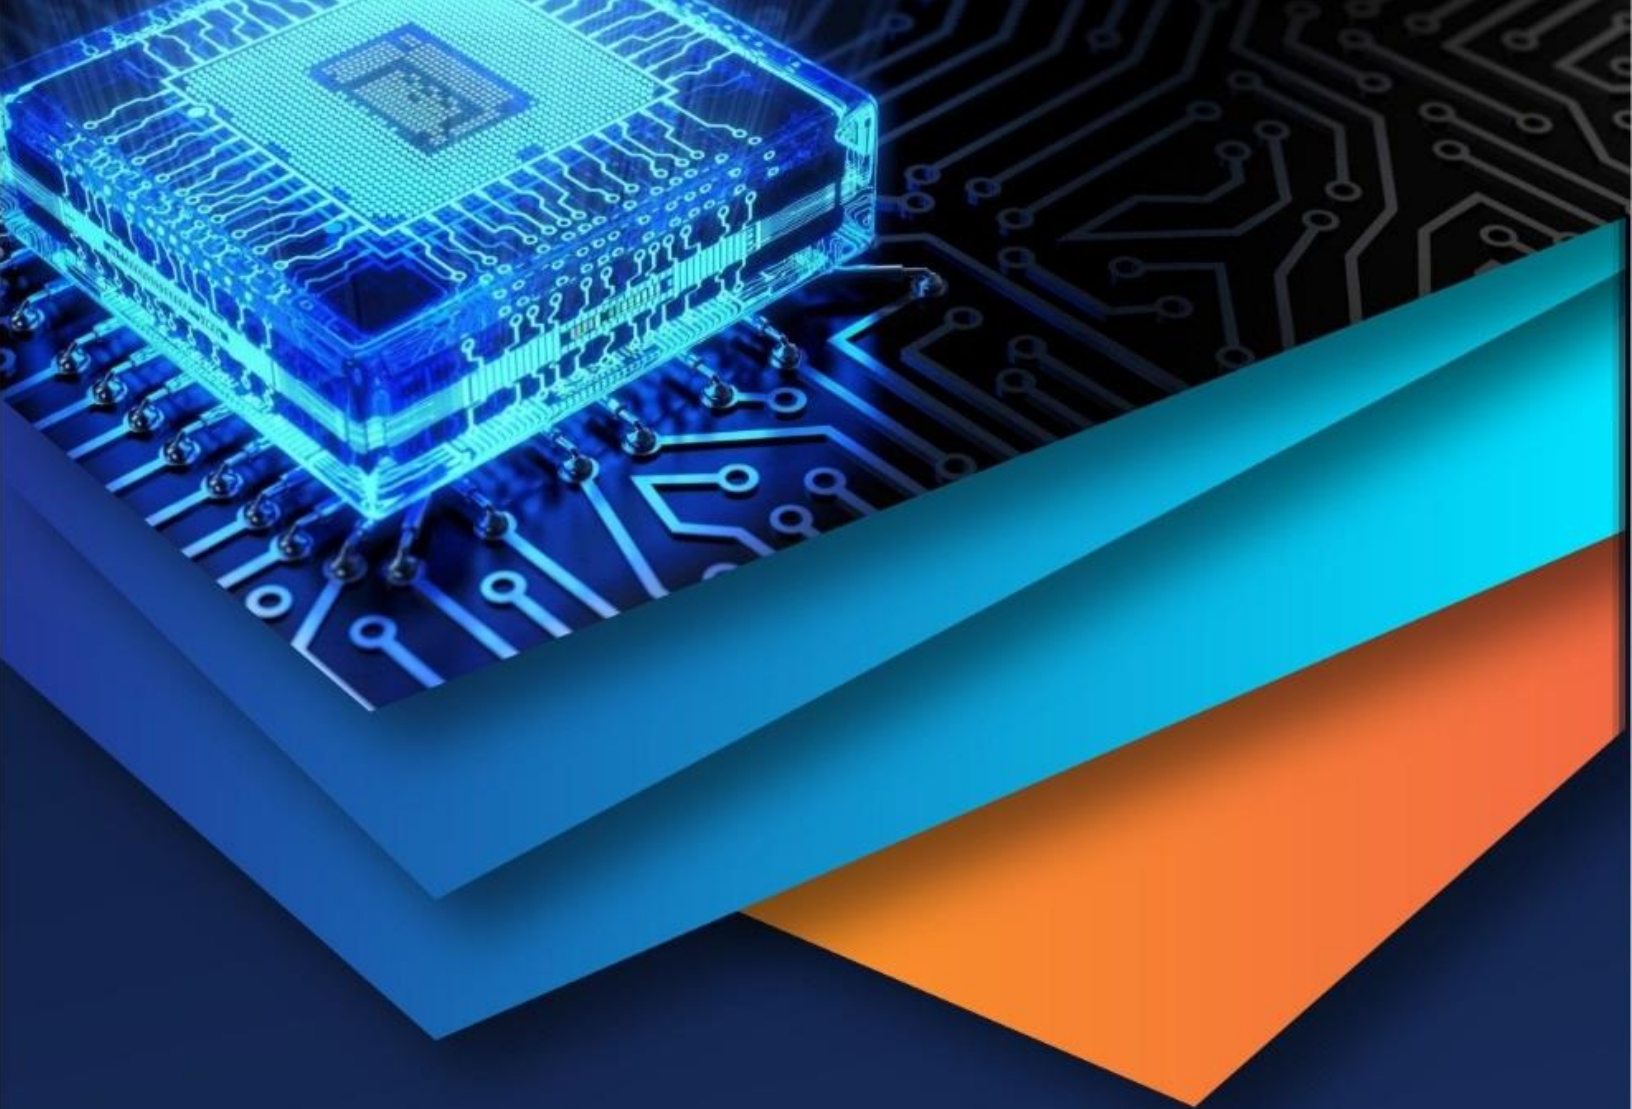

10.22214/IJRASET



45.98



IMPACT FACTOR:
7.129



IMPACT FACTOR:
7.429



INTERNATIONAL JOURNAL FOR RESEARCH

IN APPLIED SCIENCE & ENGINEERING TECHNOLOGY

Call : 08813907089  (24*7 Support on Whatsapp)